

## Synthesis and liquid crystalline properties of a disc-shaped molecule with azobenzene at the periphery

Md Lutfor Rahman,<sup>a,\*</sup> Carsten Tschierske,<sup>b</sup> Mashitah Yusoff<sup>a</sup> and Sidik Silong<sup>c</sup>

<sup>a</sup>*School of Science and Technology, Universiti Malaysia Sabah, Locked Bag 2073, 88999 Kota Kinabalu Sabah, Malaysia*

<sup>b</sup>*Institute of Organic Chemistry, Martin-Luther-University Halle-Wittenberg, Kurt-Mothes Str. 2, Halle D-06120, Germany*

<sup>c</sup>*Department of Chemistry, University Putra Malaysia, 43400 Serdang, Malaysia*

Received 1 November 2004; revised 25 January 2005; accepted 1 February 2005

**Abstract**—A triphenylene-based novel liquid crystal was synthesised whose peripheral cores are six rod-like azobenzene moieties linked through alkyl chains. A disc-shaped molecule 2,3,6,7,10,11-hexakis-[[4-(4-nitrophenylazo)phenoxy]hexyloxy]triphenylene was prepared by using a ferric chloride oxidative trimerisation of 1,2-bis-[[4-(4-nitrophenylazo)phenoxy]hexyloxy]benzene. Differential scanning calorimetry and polarising optical microscopy analysis revealed the existence of a nematic mesophase.  
© 2005 Elsevier Ltd. All rights reserved.

Discotic liquid crystals are usually composed of molecules with a disc-like core and aliphatic tails. Substituted hexaethers of triphenylene have been widely synthesised and studied as discotic mesogens. A number of reported discogens consist of a flat, or nearly flat, rigid core surrounded by a number of aliphatic sidechains having binary, trigonal, tetragonal or hexagonal symmetries. Discotic liquid crystals exhibiting mesophases are used in many device applications.<sup>1,2</sup> The potential uses of these materials as photoconductors,<sup>3</sup> one-dimensional conductors<sup>2,4</sup> and light emitting diodes<sup>5</sup> has attracted considerable attention. Several research groups have been working on the synthesis of functionalised triphenylene-based discotic liquid crystals and their potential applications.<sup>6–10</sup>

An extensive study on the synthesis of discotic liquid crystals, based on a triphenylene, showed most of the compounds to form columnar mesophases.<sup>2,6,11</sup> However, current efforts have been directed towards designing novel molecules, which in some way combine the features of rod-shaped and disc-like molecules having photoactive properties. In one example of the combination of calamitic (rod-shaped) and discotic (disc-shaped) molecules, the discotic and calamitic moieties were


incompatible with the molecular topology and induced the formation of a smectic phase.<sup>12</sup> Compatible combination of discotic and calamitic mesogens results in the formation of a nematic phase.<sup>13</sup>

We have reported that when rod-shaped azobenzene moieties were incorporated into discotic triphenylene molecules having an acrylate backbone via ester linkages, a side group liquid crystal polymer was produced.<sup>14</sup> Recent studied by Shimizu et al.<sup>15</sup> on a triphenylene mesogen with peripheral azobenzene units, shows kinetically controlled bimesomorphism with metastable smectic and stable hexagonal columnar phases created by the rod–disc alternation of the molecular shape, on cooling. This molecule comprised a triphenylene core with six azobenzene units linked via short (C<sub>3</sub>) alkyl chains using ester bonds.<sup>15</sup>

It is well known that photo-orientation of azobenzene units is easily induced through *trans*–*cis*–*trans* isomerisation cycles by irradiating liquid crystalline materials containing chromophores with linearly polarised light. Thus, azobenzene-containing materials have potential technological applications such as in high density optical data storage, optical image processing, dynamic holography, optical computing and pattern recognition.<sup>16–20</sup> In the work described here we have incorporated azobenzene moieties into a triphenylene molecule via alkyl chains (C<sub>6</sub>) using etherification, giving, triphenylene-based discotic liquid crystals having six peripheral rod-like azobenzene units with terminal nitro groups.

**Keywords:** Liquid crystals; Nematic phase; Azobenzene; Disc-shaped molecule.

\*Corresponding author. Tel.: +60883200005742; fax: +6088435324; e-mail: [lutrln@hotmail.com](mailto:lutrln@hotmail.com)

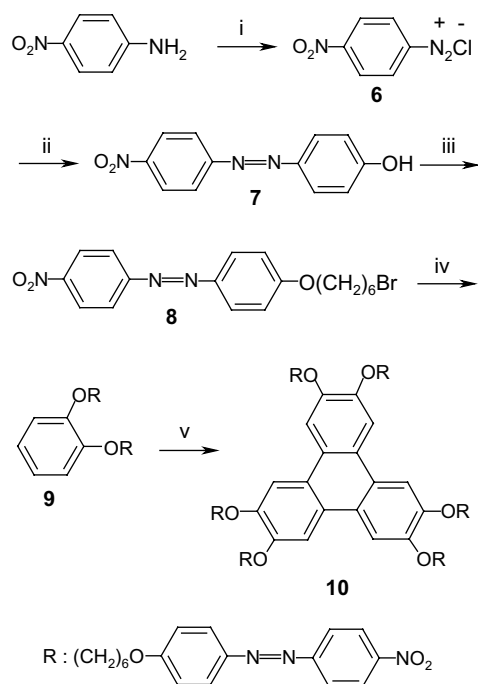

**Scheme 1.** Reagents and conditions: (i)  $\text{NaNO}_2$ , 3 equiv  $\text{HCl}$ ,  $2^\circ\text{C}$ ; (ii)  $\text{NaOH}$ ,  $\text{C}_6\text{H}_5\text{OH}$ ,  $2^\circ\text{C}$ , 64%; (iii)  $\text{K}_2\text{CO}_3$ ,  $\text{KI}$ ,  $\text{Br}(\text{CH}_2)_6\text{Br}$ , reflux, 68%; (iv) catechol,  $\text{K}_2\text{CO}_3$ ,  $\text{KI}$ , reflux, 46%; (v)  $\text{FeCl}_3$ ,  $\text{CH}_2\text{Cl}_2$ ,  $\text{H}_2\text{SO}_4$ , rt, 26%.


Scheme 1 outlines our synthetic approach. The peripheral units of the mesogenic part were prepared by diazotisation of 4-nitroaniline and then coupling of diazonium salt **6** with phenol yielding 4-(4-nitrophenylazo)phenol **7**. The flexible spacer was introduced by alkylation of phenol **7** with a 10-fold excess of 1,6-dibromohexane in the presence of potassium carbonate as base to give 1-bromo-4-(4-nitrophenylazo)phenoxyhexane **8**. Com-

pound **8** was used to dialkylate catechol, in the presence of potassium carbonate, to give 1,2-bis-[4-(4-nitrophenylazo)phenoxyhexyloxy]benzene **9**. Finally, a disc-like molecule, 2,3,6,7,10,11-hexakis-[4-(4-nitrophenylazo)phenoxyhexyloxy]triphenylene **10** was prepared by oxidative cyclotrimerisation of **9** with ferric chloride as the oxidant (Scheme 1).

The structures of the intermediates and the final compound were confirmed by spectroscopic analysis. The  $^{13}\text{C}$  NMR spectrum of **10** (Fig. 1), had signals corresponding to all the carbon atoms of **10** (only one azobenzene unit is shown in detail in Figure 1, that is,  $\text{R} = \text{O}(\text{CH}_2)_6\text{OC}_6\text{H}_4-4-\text{N}_2-\text{C}_6\text{H}_4-4-\text{NO}_2$ ). There are 18 carbon atoms in the triphenylene core but only three distinct positions (x, y, z). The x, y and z positions correspond to three signals and all other signals correspond to the carbon atoms of the six rod-shaped azobenzene moieties and the alkyl chains (Fig. 1).

**Mesomorphic properties:** The phase transition temperatures as well as the phase transition enthalpy changes were determined using differential scanning calorimetry (DSC). The DSC thermograms of **10** showed two endothermic peaks at  $133.9$  and  $146.1^\circ\text{C}$  and the enthalpy changes of these transitions were  $49.4$  and  $1.56\text{ J g}^{-1}$ , respectively (Fig. 2). On cooling, two exothermic peaks were also observed at  $141.3$  and  $102.7^\circ\text{C}$  and the enthalpy changes of these transitions were  $2.25$  and  $46.4\text{ J g}^{-1}$ , respectively.

The phase structures were determined by polarising optical microscopy. The polarised optical micrograph of **10**, observed in the liquid crystalline phase upon cooling, is shown in Figure 3. On cooling the isotropic phase, a schieleren texture was observed under the polarising microscope at  $136.5^\circ\text{C}$  (Fig. 3). This schieleren texture is of high fluidity and the optical texture is of a

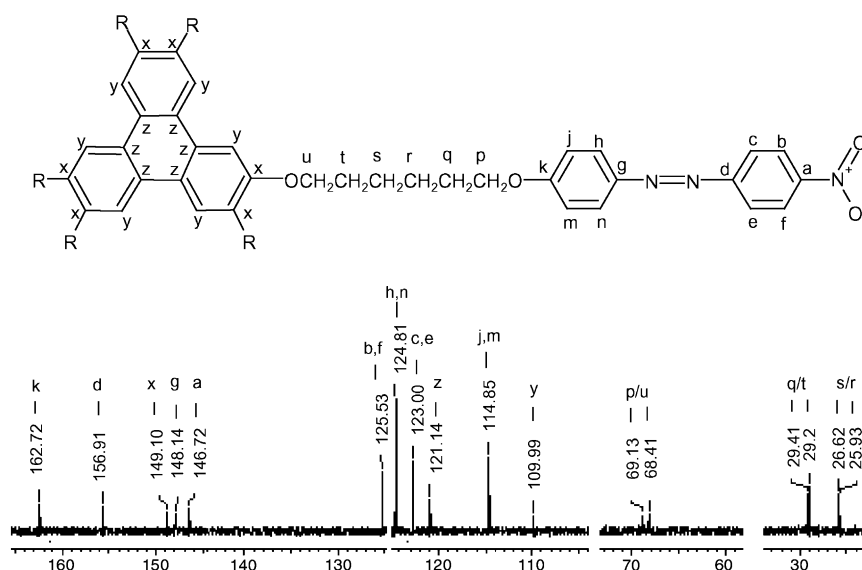

**Figure 1.**  $^{13}\text{C}$  NMR spectrum of **10**. Only one azobenzene unit with an alkyl chain is shown in the chemical structure, that is,  $\text{R} = \text{O}(\text{CH}_2)_6\text{OC}_6\text{H}_4-4-\text{N}_2-\text{C}_6\text{H}_4-4-\text{NO}_2$ .

Download English Version:

<https://daneshyari.com/en/article/5292957>

Download Persian Version:

<https://daneshyari.com/article/5292957>

[Daneshyari.com](https://daneshyari.com)