



Isothermal decomposition behavior of the high nitrogen concentration γ -Fe[N] prepared from pure iron

Zhijun Jiang, Xiaoling Li, Jianfeng Gu*, Mingjuan Hu, Zuchang Zhu

Shanghai Key Laboratory of Materials Laser Processing and Modification, School of Materials Science and Engineering, Shanghai Jiao Tong University, Shanghai 200240, China

ARTICLE INFO

Article history:

Received 7 April 2008

Received in revised form 26 May 2008

Accepted 26 May 2008

Available online 7 July 2008

PACS:

61.10.Nz

82.30.Lp

77.84.Bw

Keywords:

Heat treatment

Hardness

High nitrogen steels

Isothermal transformation

Precipitation

ABSTRACT

The isothermal decomposition characteristic of the homogeneous high nitrogen austenitic samples prepared by a new multi-stage nitriding process was investigated by SEM and TEM in this paper. Lamellar-structure precipitations arranged on the decomposed austenite grain boundaries (GBs) and the flaky γ' particles and network-structure precipitations appeared inside of the γ matrix. The extra high Vickers hardness more than 800 HV was found in the 5-h aged samples, which was different from those of the bainitic/martensitic structures in Fe–C alloys. The SAED analysis indicates the γ' has the coherent relation with the parent γ -Fe[N] phase and the interstitial nitrogen atoms are inclined to aggregate on $\{110\}\gamma'/\gamma$ planes, which also contributes to the hardness of the matrix.

© 2008 Elsevier B.V. All rights reserved.

1. Introduction

Dissolved nitrogen atoms in austenitic stainless steels can stabilize the austenite grains and bring them high strength, good impact toughness, excellent corrosion resistance and other benefits [1]. Although new techniques such as high-pressure melting and powder metallurgy methods have been developed for many years, the production of high nitrogen steels (HNSs) has a major obstacle of its low solubility of nitrogen in liquid Fe (<0.045 wt.% at atmospheric pressure) [2,3]. The difficulties in preparing the HNSs samples also greatly restrict the experimental researches on their mechanical, thermal or corrosion properties. Simultaneously, the decomposition mechanisms of high nitrogen austenite are still somewhat unclear, especially the nucleation mechanism of the nitride precipitation from the parent phases and the growth of the ferrite lath on the austenitic grain boundaries (GBs) [4–9].

In the present work, two specially designed contrastive gas-nitriding processes were carried out at an elevated temperature

higher than that used in traditional gas-nitriding process to prepare high nitrogen concentration austenite samples. Micro-structure observations and hardness analysis were performed on both the as-quenched and the aged samples to investigate the decomposition behavior of the high nitrogen concentration austenite.

2. Experimental

Pure-iron samples with the thickness of 100 μm were annealed in the hydrogen protection atmosphere at 1100 °C for 8 h, and then nitrided in the quartz tube furnace with the inner diameter of 45 mm at 645 °C. The nitriding atmosphere consists of the gaseous ammonia and the gas mixture of nitrogen and hydrogen, which decomposed from other ammonia gas source. In process one, the annealed samples were single-stage nitrided in the atmosphere of 15 vol.%NH₃ + 64 vol.%N₂ + 21 vol.%H₂ for 3 h and then oil quenched. In process two, other samples were two-stage nitrided: (1) in the atmosphere as the former gas content for 6 h, and (2) in the atmosphere of 5 vol.%NH₃ + 72 vol.%N₂ + 23 - vol.%H₂ for another 2 h. After nitriding, these samples were isothermally aged at 225 °C in the salt bath for different durations and then water quenched.

* Corresponding author. Tel.: +8621 34203743; fax: +8621 34203742.

E-mail address: gujf@sjtu.edu.cn (J. Gu).

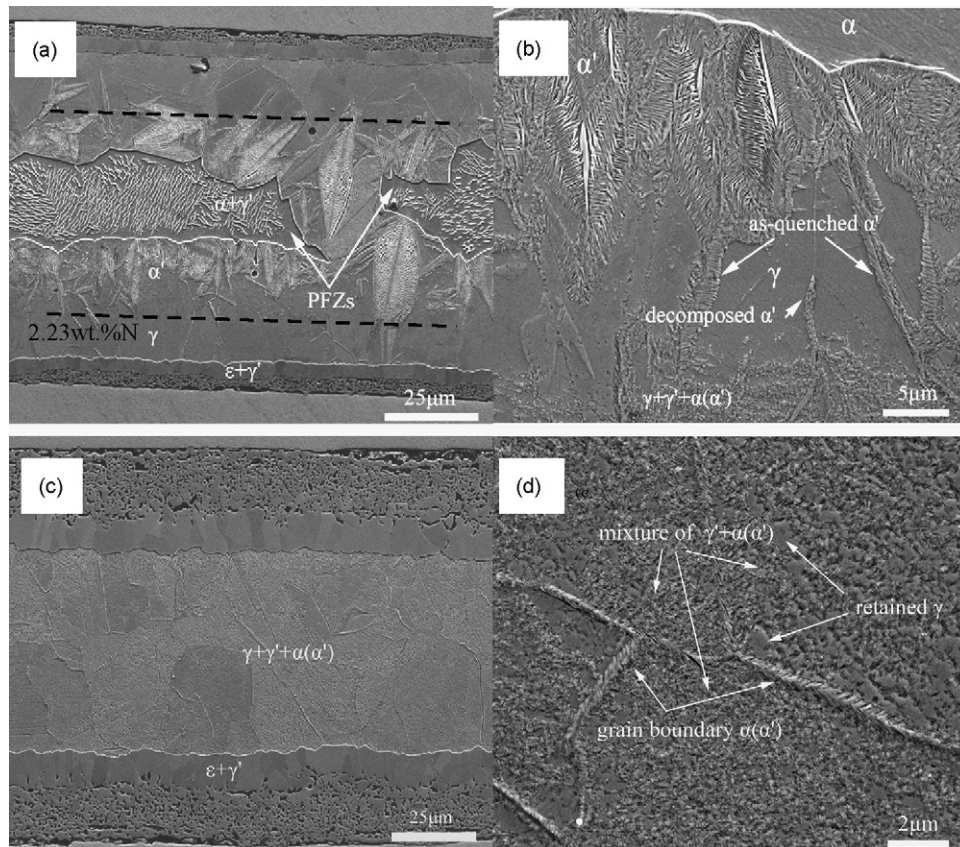


Fig. 1. SEM micrographs of the aged Fe–N samples. (a) Cross-section of the single-stage nitrided and 5-h aged sample; (b) austenite region in single-stage nitrided sample; (c) cross-section of the 6 + 2-h nitrided and 5-h aged sample; (d) austenite region in two-stage nitrided sample.

Microstructures of the nitrided or the aged samples were observed by the scanning electron microscope (Philips FEI Quanta 200), and their microhardness was tested by the Vickers hardness tester (MH-6). The aged samples were prepared to thin foils, electric polished in the solution of 10% perchloric acid and 90% acetic acid at the room temperature, and observed by the transmission electron microscope (JEOL JEM-2010 200 kV). Some aged austenite samples were also determined by X-ray diffraction apparatus (D/Max-2200 Cu K α 40 kV).

3. Results and discussion

3.1. Preparation and ageing process of high nitrogen austenite

The conventional gas nitriding is usually carried out within the temperature range between 500 and 550 °C, however in this work, pure-iron foils (Fe > 99.97 wt.%) were nitrided at 645 °C which is much higher than the eutectoid austenitic temperature (590 °C) of the Fe–N alloy [10]. The designedly elevated temperature brings an additional austenitic transformation to this gas–solid reaction and diffusion process. To obtain the single-phased and homogenous austenite layer, the two-stage nitriding process was put forward. At the first so-called “boost-nitriding” stage, the pure-iron samples were held in the atmosphere with higher Nitrogen potential (N_p) [11]; while at the second so-called “diffusing” stage, the N_p value was decreased to a lower level by adjusting the volume ratio of NH₃ as mentioned above. The higher N_p value in the first stage helps to offer plenty of free nitrogen atoms into the surface layer and accelerate the nitrogen diffusing. However, the lower one in the second stage slows the growth of the nitride layer and homogenize the nitrogen distribution in the γ matrix.

Fig. 1 shows the clear SEM micrographs of the separated layers relative to the different Fe–N phases obtained from the nitrided and the aged samples. The surface nitride layer in Fig. 1(a), i.e. the so-called white layer, consists of the ϵ -Fe₂₋₃N and γ' -Fe₄N compounds and keeps growing thicker during the nitriding process. The γ -Fe[N] grains nucleate on the interface of the white layer and the original ferrite layer and form a new austenite layer between them. With the moving of the γ/α interface, this new γ layer grows thicker and makes the ferrite layer shrinking to the center.

Bell [12] has given out a relationship between the martensite transformation start temperature (M_s) and nitrogen content (N_c) as: M_s (°C) = 533 – 228 N_c (wt.%). According to this formula, the suppositional boundaries which divide the γ layer into the high-N and low-N regions can be marked out as 2.23 wt.%N lines. The low-N austenite region adjacent to α phase has sheared to α' -Fe[N] martensite when it was oil-quenched to the room temperature (25 °C) after nitriding, while the high-N region adjacent to the surface still remains the austenitic state.

In the low-N austenite region, the plate martensite of α' -Fe[N] has decomposed into the tempered martensite after aged in the salt bath for 5 h, as shown in Fig. 1(b). At the same time, the high-N region decomposed into the dispersed α and γ' precipitates, which nucleated both inside of the matrix and on the GBs. Their shapes and grain sizes are much different from those of the as-quenched plate martensite.

Fig. 1(c) shows the SEM micrograph of the single-phased austenite with the white layers in a two-stage nitrided sample. The α -Fe[N] grains have completely disappeared and the γ grains have encountered at the center and homogenized due to the nitrogen diffusing. The nitrogen content of γ phase is about 2.5 wt.%

Download English Version:

<https://daneshyari.com/en/article/5361095>

Download Persian Version:

<https://daneshyari.com/article/5361095>

[Daneshyari.com](https://daneshyari.com)