



## Regular article

## Highly stretchable kirigami metallic glass structures with ultra-small strain energy loss

S.H. Chen<sup>a</sup>, K.C. Chan<sup>a,\*</sup>, T.M. Yue<sup>a</sup>, F.F. Wu<sup>a,b</sup><sup>a</sup> Advanced Manufacturing Technology Research Centre, Department of Industrial and Systems Engineering, The Hong Kong Polytechnic University, Hung Hom, Kowloon, Hong Kong<sup>b</sup> School of Materials Science and Engineering, Liaoning University of Technology, Jinzhou 121001, China

## ARTICLE INFO

## Article history:

Received 21 July 2017

Received in revised form 22 August 2017

Accepted 22 August 2017

Available online xxxx

## Keywords:

Metallic glasses

Kirigami structures

Elasticity

Strain energy loss

Cyclic loading

## ABSTRACT

Some highly stretchable kirigami metallic glass (MG) structures with ultra-small strain energy loss during cyclic loading are developed. Less than 3% of strain energy loss is achieved after 1000 loading/unloading cycles, which is much smaller than the Kapton or nanocomposites-based kirigami structures. By optimizing the kirigami pattern design and smoothing the kirigami cuts may further reduce the stress energy loss, and one kirigami MG structure even shows no obvious strain energy loss. They are potentially useful for developing reversible mechanical metamaterials/devices or substrates of functional optoelectronic devices.

© 2017 Acta Materialia Inc. Published by Elsevier Ltd. All rights reserved.

Kirigami structures, based on the ancient art of paper cutting, are being used extensively to develop metamaterials with novel mechanical and functional properties [1–8]. They are potentially useful for developing optoelectronic and optical devices, such as stretchable lithium-ion batteries [9], solar cell tracking systems [3], beam steering devices [10, 11], and triboelectric nanogenerators [12]. Besides the large apparent elasticity which can maintain the periodicity under cyclic loading, they have programmable elasticity with accurately-engineered tilted angles and out-of-plane buckling orientation of the elements [3,13]. The kirigami approach can be used to obtain predictable strain-property relationships in mechanical metamaterials, which are beneficial for developing stretchable optoelectronic and mechanical metamaterials/devices [1]. For example, Lamoureux et al. have reported that kirigami-based stretchable solar cell trackers not only have increasing energy generation efficiency, without significantly increasing the installation costs, but also expand the application of solar tracking systems [3]. Xu et al. have developed beam steering devices using kirigami nanocomposites, which can serve as optical device components in radar systems [10]. However, to maintain a long serving life, it is required that kirigami structure-based devices can maintain their elastic performance after a large number of cyclic loadings, where conventional materials severely limit the cycle life and significantly hinder their applications [10]. It has been reported that the polyimide film kirigami structure has about 18% elastic strain energy loss after 1000 cycles [1], and Kapton kirigami solar trackers also have large elastic strain energy loss up to


about 74% after 1000 cycles [3]. Therefore, there is a great need to reduce the strain energy loss of kirigami structures while maintaining the excellent elastic performance before more widespread applications of the kirigami structures in optoelectronic and mechanical metamaterials/devices can be achieved.

Metallic glasses (MGs), also known as amorphous metals, have high strength approaching the theoretical values and a relatively-larger elasticity of about 2% as compared with the conventional crystalline metals [14–16]. In this work, in order to improve the elastic performance of kirigami structures, we have developed some kirigami structures using MG films. The results have shown that kirigami MG structures not only possess programmable stretchability similar to other material-based kirigami structures, but also have elasticity larger than 198% and ultra-small strain energy losses less than 3%. Kirigami MG structures could be used in mechanical metamaterials/devices or substrates for optoelectronic devices, opening a new window for developing kirigami structures with extended cycle life.

Four kinds of kirigami structures (two straight and two curved patterns) were fabricated using MG and stainless steel films, respectively, by photochemical machining (PCM) (Fig. 1). Fe<sub>73.5</sub>Si<sub>13.5</sub>B<sub>9</sub>Cu<sub>1</sub>Nb<sub>3</sub> MG films of thickness ~ 20 μm were fabricated by rapid quenching the liquid mixture of pure elements onto a high-speed roller under an Ar atmosphere. The amorphous state of the MG films was checked using standard X-ray diffraction (XRD) analysis on a Rigaku Smartlab X-ray diffractometer (see the XRD patterns in Fig. 1a inset). The 304 stainless steel films, with thickness of ~20 μm, were bought from the market. Details of the fabricating process of kirigami MG and stainless steel structures are given in Fig. 1a. Photo-resists were firstly spread on the

\* Corresponding author.

E-mail address: [kc.chan@polyu.edu.hk](mailto:kc.chan@polyu.edu.hk) (K.C. Chan).

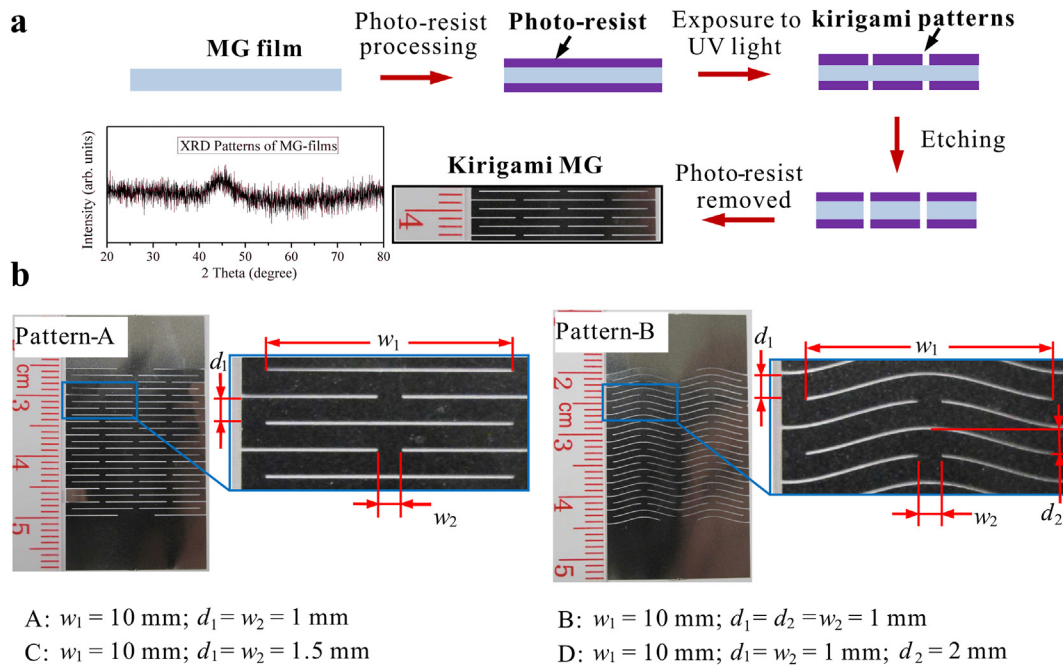

**Fig. 1.** Fabrication of kirigami MG structures. (a) Fabrication process of kirigami MG structures using photochemical machining (PCM), where in inset XRD patterns confirm the amorphous state of the MG films; (b) straight (A and C) and curved (B and D) patterns for fabricating kirigami MG structures, where the representative Patterns A and B are given as examples.

surface of both kinds of films. Thereafter, exposure of the composite films to UV light creates varying kirigami patterns on the surface of the metal films. The patterned films were then immersed into corrosive solutions to remove the cuts in the films by etching. Finally, the kirigami MG structures and steel structures were prepared by removing the photo-resists. The kirigami structures were tested on an Instron 3344 materials testing machine with a load cell of  $\pm 10 \text{ N}$ . To characterize the elastic strain energy loss of the kirigami MG structures, 1000 cycles of loading/unloading were conducted. After the mechanical tests, the stress-concentration regions of the kirigami structures were inspected using SEM on a Jeol JSM-6490 scanning electron microscope. Finite Element Modelling (FEM) analysis of the buckling of the kirigami structures with pattern A has been conducted. The input material parameters for the MG films are 200 GPa for Young's modulus [17], 4000 MPa for yield strength [17] and 0.323 for the Poisson's ratio [18], respectively. The input material parameters for 304 stainless steel are 200 GPa for Young's modulus [19], 231 MPa for yield strength [19] and 0.28 for the Poisson's ratio [19], respectively.

Since a kirigami structure can evolve into a 3D structure during the loading process, the elasticity of the kirigami structure cannot be determined by the conventional elasticity rules from the linear stage of the stress-strain curves for rigid materials. In order to determine the elastic strain of kirigami structures, cyclic loading was applied to stretch the kirigami structures by increasing the axial displacement step by step. The elasticity of the kirigami structures was determined by comparing the loading and unloading curves after each step in the loading/unloading process. The results have shown that kirigami stainless steel structures have elastic strains less than 62%, 59%, 28% and 57% for patterns A–D, respectively (Fig. 2), where the load decrease in the unloading curves, as compared with the loading curves, is obvious. While the kirigami MG structures have not shown an obvious decrease of load between the loading and unloading curves, suggesting elastic strains larger than 165%, 198%, 85% and 190% for patterns A–D, respectively. With increase of the dimensions of the kirigami patterns ( $d_1$  and  $w_2$  in Fig. 1b), the nominal elastic limits of the kirigami structures decrease significantly for both MG and stainless steel structures (Fig. 2a and c). On the other hand, by tuning the straight kirigami cuts into curved ones, the nominal elastic limits increase significantly for kirigami

MG structures. In the case of kirigami stainless steel structures, significant increase in the elastic limit has not been observed, suggesting that the elastic performance of kirigami MG structures might be more sensitive to the change of the kirigami patterns.

The increase of the elasticity in the kirigami MG structures as compared with the kirigami stainless steel structures may result from the relatively high strength (4000 MPa for MG and 231 MPa for stainless steel) and the large elastic limit of the MGs, where the same orders of stress concentration on the kirigami structures can lead to plastic deformation in stainless steel while the MG is still in the elastic state [20]. The findings show that the elastic properties of the parent materials have significant impact on the elastic performance of kirigami metal structures, and the use of MG films as parent films could be an effective way to obtain large elastic strains for developing optoelectronic and mechanical metamaterials/devices. It should be noted that kirigami paper structures have an obvious change of the deformation regime from rigid elasticity to the out-of-plane buckling in the load-nominal strain curves [21], which is not observed in most kirigami MG/steel structures in the present work. This is because that present MG and steel films have thicknesses of  $\sim 20 \mu\text{m}$ , which are far less than the distance between the cuts ( $d = 1 \text{ mm}$ ,  $1.5 \text{ mm}$ ) [21].

Maintaining the periodicity of the kirigami structures with accurately-controlled mechanical and functional properties is an important aspect in achieving a long cycle life, which requires the kirigami structures to have negligible elastic strain energy loss. However, strain energy loss is unavoidable under cyclic loading for conventional materials, such as plastics and crystalline metals, where the fatigue life is limited, especially when stretched to plastic deformation. In this work, we show that the kirigami MG structures have ultra-small strain energy loss after 1000 cycles (due to the limited nominal elastic strains being less than 62%, the cyclic loading tests were not conducted for the kirigami stainless steel structures). As shown in Fig. 3, at nominal strains reaching about 165%, 158%, 71% and 152% for patterns A–D, respectively, the load-nominal strain curves at cycle 1000 match well with the curves at cycle 1, implying small strain energy losses for 1000 cycles. By integrating the load-nominal strain curves, the strain energy loss of the kirigami MG structures with patterns A–C have been calculated as  $\sim 2.4\%$ ,  $\sim 2.8\%$  and  $\sim 1.4\%$ , respectively. No obvious strain energy loss

Download English Version:

<https://daneshyari.com/en/article/5443182>

Download Persian Version:

<https://daneshyari.com/article/5443182>

[Daneshyari.com](https://daneshyari.com)