



Regular article

Critical bending radius of thin single-crystalline silicon with dome and pyramid surface texturing



Jeong-Hyun Woo^a, Young-Cheon Kim^a, Si-Hoon Kim^a, Jae-il Jang^b, Heung Nam Han^c, Kyoung Jin Choi^{a,d}, Inho Kim^{d,e}, Ju-Young Kim^{a,d,*}

^a School of Materials Science and Engineering, UNIST (Ulsan National Institute of Science and Technology), Ulsan 44919, Republic of Korea

^b Division of Materials Science and Engineering, Hanyang University, Seoul 04763, Republic of Korea

^c Department of Materials Science and Engineering, Seoul National University, Seoul 08826, Republic of Korea

^d KIST–UNIST Ulsan Center for Convergent Materials, UNIST, Ulsan 44919, Republic of Korea

^e Center for Electronic Materials, KIST (Korea Institute of Science and Technology), Seoul 02792, Republic of Korea

ARTICLE INFO

Article history:

Received 25 May 2017

Accepted 24 June 2017

Available online xxxx

Keywords:

Surface modification

Bending test

Solar cells

Finite element analysis

Stress concentration

ABSTRACT

Four-point bending tests are performed on 50- μm -thick single-crystalline silicon (Si) wafers with dome- and pyramid-shaped surface patterns, which are used as flexible Si solar cells. Surface patterns, which act as stress concentrators, reduce the flexural strengths, leading to larger critical bending radius. The critical bending radii of surface-textured Si are much smaller than the calculated values for a single-notch geometry. The finite element analysis shows that the stress concentrations at the tips of the surface patterns effectively disperse in fine and periodic dome and irregular pyramid patterns.

© 2016 Acta Materialia Inc. Published by Elsevier Ltd. All rights reserved.

Among the various types of solar cells, crystalline silicon (Si) solar cells are widely used owing to their high energy-conversion efficiency and application feasibility. Recently, thin Si solar cells with a typical wafer thickness of $\leq 100 \mu\text{m}$, which are flexible and possess the advantages of Si solar cells, have been developed. Thin Si wafers are fragile [1]; thus, understanding the critical bending radius is important. Surface texturing of Si wafer has been widely used to reduce reflectivity and enhance light-trapping efficiency [2,3]. However, the textured surface patterns in these Si wafers act as stress concentrators for mechanical deformation, which can reduce the flexibility of thin Si solar cells [4]. The widely used surface texturing in Si wafers is the patterning of irregular pyramids, which is accomplished by chemical etching using potassium hydroxide (KOH) solution in which the etch rates are dependent of the crystallographic orientations of Si [4,5]. Meanwhile, the reflectivity is reduced to approximately 15% due to pyramid surface texturing, and the flexural strength is weakened even in thick Si wafers. On the other hand, thin single-crystalline Si solar cells with surface texturing have been reported to demonstrate higher power conversion efficiency in a bent state and are more durable for cyclic bending [6,7]. When a Si wafer has a single large notch, surface texturing in a fine and periodic array enhances the flexural strength of the Si wafer because the stress

concentration at the large notch is effectively dispersed by the surface texturing [8]. The mechanical behavior of thin single-crystalline Si wafers with surface texturing strongly depends on the shape, scale, and distribution of the textured patterns; thus, investigating the effects of surface texturing on the flexibility of thin Si wafers are highly required.

In this study, we perform surface texturing with dome and pyramid shapes on a 50- μm -thick single-crystalline Si wafer. We carry out four-point bending tests on three samples with non-, dome-, and pyramid-textured surfaces. They show elastic bending followed by catastrophic failures. The flexural strengths are analyzed using Weibull distribution, and the critical bending radii are measured. We find that the dome surface texturing has higher flexural strength and smaller critical bending radius than the pyramid surface texturing, whereas the light reflectance is similar to or lower than that of the pyramid-textured sample [9], suggesting that dome pyramid surface texturing is more appropriate for flexible solar cells.

Fig. 1 shows the fabrication procedures of the textured thin Si samples. Both side-polished (100) Si wafers with a thickness of 300 μm were chemically etched in 45 wt% KOH solution at 90 °C from which we obtained 50- μm -thick thin Si wafers, which refers to a flat surface or a non-textured sample. Using the thin Si wafers, we performed surface texturing on the dome- and pyramid-textured surfaces. Fig. 1(a) shows the procedure for the dome-textured surface. SiO_2 beads with a diameter of 500 nm, which acted as a hard mask in the subsequent reactive ion etching (RIE) process, were spread on a flat surface in a

* Corresponding author at: School of Materials Science and Engineering, UNIST, Ulsan 44919, Republic of Korea.

E-mail address: juyoung@unist.ac.kr (J.-Y. Kim).

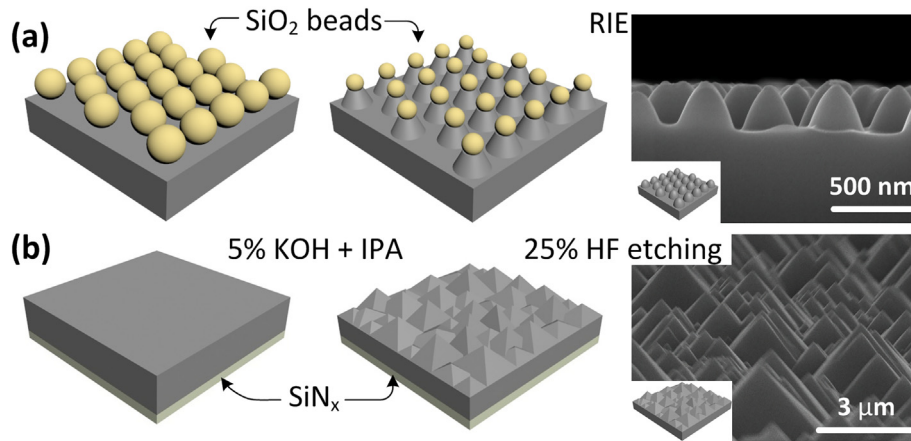


Fig. 1. Procedures for (a) dome and (b) pyramid texturing.

packed monolayer by spin coating. This surface was subjected to RIE using CF_4 gas and O_2 plasma until the SiO_2 beads were removed. Nano domes with a height of 300 nm were patterned. To form a pyramid-textured surface, we deposited a 400-nm-thick Si nitride layer as a protective layer at the backside of the wafers using plasma-enhanced chemical vapor deposition and immersed the wafers in 5 wt% KOH and 20 vol% isopropyl alcohol-mixed solution at 70 °C for 30 min. As a result of the anisotropic etch rate of Si in low-concentration KOH solution, randomly distributed pyramids were formed on the surface [5]. Fig. 1(b) shows that the height of the pyramids ranged from 3 to 10 μm . The Si nitride protective layer was removed using a 25 wt% hydrogen fluoride solution. Three samples, namely, non-, dome-, and pyramid-textured samples, were machined in the shape for a four-point bending test with a width of 3 mm and a length of 13 mm using laser scribing. Four-point bending tests were carried out at a loading rate of 2 $\mu\text{m}/\text{s}$, and movie recording was performed using a universal testing machine (Instron 5948). Because of the catastrophic failure of the three samples, at least 30 four-point bending tests were performed for each sample [10].

The stress and strain distributions were analyzed by finite element analysis (FEA). Abaqus 6.12 and Abaqus CAE were used for the FEA simulations and creation of input files, respectively. A two-dimensional deformable shell model was applied, and sample geometries in FEA were designed based on typical cross-sectional scanning electron microscopy (SEM) images of the experimental samples. Young's modulus of 169 GPa and Poisson's ratio of 0.27 were set as the mechanical properties of the Si wafer [11–13].

Fig. 2 shows the Weibull distribution of the flexural strengths, where $P(f)$ on y-axis is the survival probability of a brittle material. Flexural strength σ_f is calculated using the following equation:

$$\sigma_f = \frac{3PL}{4bd^2}, \quad (1)$$

where P , L , b , and d are the fracture force, distance of 8 mm between the support spans, sample width of 3 mm, and sample thickness, respectively. Characteristic strength σ_0 which corresponds to a survival probability of 37% [8,14,15], is 138.5 MPa for the non-textured samples, 103.4 MPa for the dome-textured samples, and 89.8 MPa for the pyramid-textured samples. The characteristic strength of the flexural strength is on the order of non-, dome-, and pyramid-textured Si samples. Surface texturing forms surface notches that act as stress concentrators; thus, the flexural strengths of the dome- and pyramid-textured samples are lower than that of the non-textured sample. Pyramid texturing can likely form sharper and deeper notch than dome texturing, resulting in higher flexural strength of the dome-textured Si sample, which will be discussed in detail later. Weibull modulus m is

3.28 for the non-textured samples, 5.0 for the dome-textured samples, and 5.21 for the pyramid-textured samples. The Weibull modulus corresponds to the magnitude of scattering in the data. A lower Weibull modulus results in wider distribution [16]. The three samples all show elastic bending and catastrophic failure in the four-point bending tests, which means that the flexural strength depends on the highest stress concentrator between the inner spans where identical tensile stress is applied at the surface. The thin Si wafer with a flat surface has the lowest Weibull modulus than the two textured surfaces. This result indicates that the flexural strength of a non-textured sample depends on the probability of containing the highest stress concentrator that is possibly generated in the thinning process by wet etching or wafer growth [8,17,18]. In the other two surface-textured samples, surface texturing most likely provides the highest surface concentrators. The pyramid-textured sample has a higher Weibull modulus than the dome-textured sample, which implies that irregular stress concentrators are introduced at the pyramid-textured surface.

Fig. 3(a) shows typical cross-sectional SEM images of a fracture surface for the dome- and pyramid-textured samples. The dome texturing formed V-shape notches with notch angle α of 75° and tip radius r of 60 nm. SiO_2 beads with hard mask RIE for dome texturing were spun-coated in the form of closed-packed monolayer in most areas where periodic domes were formed. In the pyramid-textured samples, V-shaped notches with $\alpha = 70.5^\circ$ and $r = 28$ nm were formed. The size of the pyramids was irregular, ranging from a pyramid height of 3 to 10 μm , and the tip radius was not dependent on the pyramid size. The schematic

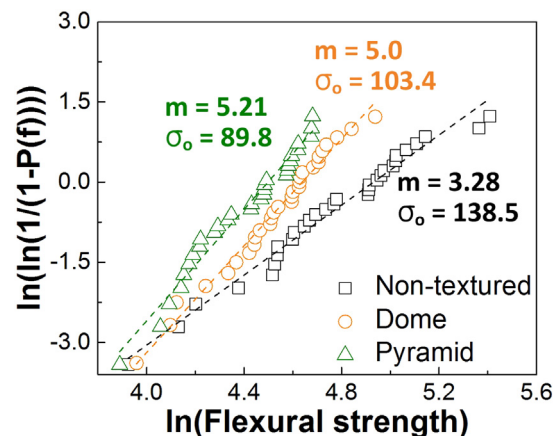


Fig. 2. Weibull distribution for flexural strength.

Download English Version:

<https://daneshyari.com/en/article/5443285>

Download Persian Version:

<https://daneshyari.com/article/5443285>

[Daneshyari.com](https://daneshyari.com)