



## Regular article

## Shape memory zirconia foams through ice templating



Xueying Zhao, Alan Lai, Christopher A. Schuh \*

Department of Materials Science and Engineering, Massachusetts Institute of Technology (MIT), Cambridge, MA, USA.

## ARTICLE INFO

## Article history:

Received 26 February 2017

Received in revised form 24 March 2017

Accepted 24 March 2017

Available online xxx

## Keywords:

Freeze casting

Foams

Shape memory effect

Martensitic phase transformation

## ABSTRACT

Ceria doped zirconia has been shown to exhibit enhanced shape memory properties in small volume structures such as particles and micropillars. Here those properties are translated into macroscopic materials through the fabrication of zirconia foams by ice templating. Directional freezing is used to produce foams with micron-sized pores and struts that can locally take advantage of the shape memory effect due to their fine scale. The foams are subjected to thermal cycling and x-ray diffraction analysis to evaluate the martensitic transformation that underlies shape memory properties, and are found to survive the transformation through multiple cycles.

© 2017 Acta Materialia Inc. Published by Elsevier Ltd. All rights reserved.

The shape memory effect in partially stabilized zirconia ceramics was discussed as early as three decades ago, but because zirconia is brittle and susceptible to cracking during the martensitic transformation, its shape memory behavior was limited to low strains and few cycles [1–3]. Recently, Lai et al. were able to alleviate the cracking problem in shape memory ceramics by producing oligocrystalline and single-crystalline structures in small volumes [4]. At the scale of a micron or so, zirconia pillars [5] and particles [6] exhibit improved shape memory properties compared with bulk zirconia, namely much larger strains (up to ~8%) and the ability to cycle through the transformation many times (up to hundreds) without cracking. The origin of this size effect lies in the relief of constraint; the paucity of grain boundaries and prevalence of free surfaces lead to transformation stress accommodation rather than cracking.

It would be highly desirable to construct macroscale materials from such micro-scale structures, in order to translate the desirable shape memory properties of ceramics to applications with scales greater than the micrometer level. In related shape memory materials such as the copper-based [7] and magnetic [8] shape memory alloys, such scaling has been accomplished by a variety of approaches, including through the formation of long microfibers or open-cell foams [9]. The three dimensional geometry of a foam is attractive for large-scale forms, while their porosity admits a large area of free surfaces to accommodate the transformation stresses that would otherwise lead to cracking [10,11]. Such approaches should be relevant to shape memory ceramics as well, and our purpose in this letter is to demonstrate the first shape memory ceramic material with bulk dimensions, produced

as a foam. We specifically strive to produce foam struts that are oligocrystalline, each of which would function like a shape memory micro-pillar.


We employ the foam synthesis method of freeze casting, which has been applied to a wide range of materials to create porous structures, including alumina, silicon nitride, titanium, tungsten, hydroxyapatite, etc. [12–19]. A water suspension of the ceramic particles is frozen and ice is then sublimated under reduced pressure, creating porosity in place of the ice crystals; the resulting porous green body is sintered to consolidate the ceramic foam struts and walls [20].

We use ice templating with directional solidification, similar to the approach reported by Chino and Dunand [13]. The general set-up for such experiments is shown in Fig. 1a, and comprises a mold with low conductivity side walls matched with a high conductivity base, through which most of the heat is extracted and directional solidification thus effected. In the simplest case, one can cast with a fixed base temperature and no control over the solidification rate; we achieved this condition using glass side walls wrapped in cotton. In a more complex case, one can program a changing base temperature so as to manipulate the rate of cooling; we achieved this by varying the boundary condition of the cold plate ( $T_0$ ) with a thermoelectric cooler attached to a copper casting base with a programmed input voltage, with low conductivity PTFE side walls.

Oxide powders were acquired from Sigma-Aldrich, and had the following particle sizes:  $ZrO_2$ , <100 nm;  $CeO_2$ , <50 nm. The powders were mixed with water to form a slurry with a solids loading of 12 vol%. An anionic dispersing agent (Darvan C-N, consisting of ammonium polymethacrylate and water) was added as 1 wt% of the powder to improve the dispersion of ceramic powders in the solvent. Polyvinyl alcohol (PVA) was also added to serve as a binder to provide green strength

\* Corresponding author.

E-mail address: [schuh@mit.edu](mailto:schuh@mit.edu) (C.A. Schuh).

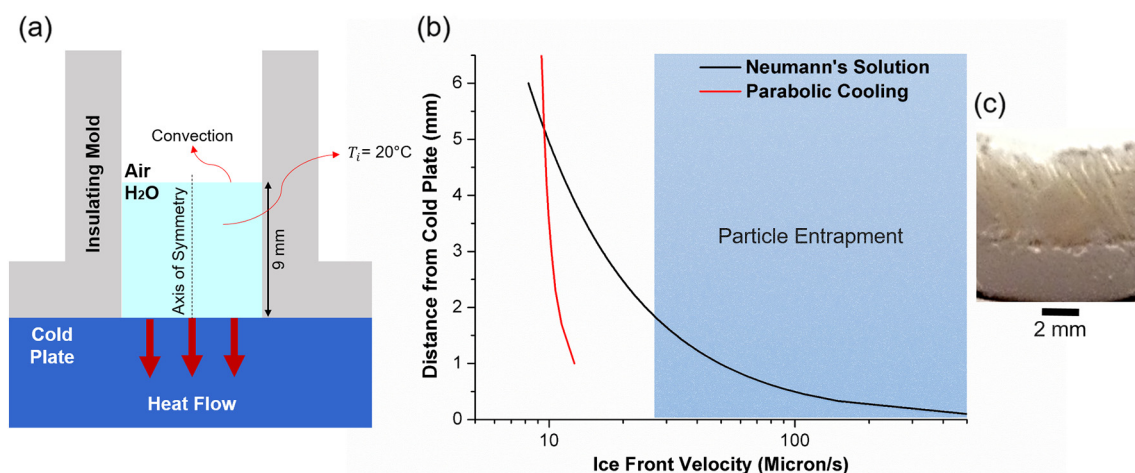

**Fig. 1.** (a) Schematic of directional freezing setup comprised of insulating side walls and conductive base (b) Predicted ice front velocities as a function of distance from the cold plate based on constant and changing boundary conditions (c) Sample chilled by constant cold plate temperature, showing a physical demarcation. (For interpretation of the references to color in this figure, the reader is referred to the web version of this article.)

after sublimation of the ice and was added as 2 wt% of the powder. After freeze casting and sublimation, the green body was sintered at 1500 °C for 10 h where interdiffusion of the oxides took place.

The solidification rate affects the microstructure of the foam that is produced, depending on its relation to the critical rate for particle ejection, and is dictated by the rate of heat extraction. An understanding of the heat transfer situation is therefore desirable to produce uniform foams, and here we use finite element modeling of the solidification process to help guide the foam synthesis. Since we model an axisymmetric situation with well-insulated side walls, the problem devolves to a one-dimensional problem of heat conduction along the z-axis, with the added complexity of the solidification front that releases the heat of fusion as it propagates. We solve this problem numerically using the ABAQUS 6.14-3 finite element solver, under the initial condition that the cast slurry is at room temperature:  $T_i = 20$  °C, and for simplicity we neglect details of the solid loading and simply model the solidification of ice from water (heat of fusion: 333.6 J/g, density of ice: 916.7 kg/m<sup>3</sup>, density of water: 1000 kg/m<sup>3</sup>, thermal conductivity of ice: 2.25 W/m·K, thermal conductivity of water: 0.58 W/m·K, specific heat of ice: 2030 J/kg·K, specific heat of water: 4187 J/kg·K). A convective boundary condition with a coefficient of 5 W/m<sup>2</sup> K to the ambient temperature of 20 °C is applied to the top surface and the bottom surface is in contact with the cold plate at an assigned temperature  $T_0$ .

Two conditions are compared in this work:

A constant cold mold temperature  $T_0 = -10$  °C. For this condition the finite element model closely matches the expected Neumann solution for a semi-infinite problem, at least at short times. The predicted ice front velocity shown in Fig. 1b is found to span a large range from hundreds of micrometers per second at the outset, to values more than an order of magnitude lower by the time the front has moved 5 mm. The problem with this wide range of velocities is that it spans the expected transition from particle engulfing to particle ejection. Fig. 1c shows a photograph of the foam structure produced by casting in this mode, which shows a clear two-zone solidification structure. There is a high density layer on the bottom, apparently due to the freezing that occurred there being too rapid for particle ejection [14]. After about 2.5 mm along the freezing direction, we observe a transition to a homogeneous porous regime. We associate this structural transition with the velocity of the ice front dropping below the critical particle ejection velocity. Comparing the location of the transition with the model results in Fig. 1b, we infer that the critical velocity is between about 20 and 30 μm/s. The reported critical velocity is about 2 μm/s for particles with diameter between 1 and 10 μm in silica-water slurry

[21]. Since the critical velocity is inversely proportional to the particle radius, it is reasonable to see a value about an order of magnitude higher for our system where the particle diameter is about 100 nm [14].

A parabolic decrease in  $T_0$  with time was also explored as a means of avoiding the structural transition described above. In order to attenuate the rate of heat extraction in the early stages and so avoid the particle engulfing regime, we designed a temperature profile ranging from 0 to  $-10$  °C over 14 min, i.e.,  $T_0 = -10\sqrt{t/14}$  ( $T_0$  in °C and  $t$  in min). This mold temperature profile yields a predicted ice front velocity as shown in Fig. 1b in red, which is nearly constant and on the order of 10 μm/s, below the transition velocity and in the range that produces uniform foam. Experimentally, we tuned the applied voltage to the Peltier cooling stage to attain nearly the same profile and indeed, the resulting foam appeared uniform along its length.

Foams produced under this controlled cooling regime had pore structures such as shown in Fig. 2a. With open pores of uniform size and struts on the order of microns that exhibit a high ratio of surface area to grain boundary area, these are oligocrystalline grain structures. The foam structure was quantified using micro computed x-ray tomography with an X-TEK XT H 225 ST instrument. Fig. 2b shows a 3D rendering of a typical foam structure, with its vertical and horizontal slices given in Fig. 2c and d respectively. The pore size distribution measured at various slices along the casting direction is shown in Fig. 2e. The average pore size (equivalent spherical diameter) is of order  $\sim 20$  μm, while the median pore size is about 10 μm, and remains close to this value all the way through the sampled volume. This observation is supportive of the expected constant solidification velocity from Fig. 1b. It is also noteworthy that Fig. 2c shows both lamellar/dendritic and reticulated pores. The literature has reported the formation of lamellar structures through ice templating by exploiting the anisotropy in the interfacial energies of ice [14,20]. The formation of reticulated pores, however, is attributed to the effect of PVA addition. This is consistent with the finding of Zuo et al. that PVA addition led to more open pores [22].

The resulting foams had a relative density of about 0.34. With typical strut widths of 7.4 μm and grain sizes of 3.0 to 3.5 μm, these oligocrystalline structures are comparable to the dimensions reported in ref. [23] in micropillar geometries to exhibit reproducible cyclic shape memory and superelasticity. This is explored in more detail in Fig. 3, where the thermally induced transformation is observed with differential scanning calorimetry (DSC) and thermomechanical analysis (TMA). In the DSC curve (Fig. 3a), the endothermic peak on heating corresponds to the transformation from monoclinic to tetragonal, or in the shape memory vernacular, martensite to austenite, respectively. The

Download English Version:

<https://daneshyari.com/en/article/5443364>

Download Persian Version:

<https://daneshyari.com/article/5443364>

[Daneshyari.com](https://daneshyari.com)