



# N-alkylation of ammonia and amines with alcohols catalyzed by Ni-loaded $\text{CaSiO}_3$



Ken-ichi Shimizu<sup>a,b,\*</sup>, Shota Kanno<sup>a</sup>, Kenichi Kon<sup>a</sup>, S.M.A. Hakim Siddiki<sup>b</sup>,  
Hideyuki Tanaka<sup>c</sup>, Yoshihisa Sakata<sup>c</sup>

<sup>a</sup> Catalysis Research Center, Hokkaido University, N-21, W-10, Sapporo 001-0021, Japan

<sup>b</sup> Elements Strategy Initiative for Catalysts and Batteries, Kyoto University, Katsura, Kyoto 615-8520, Japan

<sup>c</sup> Graduate School of Science and Engineering, Yamaguchi University, 2-16-1 Tokiwadai, Ube 755-8611, Japan

## ARTICLE INFO

### Article history:

Received 9 July 2013

Received in revised form 20 August 2013

Accepted 2 September 2013

Available online 25 September 2013

### Keywords:

Alcohols

Alkylation

Amines

Ammonia

Calcium silicate

Nickel

## ABSTRACT

Nickel nanoparticles loaded onto calcium silicate ( $\text{Ni/CaSiO}_3$ ) have been prepared by ion-exchange method followed by in situ  $\text{H}_2$ -reduction of the calcined precursor.  $\text{Ni/CaSiO}_3$  was found to be effective for the catalytic direct synthesis of primary amines from alcohols and  $\text{NH}_3$  under relatively mild conditions. Various aliphatic alcohols are tolerated, and the turnover number (TON) was higher than those of Ru-based homogeneous catalysts. The catalyst was recoverable and was reused. Effects of the surface oxidation states and particle size of Ni on the catalytic activity were studied by infrared (IR) investigation of the states of adsorbed CO and transmission electron microscopy (TEM). It is clarified that the surface  $\text{Ni}^0$  sites on small (3 nm) sized Ni nanoparticles are the catalytically active species.  $\text{Ni/CaSiO}_3$  was also effective for the alkylation of anilines and aliphatic amines with various alcohols (benzyl and aliphatic alcohols) under additive free conditions; primary amines were converted into secondary amines and secondary amines into tertiary amines.

© 2013 Elsevier B.V. All rights reserved.

## 1. Introduction


Amines are of significant importance for the bulk- and fine-chemical industry as building blocks for polymers, surfactants, dyes, pharmaceuticals and agrochemicals. Among the amines, the terminal primary amines are the most useful intermediates for further derivatization reactions [1]. Aliphatic primary amines can be synthesized by the reductive amination of the corresponding carbonyl compounds [2,3], but their selective synthesis is challenging due to their high reactivity. Although heterogeneous catalysts are used for reductive aminations of simple alcohols under  $\text{H}_2$  [2–5], they suffer from drawbacks such as limited substrate scope, low selectivity for primary amines and needs of high temperature ( $>200^\circ\text{C}$ ), high  $\text{H}_2$  pressure, and high  $\text{NH}_3$  pressure. Heterogeneous Ru [6] and Cu [7] catalysts reported by Mizuno and co-workers and homogeneous Ir catalysts reported by Fujita and co-workers [8] were effective and reusable catalysts for the direct synthesis of secondary and tertiary amines from alcohols and aqueous ammonia (or urea), but selective formation of primary amines were not reported. Milstein and co-worker [9] reported the first example

of the selective synthesis of primary amines from primary alcohols and  $\text{NH}_3$  using Ru PNP pincer complex, but the system was ineffective for the amination of secondary alcohols. Recently, Vogt and co-worker [10] and Beller and co-worker [11] independently discovered the selective amination of secondary alcohols with  $\text{NH}_3$  to give primary amines. Although these systems, driven by a borrowing-hydrogen [12] (or hydrogen-autotransfer [2]) mechanism (Scheme 1), provided successful examples catalytic primary amines syntheses, the homogeneous Ru catalysts had problems such as necessity of expensive noble metals and difficulties in recovery and reuse of catalysts.

The N-alkylation of amines with alcohols to give higher order amines has been also attracted considerable attention as an environmentally friendly synthetic method of alkyl amines [1,2]. Recently, homogeneous Ru [13] and Ir [14] catalysts were shown to be highly effective for this one-pot reaction, but these systems have problems such as difficulty in the recovery and reuse of expensive catalysts and the use of co-catalysts such as base and stabilizing ligand. Recyclable heterogeneous noble metal catalysts (Pd [15], Ru [6,16], Au [17], Pt [18] and Ag [19,20]) have been also reported, but some of them suffer from low TON, low selectivity to mono-alkylation, and necessity of co-catalysts. From the environmental and economic viewpoints, it is desired to accomplish this reaction by an inexpensive catalyst. However, most of the heterogeneous base metal catalysts reported so far (Ni [21], Fe [22] and Cu [7])

\* Corresponding author at: Catalysis Research Center, Hokkaido University, N-21, W-10, Sapporo 001-0021, Japan. Fax: +81 11 706 9163.

E-mail address: [kshimizu@cat.hokudai.ac.jp](mailto:kshimizu@cat.hokudai.ac.jp) (K.-i. Shimizu).

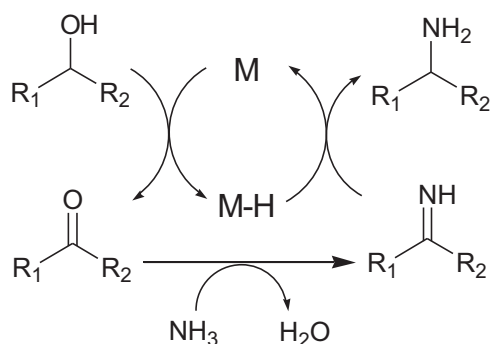

**Scheme 1.** Borrowing-hydrogen mechanism of transition metal-catalyzed amination of alcohols.

catalysts) generally suffer from low TON, limited scope and necessities of high temperatures or basic co-catalyst. For example, Ni/Cu co-loaded  $\text{Al}_2\text{O}_3$  catalyst recently reported by Sun et al. exhibited TON of 1.9 for N-alkylation of aniline with benzylalcohol in the presence of 25 mol% NaOH and 12.5 mol%  $\text{CaCl}_2$  [21].

As shown above, the development of non-noble-metal-based heterogeneous catalyst for the direct amination reactions is an important research target. We report herein that calcium silicate ( $\text{CaSiO}_3$ )-supported nickel metal nanoparticle catalyst readily prepared from inexpensive commercial materials [23] acts as a versatile heterogeneous catalyst for the selective synthesis of primary amines from alcohols and ammonia N-alkylation of amines with alcohols to give higher order amines under relatively mild conditions without any additives. In order to clarify the controlling factors of the catalytic system, the effects of the particle size and surface oxidation states of Ni on the activity is discussed based on the results of catalyst characterization.

## 2. Experimental

Commercially available organic and inorganic compounds (from Tokyo Chemical Industry, Wako Pure Chemical Industries, or Kanto Chemical) were used without further purification. The GC (Shimadzu GC-14B) and GCMS (Shimadzu GCMS-QP2010) analyses were carried out with Ultra ALLOY capillary column UA<sup>+</sup>-5 (Frontier Laboratories Ltd.) capillary column (Shimadzu) using nitrogen as the carrier gas.

$\text{CaSiO}_3$  was kindly supplied from Konoshima Chemical.  $\text{Ni}^{2+}$ -exchanged  $\text{CaSiO}_3$  was prepared by treating the support with aqueous solution of Ni nitrate for 12 h at room temperature, followed by centrifuging and washing with deionized water (three times), and by drying at 90 °C for 12 h. NiO-loaded  $\text{CaSiO}_3$  ( $\text{NiO}/\text{CaSiO}_3$ ) was prepared by calcining  $\text{Ni}^{2+}$ -exchanged  $\text{CaSiO}_3$  in air for 4 h at 350 °C. Ni-loaded  $\text{CaSiO}_3$  ( $\text{Ni}/\text{CaSiO}_3$ ) was prepared by in situ pre-reduction of  $\text{NiO}/\text{CaSiO}_3$  under  $\text{H}_2$  flow (20  $\text{cm}^3 \text{ min}^{-1}$ ) at 600 °C for 0.5 h. ICP analysis showed that Ni content in the sample was 10 wt%.  $\text{SiO}_2$  (Q-10) was supplied from Fuji Silysia Chemical Ltd. CaO was prepared by calcination of  $\text{Ca}(\text{OH})_2$  at 500 °C for 3 h. CaO or  $\text{SiO}_2$ -supported Ni (10 wt%) were prepared by the impregnation method, followed by drying at 90 °C for 12 h, and by in situ pre-reduction of the precursor under  $\text{H}_2$  at 600 °C. Raney Ni (B113 W, Ni >90%) was supplied from Evonik Industries.

$\text{Ni}/\text{CaSiO}_3$  pre-reduced at 600 °C was used as a standard catalyst. For the reaction of alcohols with  $\text{NH}_3$ , the pre-reduced catalyst in the closed glass tube sealed with a septum inlet was cooled to room temperature under  $\text{H}_2$  atmosphere. The mixture of *o*-xylene (4.0 g), alcohol (3.0 mmol), and *n*-dodecane (0.5 mmol) was injected to the pre-reduced catalyst inside the glass tube through the septum inlet. Then, the septum was removed under air, and a magnetic stirrer

was put in the tube, followed by inserting the tube inside stainless autoclave with a dead space of 33  $\text{cm}^3$ . Soon after being sealed, the reactor was flushed with  $\text{NH}_3$  from a high pressure gas cylinder and charged with 0.4 MPa  $\text{NH}_3$  at room temperature. The amount of  $\text{NH}_3$  present in the reactor before heating was 6.7 mmol (2.2 equiv. with respect to the alcohol). Then, the reactor was heated typically at 160 °C under stirring (150 rpm).

For the reaction of alcohols with amines, the mixture of alcohol (1.0 mmol) and amine (1.2 mmol) in *o*-xylene (1 g) was injected to the pre-reduced catalyst inside a reactor (cylindrical glass tube) through a septum inlet, followed by filling with  $\text{N}_2$ . Then, the resulting mixture was stirred under reflux; bath temperature was 155 °C and reaction temperature was ca. 144 °C. For both reactions, conversion and yields of products were determined by GC using *n*-dodecane as an internal standard. The products were identified by GC–MS equipped with the same column as GC and by comparison with commercially pure products.

TEM measurements were carried out by using a JEOL JEM-2100F TEM operated at 200 kV. Ni K-edge extended X-ray absorption fine structure (EXAFS) was measured in transmission mode at the BL01B1 in the SPring-8 (Proposal No. 2011B1137). The storage ring was operated at 8 GeV. A Si(111) single crystal was used to obtain a monochromatic X-ray beam. The EXAFS analysis was performed using the REX version 2.5 program (RIGAKU). The Fourier transformation of the  $k^3$ -weighted EXAFS oscillation from  $k$  space to  $R$  space was performed over the range 3.0–16.0  $\text{\AA}^{-1}$  to obtain a radial distribution function. The inversely Fourier filtered data were analyzed with a usual curve fitting method in the  $k$  range of 3.0–16.0  $\text{\AA}^{-1}$ . The parameters for the Ni–O and Ni–Ni shells were provided by the FEFF6.

The surface characterization of the  $\text{Ni}/\text{CaSiO}_3$  was carried out by the infrared (IR) spectroscopic investigation of adsorbed CO over the catalyst. The  $\text{Ni}/\text{CaSiO}_3$  catalyst (40 mg) was pressed into self-supporting pellet of 20 mm in diameter, and was placed in an infrared cell, which was connected to a closed gas circulation system equipped with vacuum line. The  $\text{Ni}/\text{CaSiO}_3$  catalyst pre-reduced at 600 °C was placed in the IR cell and reduced again by  $\text{H}_2$  at 500 °C for 10 h, followed by evacuation at the same temperature for 1 h before use. Adsorption of CO was carried out at 25 °C. Infrared spectra were recorded by an FT-IR (Jasco. FT/IR 7300) equipped with an MCT detector. The spectra were obtained by 100 scans at 4  $\text{cm}^{-1}$  resolution. The spectra of adsorbed CO were obtained from rationing the background spectra of the catalyst to those of adsorbed CO.

## 3. Results and discussion

The XRD spectrum of  $\text{Ni}/\text{CaSiO}_3$  (recorded under ambient conditions) showed broad lines due to metallic Ni. Fig. 1 shows the EXAFS spectrum of  $\text{Ni}/\text{CaSiO}_3$ . The catalyst pre-reduced in a flow of  $\text{H}_2$  for 0.5 h at 600 °C was cooled to room temperature in the flow of  $\text{H}_2$  and was sealed in a cell made of polyethylene under  $\text{N}_2$ , and then the EXAFS spectrum was taken at room temperature. Table 1 shows the results of curve-fitting analyses of the EXAFS. The EXAFS of  $\text{Ni}/\text{CaSiO}_3$  consists of a Ni–Ni shell (at 2.48 Å with coordination number of 4.3) and a Ni–O shell (at 2.00 Å and coordination number of 2.6). By comparison with the crystallographic data of Ni metal, the Ni–Ni shell was assigned to metallic Ni. The weak contribution of the Ni–O shell indicates the presence of NiO or  $\text{Ni}^{2+}$  species as minor Ni species. Fig. 2 shows Ni particle size distributions of  $\text{Ni}/\text{CaSiO}_3$  pre-reduced at different temperatures (600 °C and 700 °C). The average particle sizes of the catalysts reduced at 600 °C and 700 °C were  $3.0 \pm 0.8 \text{ nm}$  and  $12.6 \pm 2.9 \text{ nm}$ , respectively. The average size of Ni crystallites in  $\text{Ni}/\text{CaSiO}_3$  (reduced at 600 °C) estimated by XRD (Fig. 1) using Scherrer equation is

Download English Version:

<https://daneshyari.com/en/article/54466>

Download Persian Version:

<https://daneshyari.com/article/54466>

[Daneshyari.com](https://daneshyari.com)