



Microstructural characterization of an $\alpha+\beta$ type Ti-5.5Mo-7.2Al-4.5Zr-2.6Sn-2.1Cr alloy during recrystallization annealing



Ran Shi, Guoju Li, Yumeng Xia, Qunbo Fan^{*}, Fuchi Wang, Hongmei Zhang, Xingwang Cheng

School of Materials Science and Engineering, Beijing Institute of Technology, Beijing 100081, China

ARTICLE INFO

Article history:

Received 28 November 2016
Received in revised form
14 January 2017
Accepted 12 February 2017
Available online 16 February 2017

Keywords:

Recrystallization
Three-dimensional morphology
Electron backscatter diffraction
Titanium alloy
Microstructure

ABSTRACT

An $\alpha+\beta$ type titanium alloy was subjected to various periods of recrystallization annealing and the resulting microstructural evolution was characterized. The results revealed that the recrystallization rate of the β phase was higher than that of the α phase, owing to the high strain energy storage of this phase during large deformation forging. Moreover, the recrystallized fraction of both the α and β phases increased with increasing holding time at 740 °C. The recrystallization fraction of the β phase accounted for 70.13% after annealing for 5 h. However, the average grain size remained constant when the recrystallization fraction reached approximately 54%, indicating that further grain refinement was prevented, owing to the high degree of recrystallization. The spatial microstructure which consisted of a globular, homogeneous, and equiaxed α phase dispersed in sub-structured β matrix grains, was characterized via a novel three-dimensional electron backscatter diffraction technique. The grain orientation and morphological parameters, including the equivalent-sphere diameter and number of neighboring grains, were calculated and discussed.

© 2017 Elsevier B.V. All rights reserved.

1. Introduction

Recrystallization affects the microstructure and mechanical properties of materials during forging and annealing and is therefore important from both theoretical and industrial viewpoints [1]. Grain refinement based on continuous dynamic recrystallization (DRX) was realized through multi-directional forging [2,3]. Ning et al. [4,5] developed a unique heat treatment method to produce a gradient microstructure. In those works, multiple passes of forging and annealing treatment resulted in significant grain size refinement, owing to the occurrence of dynamic and static recrystallization.

Furthermore, the microstructure of $\alpha+\beta$ titanium alloys can be improved through severe deformation in the β -phase field and subsequent annealing in the $\alpha+\beta$ phase field [6]. Previous studies [7,8] have shown that the formation of fine grains and the enhancement of high-temperature mechanical properties of titanium alloys subjected to β -forging occur predominantly via DRX. The effect of cooling rate, annealing, and aging temperature (during

subsequent heat treatment in the $\alpha+\beta$ phase field) on microstructural evolution and the mechanical properties has been considered in various studies [9–14]. Meng et al. [15] predicted the evolution of the phase fraction (especially of the primary α phase) of two-phase Ti-alloys, with temperature. In addition, Popov et al. [16] determined the effect of heating temperature and holding time on the occurrence of structural and phase transformations in a Ti-6-4 Eli titanium alloy. Jiang et al. [17] considered the effect of recrystallization during annealing of a cold-rolled Ti-6Al-4V alloy and showed that the recrystallization sites of preferred orientations and favorable grain growth played an important role in static recrystallization. When static recrystallization occurs during annealing, the microstructure evolves via competing processes of recovery, nucleation of recrystallization, and grain growth [18]. The influence of holding time at recrystallization temperature on specific characteristics (recrystallization rate and fraction, grain size and phase distribution) has scarcely been investigated. Elucidation of the static recrystallization behavior could aid in the refinement of microstructures.

Therefore, in this work, the microstructural evolution associated with increasing recrystallization-annealing time was characterized via two-dimensional (2D) electron backscatter diffraction (EBSD) analysis. Furthermore, three-dimensional (3D) microstructural

^{*} Corresponding author.

E-mail address: fanqunbo@bit.edu.cn (Q. Fan).

characterization was performed via serial-sectioning using a focused ion beam (FIB) [19–21], field emission scanning electron microscopy (SEM) [22–25] with EBSD, and computer-aided 3D reconstruction and visualization [26]. The precise shape, spatial misorientation and neighboring relationship of the grains, as well as spatial distribution of the phases were obtained via the 3D FIB–EBSD method [27–30].

2. Material and methods

The titanium alloy (Ti-5.5Mo-7.2Al-4.5Zr-2.6Sn-2.1Cr) was prepared by vacuum self-consuming electricity arc melting, followed by rough blooming forging in the β phase field and large deformation forging in the $\alpha+\beta$ phase field. Afterwards, $5\text{ mm} \times 8\text{ mm} \times 1\text{ mm}$ specimens were cut from the forged ingot and subsequently solution-treated at $880\text{ }^\circ\text{C}$ for 0.5 h. The specimens were then heat-treated at $740\text{ }^\circ\text{C}$ for 1 h, 2 h, and 5 h, respectively, and water quenched to retain the high-temperature microstructure. The 2D EBSD measurements were performed at a step size of $0.15\text{ }\mu\text{m}$ using a FEI Nanosem 430 field emission gun scanning electron microscope (SEM, HITACHIS-4800 N, Japan) operated at 20 kV. The samples designated for 2D EBSD were mechanically polished and then electropolished (25 $^\circ\text{C}$, 25 V, $\sim 30\text{ s}$, solution: 6% HClO_4 , 34% $\text{CH}_3(\text{CH}_2)_3\text{OH}$, and 60% CH_3OH) to remove the stress from the surface layers.

For serial-sectioning, small ($5\text{ mm} \times 1\text{ mm} \times 0.5\text{ mm}$) samples were cut from the water-quenched specimen heat-treated at $740\text{ }^\circ\text{C}$ for 5 h. The geometry of the FIB–SEM system requires that the sampling area is positioned close to an edge of the sample. Therefore, the sample was ground to a thickness of $\sim 26\text{ }\mu\text{m}$ (Fig. 1(a)). Measurements were performed on a Zeiss XB1540 crossbeam instrument (Carl Zeiss NTS GmbH, Germany), equipped with a field emission electron column and a Ga^+ -ion emitter. For orientation microscopy, a Nordlys F EBSD detector (Oxford Instruments HKL, UK) was positioned on one side of the FIB column

(Fig. 1(b)). This positioning allows a 180° rotation of a 16.5° pre-tilted sample holder and, in turn, quick and precise changes between FIB milling (sample at 36°) and EBSD mapping (sample at 70°). The FIB was operated at an accelerating voltage of 30 kV and a milling current of 4 nA. Prior to the experiment, milling was used to create a marker (cross) that was used for drift correction (Fig. 1(c), FIB view). The cross-section was then serial-milled in milling steps of $\sim 100\text{ nm}$, and the milled region ($\sim 15 \times 10\text{ }\mu\text{m}^2$) was examined (Fig. 1(c), SEM view) after each step.

3. Results and discussion

3.1. 2D EBSD analysis

The microstructure development of a $60 \times 60\text{ }\mu\text{m}^2$ region was investigated during recrystallization annealing. Fig. 2 shows the recrystallized-fraction distribution maps of the α and β phases. The recrystallized, sub-structured, and deformed grains are shaded in blue, yellow, and red, respectively. A subgrain is defined by a minimum angle (θ_c) of 1° . If the average misorientation angle within the grain exceeds θ_c , the grain is classified as being “deformed”. Some grains consist of subgrains with an internal misorientation of $<\theta_c$, and exhibit a subgrain-to-subgrain misorientation of $>\theta_c$. In this case, the grain is classified as “sub-structured”. The remaining grains are classified as “recrystallized”. The maps reveal that the grain size of the α phase decreases significantly with increasing annealing time. During the static recrystallization process, the sub-structured matrix resulting from DRX [31] decreases with increasing area of the recrystallized grains.

Fig. 3 shows the distribution histogram and average-grain-size evolution of the α and β phases with annealing time. The α and β phases comprise a negligible fraction (7%) of the deformed grains. Recrystallization fractions of 46.61% and 47.01% of the α phase occur after annealing for 1 h and 2 h, respectively, at $740\text{ }^\circ\text{C}$. The corresponding average grain sizes, $0.86\text{ }\mu\text{m}$ and $0.72\text{ }\mu\text{m}$, reveal that the

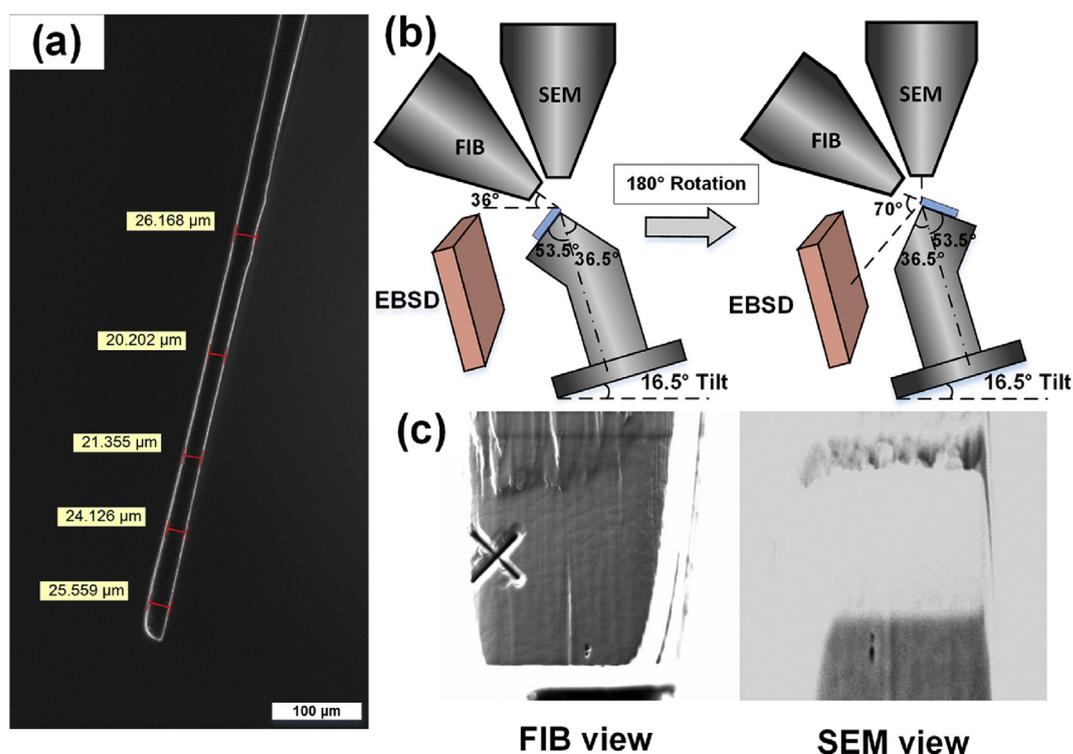


Fig. 1. (a) Optical micrographs of the prepared sample; (b) schematic of the experimental setup used for the 3D FIB–EBSD method; (c) images from FIB and SEM view.

Download English Version:

<https://daneshyari.com/en/article/5459785>

Download Persian Version:

<https://daneshyari.com/article/5459785>

[Daneshyari.com](https://daneshyari.com)