



# Fabrication and electrochemical behavior study of nano-fibrous sodium titanate composite



Yeqian Ge<sup>a,b,c,\*</sup>, Jiadeng Zhu<sup>b</sup>, Mahmut Dirican<sup>b,d</sup>, Hao Jia<sup>b</sup>, Meltem Yanilmaz<sup>b</sup>, Yao Lu<sup>b</sup>, Chen Chen<sup>b</sup>, Yiping Qiu<sup>c</sup>, Xiangwu Zhang<sup>b,\*\*</sup>

<sup>a</sup> College of Textiles and Garments, Shaoxing University, Shaoxing 312000, China

<sup>b</sup> Department of Textile Engineering, Chemistry and Science, North Carolina State University, Raleigh, NC 27695-8301, USA

<sup>c</sup> Department of Textile Materials Science and Product Design, College of Textile, Donghua University, Shanghai 201620, China

<sup>d</sup> Department of Materials Science and Nanotechnology Engineering, Abdullah Gül University, Kayseri, Turkey

## ARTICLE INFO

### Keywords:

Sodium titanate  
Nanocomposites  
Electrospinning  
Sodium-ion batteries  
Electrochemical properties

## ABSTRACT

Nanofiber structured  $\text{Na}_2\text{Ti}_3\text{O}_7$  was synthesized via electrospinning process which was further used as an anode material for sodium-ion batteries for the first time. One-dimensional construction of  $\text{Na}_2\text{Ti}_3\text{O}_7$  composite could contribute to better electrochemical activity. It was demonstrated that the capacity of  $\text{Na}_2\text{Ti}_3\text{O}_7$  nanofibers was significantly improved to  $257.8 \text{ mAh g}^{-1}$  at  $30 \text{ mA g}^{-1}$ . Furthermore, the rate capability of  $\text{Na}_2\text{Ti}_3\text{O}_7$  nanofibers was significantly enhanced, showing charge capacities were 161.8, 116.5, and  $72.4 \text{ mAh g}^{-1}$  at 100, 200, and  $400 \text{ mA g}^{-1}$ , respectively. Therefore, improved specific capacity and rate capability made  $\text{Na}_2\text{Ti}_3\text{O}_7$  nanofibers composite as a promising anode material for sodium-ion batteries.

## 1. Introduction

The intensive depletion of fossil fuels brings about energy and environment concerns throughout the world. Aim to release the tension of this crisis, massive renewable energy are being explored, such as solar energy, nuclear energy. Meanwhile, to save these energy, relevant energy storage devices should also be developed. Rechargeable batteries are widely used in portable devices, and now have been expanded to electronic vehicles, even large-scale energy storage systems, etc. [1,2]. Compared with lithium-ion batteries, sodium-ion batteries possess features of low cost and abundant sodium resource, having great potential to be applied particularly in the large-scale energy storage field [3,4]. Many efforts have been devoted to pursue a proper anode material for sodium-ion batteries, since graphite, the most common-use anode material in lithium-ion batteries, has little ability to store sodium ions in its layer structure due to the relatively larger radius of Na ions [5].

Titanium-based oxide insertion materials are considered with good chemical stability, good safety and sufficient resource in electrochemical utilization [6]. Among which, sodium titanate ( $\text{Na}_2\text{Ti}_3\text{O}_7$ ) is drawing attention to the potential usage in sodium-ion batteries because it has the lowest insertion voltage (0.3 V vs.  $\text{Na}^+/\text{Na}$ ). It is found that theoretically 1 M  $\text{Na}_2\text{Ti}_3\text{O}_7$  can reversibly react with 2 M Na

ions to achieve a capacity of  $178 \text{ mAh g}^{-1}$  [7]. However, the practical capacity of bulk  $\text{Na}_2\text{Ti}_3\text{O}_7$  is restricted because of the sluggish kinetics. By designing into nanosize, the specific surface area of energy materials are enlarged. In addition, nanosize structure can reduce ion and charge transportation distance, leading to faster ion diffusion and charge transfer. Particularly, nanofiber structure can provide electron transfer network pathway, resulting in better electronic conductivity [4,8–10]. However, not much work has been done on  $\text{Na}_2\text{Ti}_3\text{O}_7$  exploration in battery field. Table 1 presented the electrochemical properties of reported  $\text{Na}_2\text{Ti}_3\text{O}_7$ .

Herein, for the first time, we proposed a nanofiber structured  $\text{Na}_2\text{Ti}_3\text{O}_7$  by using electrospinning method and thermal treatment, applying it as anode material for sodium-ion batteries. As a result, the charge-discharge capacity and rate capability were significantly improved.

## 2. Experimental sections

### 2.1. Materials synthesis

The processing of sodium titanate nanofibers was shown in Fig. 1a. An amount of 6.76 g  $\text{Ti}(\text{OC}_4\text{H}_9)_4$  (Aldrich, 97%) was added dropwise to a polymer solution with 1 g poly(vinyl pyrrolidone) (PVP, Thermo


\* Corresponding author at: College of Textiles and Garments, Shaoxing University, Shaoxing 312000, China.

\*\* Corresponding author.

E-mail addresses: [yge3@ncsu.edu](mailto:yge3@ncsu.edu) (Y. Ge), [yge3@ncsu.edu](mailto:yge3@ncsu.edu) (X. Zhang).

**Table 1**  
Electrochemical property comparison of  $\text{Na}_2\text{Ti}_3\text{O}_7$  in this work with reported  $\text{Na}_2\text{Ti}_3\text{O}_7$ .

	Reversible capacity ( $\text{mAh g}^{-1}$ at $\text{mA g}^{-1}$ )	Rate capability ( $\text{mAh g}^{-1}$ at $\text{mA g}^{-1}$ )
$\text{Na}_2\text{Ti}_3\text{O}_7/\text{C}$ particles [14]	178 at 35.6	55 at 14240
$\text{Na}_2\text{Ti}_3\text{O}_7$ particles [16]	177 at 17.8	71 at 890
$\text{Na}_2\text{Ti}_3\text{O}_7$ nanotubes [17]	205 at 400	100 at 3000
$\text{Na}_2\text{Ti}_3\text{O}_7$ nanoparticles [13]	188 at 17.8	64 at 356
$\text{Na}_2\text{Ti}_3\text{O}_7$ nanorods [18]	Around 200 at 17.8	Around 140 at 89
Microspherical $\text{Na}_2\text{Ti}_3\text{O}_7$ [19]	Around 177 at 354	Around 90 at 3540
$\text{Na}_2\text{Ti}_3\text{O}_7$ nanofibers (this work)	242.3 at 30	72.4 at 400

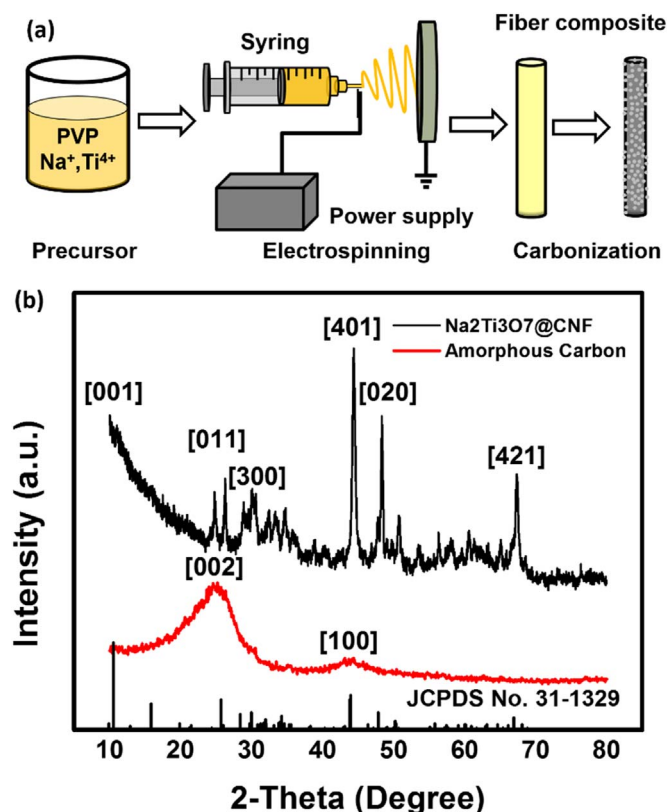

**Fig. 1.** (a) Schematic illustration of the fabrication process of  $\text{Na}_2\text{Ti}_3\text{O}_7$  nanofibers. (b) XRD patterns of  $\text{Na}_2\text{Ti}_3\text{O}_7$  nanofibers and amorphous carbon.

Fisher Scientific,  $M_w=1,300,000 \text{ g mol}^{-1}$ ) in solvent of 14 g  $\text{C}_2\text{H}_5\text{OH}$ , (Aldrich,  $\geq 99\%$ ) and 1.2 g  $\text{CH}_3\text{COOH}$  (Aldrich,  $\geq 99\%$ ). Then 1.196 g  $\text{CH}_3\text{COONa}$  (Aldrich,  $\geq 99\%$ ) was also added into the solution with vigorous stirring for two days at around 1000 r/min. Then the precursor solution was spun on an electrospinning setup with a voltage of 20 kV, flow rate of  $0.75 \text{ ml h}^{-1}$  and a tip-to-collector distance of 15 cm. The nanofiber mat was stabilized in air at  $280^\circ\text{C}$  for 5.5 h then further treated in nitrogen at  $750^\circ\text{C}$  for 4 h [3,4]. During processing, PVP was pyrolyzed into amorphous carbon and  $\text{Na}_2\text{Ti}_3\text{O}_7$  could be synthesized [3,17], therefore,  $\text{Na}_2\text{Ti}_3\text{O}_7$  nanofiber contained carbon ingredient. As comparison, pure  $\text{Na}_2\text{Ti}_3\text{O}_7$  particles were also produced by sol-gel method from the same solution as  $\text{Na}_2\text{Ti}_3\text{O}_7$  nanofibers. The solution was first dried in the oven at  $50^\circ\text{C}$  overnight and then sintered at  $750^\circ\text{C}$  for 4 h in air.

## 2.2. Structural and morphologic characterization

The morphology of  $\text{Na}_2\text{Ti}_3\text{O}_7$  samples were observed by field-emission scanning electron microscopy (FE-SEM, FEI VERIOS 460 L) and transmission electron microscopy (TEM and HRTEM, Hitachi HF 2000, accelerating voltage 200 kV). The lattice structure of  $\text{Na}_2\text{Ti}_3\text{O}_7$  nanofiber was confirmed with standard file by using wide-angle X-ray diffractometer (WAXD, Rigaku Smartlab). The carbon content was conducted by elemental analysis (EA, Perkin Elmer 2400 Series II CHNS/O Elemental Analyzer).

## 2.3. Electrochemical characterization

Sodium titanate samples were assembled into CR2032 coin cells. The electrode was making from slurry onto copper foil, which composed of active material, carbon black and sodium alginate binder in deionized water with the weight ratio 8:1:1. The mass loading of the active material was around  $1 \text{ mg cm}^{-2}$ . The electrode was punched into half-inch circles and heated in the oven at  $100^\circ\text{C}$  overnight before using. The counter electrode was sodium slice. Electrolyte was made of 1 M  $\text{NaClO}_4$  (98%) dissolved in ethylene carbonate (98%) and dimethyl carbonate ( $\geq 99\%$ ) (1:1 by volume). Glass fiber mat (Whatman) was used as the separator. All the assembling process was completed in an argon-filled glove box. Charge-discharge performance and rate capability at a voltage range of 0–2.5 V (vs.  $\text{Na}/\text{Na}^+$ ) were carried galvanostatically on a LAND (CT2001A) battery testing system. With the scan rate of  $0.1 \text{ mV s}^{-1}$ , CV feature of  $\text{Na}_2\text{Ti}_3\text{O}_7$  nanofibers were described by Reference 600 Potentiostat/Galvanostat/ZRA (GAMRY).

## 3. Results and discussion

The XRD spectrum of  $\text{Na}_2\text{Ti}_3\text{O}_7$  nanofibers from 10 to  $80^\circ$  was exhibited in Fig. 1b. Notably, main diffraction peaks at  $10.56^\circ$ ,  $25.76^\circ$ ,  $29.64^\circ$ ,  $39.78^\circ$ ,  $47.48^\circ$ , and  $66.96^\circ$  were appeared, which could be indexed to the [001], [011], [300], [400], [020], and [421] crystal planes of  $\text{Na}_2\text{Ti}_3\text{O}_7$  presented in JCPDS No. 31–1329 [11]. The curve had very strong slope at the beginning, which was resulted from the background signal. However, the XRD peak intensity and resolution of  $\text{Na}_2\text{Ti}_3\text{O}_7$  nanofibers were low, which was attributed to the introduction of amorphous carbon [12]. The carbon content of  $\text{Na}_2\text{Ti}_3\text{O}_7$  nanofibers were detected with 5.82%. The XRD curve of pure carbon pyrolyzed from PVP was also provided as comparison, presenting broad peaks at around  $26^\circ$  and  $43^\circ$ , corresponding to the [002] and [100] phase of the graphitized structure [3].

The morphology of  $\text{Na}_2\text{Ti}_3\text{O}_7$  particles and nanofibers was observed by SEM. Fig. 2a and b demonstrated  $\text{Na}_2\text{Ti}_3\text{O}_7$  particles were agglomerated into bigger bulk. The average particle size of primary and secondary particles were around  $0.93 \mu\text{m}$  and  $20 \mu\text{m}$ , respectively. As to  $\text{Na}_2\text{Ti}_3\text{O}_7$  nanofibers, distinct fine nano-fibrous structure with around 140 nm in diameter were exhibited in Fig. 2c and d. In order to confirm the structure of  $\text{Na}_2\text{Ti}_3\text{O}_7$  nanofiber, TEM and HRTEM were also illustrated in Fig. 2e and f. The nanofiber was composed with amorphous and crystal phases, indicated carbon and  $\text{Na}_2\text{Ti}_3\text{O}_7$  crystal. In addition, the lattice spacing indexed in HRTEM images was  $5.59 \text{ \AA}$  for [101] lattice planes of  $\text{Na}_2\text{Ti}_3\text{O}_7$ , agreed with the XRD result.

The first three charge-discharge curves of  $\text{Na}_2\text{Ti}_3\text{O}_7$  particles and nanofibers at  $30 \text{ mA g}^{-1}$  were recorded between 0 and 2.5 V (vs.  $\text{Na}/\text{Na}^+$ ), shown in Fig. 3a and b. Notably, electrochemical activity of  $\text{Na}_2\text{Ti}_3\text{O}_7$  particles was limited. At the first cycle, the discharge capacity and charge capacity were only  $96.3 \text{ mAh g}^{-1}$  and  $52.3 \text{ mAh g}^{-1}$ , respectively, which indicated that 45.7% of sodium ions became irreversible during this cycling. In contrast,  $\text{Na}_2\text{Ti}_3\text{O}_7$  nanofibers demonstrated a charge capacity of  $257.8 \text{ mAh g}^{-1}$  at the first cycle, which was 5 times higher than that of  $\text{Na}_2\text{Ti}_3\text{O}_7$  particles. In order to further understand the electrochemical reaction of  $\text{Na}_2\text{Ti}_3\text{O}_7$  nanofibers, CV measurements were conducted on Gamry tester. According to

Download English Version:

<https://daneshyari.com/en/article/5463524>

Download Persian Version:

<https://daneshyari.com/article/5463524>

[Daneshyari.com](https://daneshyari.com)