



Surface wettability switching of metal-organic framework mesh for oil-water separation



Zixi Kang^{a,b,*}, Sasa Wang^{a,b}, Lili Fan^{a,b}, Zhenyu Xiao^{a,b}, Rongming Wang^{a,b}, Daofeng Sun^{a,b,*}

^a College of Science, China University of Petroleum (East China), Qingdao Shandong 266580, People's Republic of China

^b State Key Laboratory of Heavy Oil Processing, China University of Petroleum (East China), Qingdao Shandong 266580, People's Republic of China

ARTICLE INFO

Keywords:

Metal-organic framework
Deposition
Oil-water separation
Surface wettability switching
Porous materials

ABSTRACT

The surface wettability switching of JUC-150 Metal-Organic Framework (MOF) mesh from hydrophilicity to hydrophobicity was achieved by a facial polydimethylsiloxane (PDMS) modification method. The PDMS modified JUC-150 mesh (JUC-150@PDMS mesh) exhibited high oil-water separation efficiency and flux attributed to the porous structure of the nickel mesh substrate. The passing phase (water or oil) through the MOF mesh can be determined according to the demand, which is of vital importance for industrial applications. Furthermore, this method is universal for other MOF meshes, films and membranes that will be applied in the field of water purification and gas mixture separation with steam.

1. Introduction

Metal-organic frameworks (MOFs), benefited from their crystallinity and tenability, have emerged as novel candidates in gas storage and separation [1,2]. Nowadays, turning MOFs into membrane materials [3] and exploring their performances for applications in separation and purification have attracted great interests of researchers working in the fields of chemistry, chemical engineering, materials science, etc. [4–7].

At present oil leakage and oil-contaminated water need to be addressed urgently since it has become a worldwide issue [8–11]. Developing new functional materials for efficient treatment of oily water is therefore imperative. Currently, the research of “smart” surface with reversible wettability has aroused great interests [12–15], especially the wettability switching between hydrophobicity and hydrophilicity driven by external stimuli, such as light, temperature, electricity, solvent, etc. However, the transitions of surface wettability triggered by the aforementioned approaches generally require a long period of time, even several weeks, which restricts their large-scaled uses. Additionally, these approaches need either complex steps or special equipment to be carried out. Hence, it would be highly demanded to manipulate the wettability transition with a time saving and convenient method.

In this work, we will suggest a facial PDMS modification method to realize the surface wettability switching of MOF mesh. A hydrophilic and stable MOF (JUC-150) we previously synthesized was chosen to grow on the nickel mesh substrate [16]. After a simple in-situ growth

step, the nickel mesh substrate was coated with intergrown JUC-150 crystals. Then, the hydrophilic surface of the MOF mesh could be turned into hydrophobic by 1 h PDMS modification. The JUC-150@PDMS mesh showed outstanding hydrophobic behavior. It allowed the oil phase to permeate through quickly, whereas the aqueous phase was effectively retained. The separation methodology was solely based on gravity, the results of which proved the JUC-150@PDMS mesh to be an energy-efficient oil-water filter (Fig. 1). Our work shows the great potential of the JUC-150@PDMS mesh for future practical applications in oil-water related separations. More importantly, this modification method is universal and can be extended to various MOF meshes, films and membranes, especially when they are applied in humid conditions.

2. Results and discussion

2.1. JUC-150@PDMS mesh

The JUC-150 MOF mesh was prepared by in-situ growth method on the nickel mesh substrate and the easy-operation PDMS modification was carried out at 220 °C for one hour. The powder X-ray diffraction (PXRD) patterns collected from the as-synthesized JUC-150 MOF mesh and JUC-150@PDMS mesh are shown in Fig. 2a. As can be seen, the PXRD patterns of the pristine and the modified JUC-150 meshes are in accordance with the simulated one of JUC-150. It suggests that high crystalline MOF crystals were grown on the substrate surface and their crystal characteristics were well preserved after the thermal PDMS modification step at high temperature,

* Corresponding author at: College of Science, China University of Petroleum (East China), Qingdao Shandong 266580, People's Republic of China
E-mail addresses: kangzixi69@126.com (Z. Kang), dfsun@upc.edu.cn (D. Sun).

<http://dx.doi.org/10.1016/j.matlet.2016.11.088>

Received 11 September 2016; Received in revised form 21 November 2016; Accepted 24 November 2016

Available online 24 November 2016

0167-577X/ © 2016 Elsevier B.V. All rights reserved.

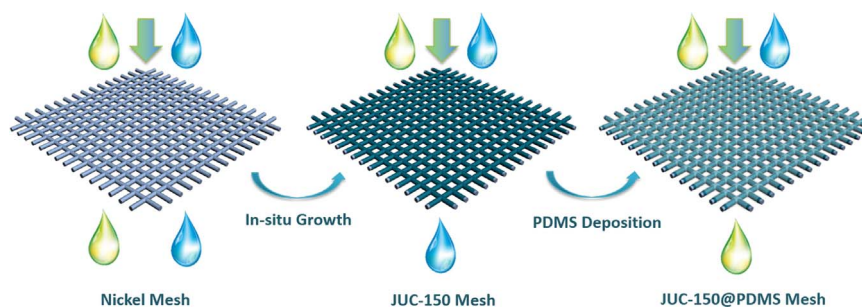


Fig. 1. Schematic illustration of the surface wettability switching of JUC-150 MOF mesh.

confirming the desired thermal stability of JUC-150 material.

Different magnification SEM pictures of the pristine JUC-150 mesh and JUC-150@PDMS mesh are shown in Figs. 2b and 2c. As seen in these pictures, JUC-150 crystals homogeneously covered the substrate surface, forming a continuous MOF layer with a roughness comparable to the size of the individual MOF crystals. After modification with PDMS, the outlines of the JUC-150 crystals could still be clearly distinguished (Figs. 2e and 2f), which means the MOF crystallinity was maintained well. This is consistent with the XRD results. The JUC-150@PDMS mesh exhibited smoother surface with a water contact-angle of 143.6° (Fig. 2d), suggesting the successful switching of the mesh surface wettability from hydrophilicity to hydrophobicity.

To investigate the interaction between JUC-150 and PDMS in JUC-150@PDMS mesh, XPS spectra were recorded and shown in the supporting information. As can be seen in Fig. S1b, the peak of Si 2p only appeared for JUC-150@PDMS, suggesting the successful modification of JUC-150 mesh with PDMS. We also noticed that the binding energy of Ni 2p shifted a little bit (Fig. S1c), which revealed the possible bond formed between the Ni centers of JUC-150 and O atoms from the PDMS [17].

We also extended this method to another MOF [$\text{Ni}_2(\text{L-asp})_2\text{Bipy}$, L-asp= L-aspartic acid, Bipy = 4'-4'-bipyridine] mesh and membrane [18]. The structure and morphology characterizations of $\text{Ni}_2(\text{L-asp})_2\text{Bipy}$ mesh and membrane before and after PDMS modification can be found

in supporting information (Fig. S2 and S3). The PDMS modification method shows potential in turning MOF membrane materials to suitable candidates for gas separation in humid conditions, such as reforming gas purification.

2.2. Water-oil separation

The pristine JUC-150 mesh is hydrophilic with a water contact angle close to 0° , compared with $143 \pm 2^\circ$ after PDMS modification. From the Wenzel equation [19], it can be observed that the apparent water contact angle is determined by the combined effect of surface morphology and the surface chemical composition. Since the surface chemical composition is fixed for a solid, the roughness can magnify the wettability levels of the solid surface to its extreme. In this case, the rough multi crystal surface raises either the hydrophilicity or hydrophobicity of MOF meshes before and after the modification.

Given the fact that the pristine JUC-150 and JUC-150@PDMS meshes exhibit hydrophilic and hydrophobic character respectively, the separation tests of gasoline-water were carried out on these meshes and the nickel mesh substrate (Fig. 3). When a mixture of water (dyed by acid red 18) and gasoline was poured into the filter with a nickel mesh substrate, both components passed through and fell into the baker. After the nickel mesh substrate was coated with the hydrophilic JUC-150 MOF layer, a water film was formatted on the pre-wetted

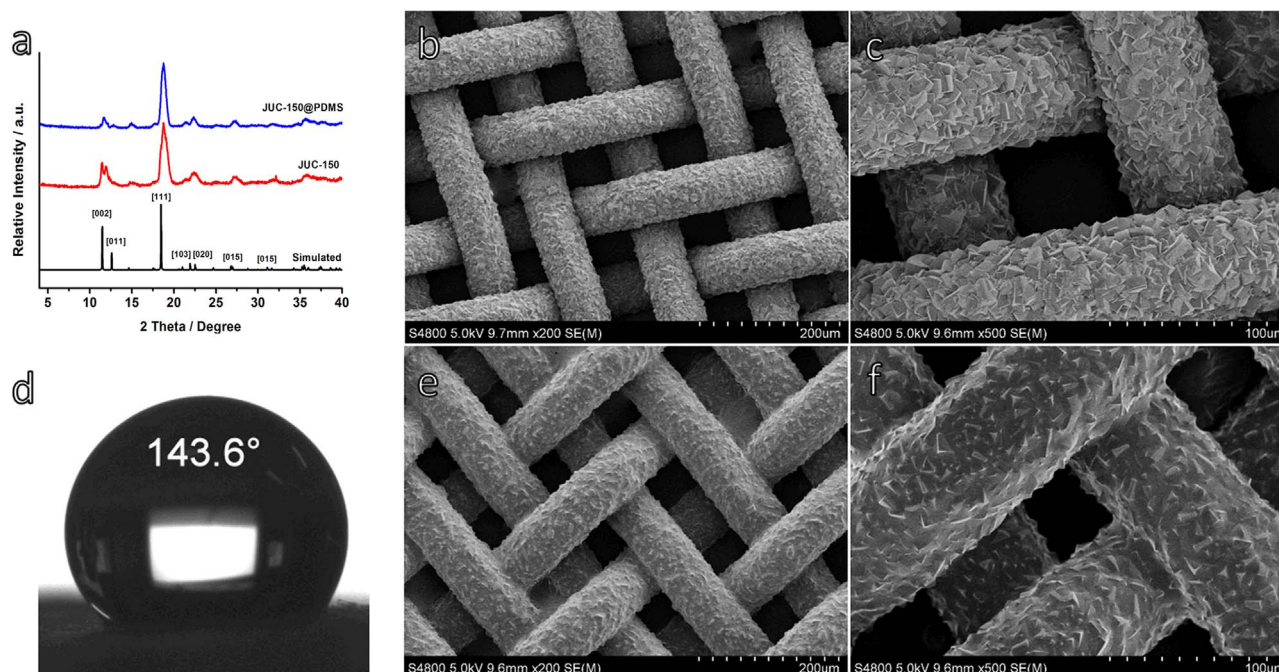


Fig. 2. (a) Powder X-ray Diffraction patterns of the simulated JUC-150 (black), JUC-150 mesh (red) and JUC-150@PDMS mesh (blue), respectively; (b, c) Different magnification top view SEM images of JUC-150 mesh; (d) Water contact-angle of JUC-150@PDMS mesh; (e, f) Different magnification top view SEM images of JUC-150@PDMS mesh. (For interpretation of the references to color in this figure legend, the reader is referred to the web version of this article.)

Download English Version:

<https://daneshyari.com/en/article/5463601>

Download Persian Version:

<https://daneshyari.com/article/5463601>

[Daneshyari.com](https://daneshyari.com)