



Sulphur poisoning of Ni catalysts used in the SNG production from biomass: Computational studies

Izabela Czekaj*, Rudolf Struis, Jörg Wambach, Serge Biollaz

Paul Scherrer Institut, General Energy Research Department (ENE), CH-5232 Villigen PSI, 5200 Villigen, Aargau, Switzerland

ARTICLE INFO

Article history:

Received 9 September 2010

Received in revised form 18 October 2010

Accepted 21 October 2010

Available online 15 December 2010

Keywords:

Nickel catalyst

Alumina support

Sulphur poisoning

DFT

Methanation

Metal deposition

Metal-support interactions

ABSTRACT

The purpose of this study was to investigate the sulphur deactivation mechanism during an industrial methanation process, but also after catalyst regeneration. In the present work we extended our computational investigations to study the adsorption of sulphur poisoning compounds on the Ni/Al₂O₃ catalyst. The focus was to study possible catalyst changes and thus the modified catalytic behaviour of the nickel particles, as well as to see differences in the poisoning behaviour, when sulphur adsorbs either on the Ni particle or on the support. This was done using Density Functional Theory calculations (StoBe) with cluster model and non-local functional (RPBE) approach. For modelling the catalyst, an Al₁₅O₄₀H₃₅ cluster has been selected representing the γ -Al₂O₃(1 0 0) surface, and Ni metal particles of different sizes were cut from a Ni(1 0 0) surface and deposited on the Al₁₅O₄₀H₃₅ cluster. Several poisoning agents have been found to be stable on both Ni clusters and alumina support such as COS, H₂S, or hydrogen thiocarbonates.

© 2010 Elsevier B.V. All rights reserved.

1. Introduction

Recently, surface modifications on a commercial Ni/Al₂O₃ catalyst during the production of methane from synthesis gas were investigated by *quasi in situ* X-ray photoelectron spectroscopy (XPS) [1,2]. Further, we studied the sulphur poisoning processes on the Ni/Al₂O₃ catalyst used for the methanation process [3]. The purpose of this study was firstly to investigate deactivation mechanisms caused by sulphur adsorption during an industrial methanation process and secondly possible regeneration routes. The reactivation attempt was done with water at methanation relevant temperature with idea to remove carbon and hydrocarbons from blocking nickel surface sites. It was reported by us [3] that after a reactivation the catalyst was active for a much shorter time when compared with a newly loaded Ni/Al₂O₃ catalyst. The samples had been collected from a methanation reactor fed with producer gas from the industrial biomass gasifier in Güssing (Austria). S 2p X-ray photoelectron spectroscopy (XPS) pointed at the presence of sulphide and sulphate, but the data were too noisy to reach more specific conclusions as well as the samples had been transported in air conditions. XANES analysis of S K-edge showed unequivocally that the catalyst could not have been deactivated by inorganic H₂S only, but more by organic-type sulphur compounds.

Also from other fields of research [4], it was observed that sulphur compounds, such as SO₂, significantly degraded the Pt electrocatalysts in fuel cells. Sulphur compounds deactivate heterogeneous catalysts by adsorbing to metal active sites, forming a strong chemical bond between sulphur atoms and the active metal catalysts. Another common air contaminant, carbonyl sulphide (COS), has not been studied in conjunction with SO₂ or H₂S. In industrial catalysts, considerable attention has been focused on the role of sulphur transition-metal complexes in catalysis poisoning [5], where also CS₂ and COS were found to be important sulphur-transfer reagents. Both compounds have been considered as possible sulphur sources for preparing thin layers of semiconductor materials.

Several studies have been initiated to understand the mechanism of the sulphur poisoning process, to improve the sulphur tolerance, and to find ways to regenerate the catalyst. It has been proposed that the mechanism of sulphur poisoning is very similar to that of the NO_x storage process [6,7]. Under lean conditions, SO₂ is oxidized on the precious metal site and then reacts with the support and the NO_x storage component. Under rich conditions, sulphur containing species interact with the noble metal and sulphides, such as PtS, are formed.

The effect of the carrier material and additives on the sulphur adsorption–desorption behavior was noticed for the first time by the researchers from Toyota [8]. By increasing the acidity of the support, they obtained a decrease of the sulphur deposit. The amount of the formed sulphated species was lower for the TiO₂ and SiO₂ in

* Corresponding author. Tel.: +41 056 310 4464; fax: +41 056 310 2199.

E-mail address: izabela.czekaj@psi.ch (I. Czekaj).

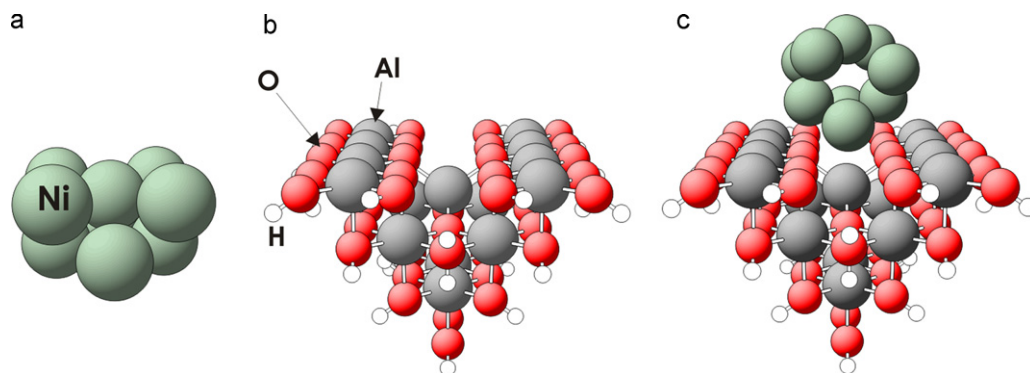


Fig. 1. Geometric structure of clusters: (a) $\text{Ni}_9(100)$, (b) $\text{Al}_{15}\text{O}_{40}\text{H}_{41}(100)$, (c) $\text{Ni}_9/\text{Al}_{15}\text{O}_{40}\text{H}_{35}$.

comparison to the $\gamma\text{-Al}_2\text{O}_3$ support. This suggests that the lower S deposit is more related to the improvement of the SO_2 poisoning resistance. The influence of different promoters on the sulphate decomposition temperature has also been studied [8,9]. It was observed that a beneficial effect is produced by doping Al_2O_3 with Li and afterwards mixing with TiO_2 . A further thermal stability improvement was recently obtained by using a Ti doped nanocomposite of Al_2O_3 and $\text{ZrO}_2\text{-TiO}_2$ as support [10].

In the present work we extended our computational investigations to study the adsorption of sulphur containing compounds on the $\text{Ni}/\text{Al}_2\text{O}_3$ catalyst for a better understanding of chemical processes appearing on regenerated catalysts. The focus was to study possible catalyst changes and the thus modified catalytical behaviour of the nickel particles, as well as to see differences in the poisoning behaviour when sulphur either adsorbs on Ni particles or on the support.

2. Computational details

In our DFT studies the Ni and $\gamma\text{-Al}_2\text{O}_3$ support surfaces are modelled by Ni_9 (Fig. 1a) and $\text{Al}_{15}\text{O}_{40}\text{H}_{35}$ clusters (Fig. 1b). Both clusters represent (100) surface of catalysts. For the $\gamma\text{-Al}_2\text{O}_3$, cluster neutrality with respect to the surface is achieved by saturating the peripheral oxygen centres with hydrogen atoms placed at the standard OH distance, $R_{\text{OH}} = 0.97 \text{ \AA}$. Fig. 1c shows

cluster $\text{Ni}_9/\text{Al}_{15}\text{O}_{40}\text{H}_{35}$, which represents nickel particle at the support.

The electronic structure of clusters was calculated by *ab initio* density functional theory (DFT) methods (program code StoBe [11]) using the non-local generalized gradient corrected functionals according to Perdew, Burke, and Ernzerhof (RPBE) [12,13], in order to account for electron exchange and correlation. All Kohn-Sham orbitals are represented by linear combinations of atomic orbitals (LCAO's) using extended basis sets of contracted Gaussians from atom optimizations [14,15]. During relaxation, the nickel atoms in the supported clusters had allowed to move in 3D space.

3. Results and discussion

Several poisoning agents have been found to be stable on both Ni clusters and pure alumina support (see Fig. 2), such as carbonyl sulphide (COS), hydrogen sulphide (H_2S), or hydrogen thio-carbonates in different orientations on the surface (OHOCS or SHOCO). The adsorption energy for particular adsorbates is shown in Table 1.

Our results clearly demonstrate that sulphur particles are not only stabilized on the nickel, but also on the support surface. The latter two species can be expected present at the catalyst surface during SNG production from biomass-based producer gas [16].

Carbonyl sulphide and hydrogen sulphide species have been found to be most stable adsorbates in the systems investigated

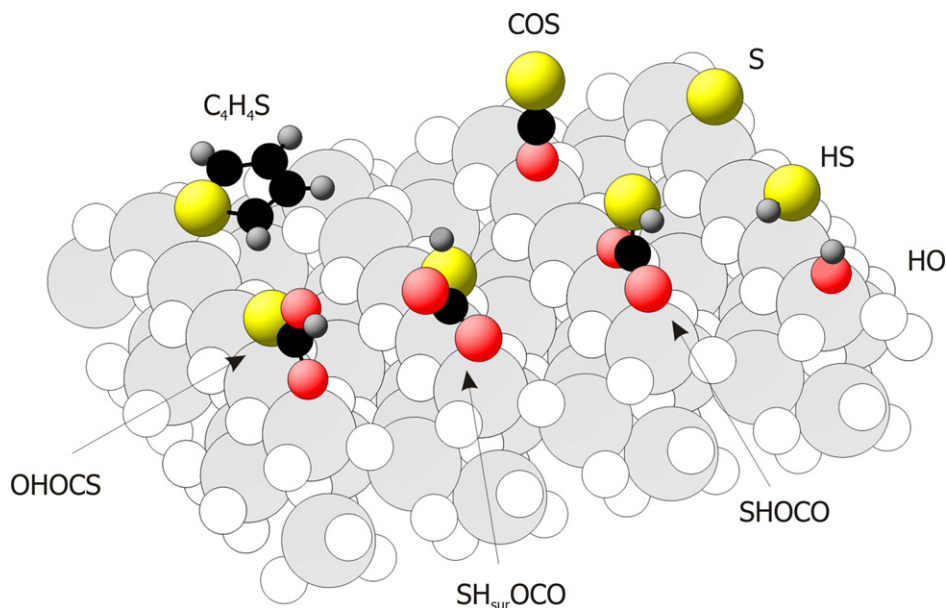


Fig. 2. Sulphur compounds at $\gamma\text{-Al}_2\text{O}_3$.

Download English Version:

<https://daneshyari.com/en/article/55886>

Download Persian Version:

<https://daneshyari.com/article/55886>

[Daneshyari.com](https://daneshyari.com)