



Fuel cell electrodes using carbon nanostructures

M. Lebert^{a,*}, M. Kaempgen^b, M. Soehn^c, T. Wirth^d, S. Roth^a, N. Nicoloso^c

^a Max-Planck-Institute for Solid State Research, D-70569 Stuttgart, Germany

^b University of California, Department of Physics and Astronomy, Los Angeles, CA, USA

^c TU Darmstadt, Department of Renewable Energies, D-64283 Darmstadt, Germany

^d University of Cambridge, Department of Engineering, Cambridge CB2 1PZ, UK

ARTICLE INFO

Article history:

Available online 23 December 2008

Keywords:

Carbon nanotubes
Fuel cell
GDE
HT-PEMFC
PAFC
PEMFC
SWNT
MWNT

ABSTRACT

The use of carbon nanotubes (SWNT, MWNT, and aligned CNT) for low and intermediate temperature fuel cells has been investigated with thin film CNT/Pt-electrodes of ($1 < d < 10 \mu\text{m}$). For membrane electrode assembly (MEA) the electrodes were combined either with Nafion[®] 117 or polycarbonate (PC) membranes wetted with H_3PO_4 . The fuel cell characteristics of the CNT-based MEAs were determined at atmospheric pressure, different catalyst concentrations (Pt) and temperatures ($\text{RT} < T < 150^\circ\text{C}$). The performance is competitive to well-established phosphoric acid (PAFCs) or polymer electrolyte membrane fuel cell (PEMFC), e.g. PBI/ H_3PO_4 . Liquid state processing of CNTs allows flexible electrode design and opens new ways for integrated and significantly mass-/volume-reduced fuel cell electrodes with high saving potential for catalyst and carbon material. Microsized high performance power supplies and battery chargers for consumer electronics are the most promising applications.

© 2008 Elsevier B.V. All rights reserved.

1. Introduction

A great deal of research is currently performed on fuel cells (FC) as energy conversion devices with hydrogen and C_1 (or higher) compounds as fuels. Due to efficiency advantages they are an interesting alternative to combustion engines, especially in the low temperature range ($T < 200^\circ\text{C}$). To achieve further improvement in performance and long-term stability materials, designs and production techniques have to be established, however. Carbon nanotubes (CNTs) have raised many expectations due to their unique properties, e.g. high (electro)chemical stability, high electrical conductivity and high surface area. Randomly oriented single or multiwalled carbon nanotubes (SWNTs, MWNTs) can be easily converted into highly conducting thin porous networks suitable for gas diffusion electrodes (GDEs) in FCs [1,2]. Partially aligned MWNTs grown on commercial carbon fibres [3] combine the well known properties of conventional carbon electrodes with the high specific surface area of MWNTs (up to $1000 \text{ m}^2/\text{g}$ [4]). Fully aligned nanocarbon materials can be prepared by the vertical growth of MWNTs on thermally insulating substrates allowing well-defined spatial distribution of properties. Aligned MWNTs are discussed as gas diffusion layers [5,6] and catalyst support [7,8].

The materials essentially differ with respect to the local structure and surface area and thus the actual state of the three-phase boundary catalyst/reactant gas/electrolyte. As main advantage CNTs allow flexible electrode design and processing, especially suited for small-scale applications, e.g. nano/micro-sized FCs with high power density.

2. Experimental

Carbon nanostructures with different ordering and morphology have been prepared as catalyst supports and tested in a home made fuel cell test bench at $\text{RT} < T < 150^\circ\text{C}$ under atmospheric pressure in PAFC and PEMFC configuration. In the following the main experimental results are presented.

2.1. Random, non-aligned CNT network electrodes

2.1.1. SWNT network electrodes

SWNTs made by high pressure CO disproportionation (HiPco [9,10]) from CNI/Unidym[®] are purified and functionalized by ultrasonication in conc. HNO_3 as reported in detail elsewhere [11]. Briefly, the oxidative treatment introduces oxygen surface defects ($-\text{OH}$, $-\text{C}=\text{O}$, $-\text{COOH}$ [1]) into the SWNT thereby enhancing their solubility in aqueous solutions and their conductivity [12]. In order to achieve a thin monolithic GDE with a hydrophobic gas diffusion part and a hydrophilic catalyst part the following procedure has

* Corresponding author. Tel.: +49 711 2572483; fax: +49 711 3052112847.
E-mail address: michael.lebert@daimler.com (M. Lebert).

been applied: half of the sonicated SWNT solution was mixed with a 60 wt% PTFE dispersion (Sigma–Aldrich®) at a ratio of 2:3. The SWNT/PTFE solution was filtered through a PC filter membrane ($A = 5 \text{ cm}^2$, pore size: $0.1 \mu\text{m}$), using a simple filter flask and moderate vacuum. The SWNTs and the PTFE particles form an entangled hydrophobic network, which serves as the hydrophobic part of the GDE. Afterwards, the rest of the SWNT solution was filtered/deposited on top of the network creating the hydrophilic layer. This way, a micro-sized two-component material with a confined hydrophobic and hydrophilic part has been achieved. After washing thoroughly with water, the catalyst solution ($0.1 \text{ M H}_2\text{PtCl}_6$ in isopropanol) was cast on to the hydrophilic side. Then, the entire network was annealed at 100°C under H_2 flow for 1 h to reduce the precursor to metallic Pt. For MEA preparation a PC filter membrane (pore size 10 nm) soaked with H_3PO_4 was sandwiched between two of the electrodes described above.

For fuel cell testing, the SWNT electrodes are installed in a home-built cell holder with meander flow fields and an effective electrode area of 3 cm^2 . The SWNT-GDEs were pressed with the hydrophobic side onto the flow fields, the hydrophilic side to the membrane. I – V curves were taken at atmospheric pressure with non-humidified gases as a function of temperature.

2.1.2. Spray-dried MWNT electrodes

Spray-dried CNT electrodes have been prepared by depositing MWNT/Pt inks with defined Pt/C ratios by an air-brush onto polymer electrolyte membranes (Nafion 117). The membrane was heated to 100°C to improve the contact between membrane and catalyst.

The MWNTs were wet chemically platinized as described in detail in [13]. Electrodes of different thicknesses (e.g. 1 and $6 \mu\text{m}$) were prepared from the same ink for performance tests at reduced Pt loading. In case of the $1 \mu\text{m}$ sample only 1/6 of the liquid ink was deposited. Hence, as the density of Pt (number of Pt particles per cm^3 carbon support) was kept constant the overall number of catalyst particles was reduced to 1/6.

Fuel cell tests of the spray-dried MWNT-MEAs were carried out in the same arrangement as described above, solely the active cell area was changed ($A = 10 \text{ cm}^2$). The cells were operated at 80°C with humidified H_2 and O_2 ($75\% < \text{r.h.} < 95\%$) to minimize ohmic losses of the electrolyte.

2.1.3. Control of catalyst composition

The efficiency of the catalyst preparation has been checked by X-ray fluorescence (XRF) after reduction of the hexachloroplatinate precursor and washing of the samples. No traces of Pt could be found in the (vaporized) filtrate indicating complete conversion of Pt^{4+} to metallic Pt and strong adherence of Pt to the CNT surface. Carbon loss also appears negligibly small, since no colour change of the filtrate was observed (already a few μg of CNTs would cause visible changes).

2.2. Aligned MWNTs for fuel cell electrodes

2.2.1. Partly aligned MWNTs on commercial carbon fibres

Partly aligned MWNTs on C-fibre substrates (carbon cloth, E-TEK® Co., USA) have been obtained by catalysed chemical vapour deposition (CCVD) in a 2" tube furnace (Carbolite®). The MWNTs are grown on the graphitic fibre supports from thermally evaporated Fe catalyst with a thickness of 0.7 nm on top of a sputtered Al_2O_3 (10 nm) support layer. The samples are heated in Ar flow of 1 l/min with a ramp rate of 20°C/min . The samples are annealed at 750°C in Ar/ H_2 atmosphere for 15 min to split the Fe film into nano-islands and catalysing the MWNT growth while feeding C_2H_2 for 10 min.

2.2.2. Fully aligned and polymer stabilized MWNTs

For growth of fully aligned MWNTs a Si wafer has been coated with a 10-nm thick Fe film and exposed at 800°C to NH_3 (4 min) and to C_2H_2 (10 min) at 1.8 mbar . Vapour deposition of parylene-N [14] was used to mechanically stabilize the fragile MWNT structure. The MWNT/parylene film was then removed from the silicon substrate by etching in 30 wt% KOH solution at $80\text{--}100^\circ\text{C}$ (etching results in HF are similar [15]). After a few minutes the composite film separates from the substrate leaving a flexible and stable film. Plasma oxidation was then performed to remove excess parylene [16]. Uncovering of the MWNTs is necessary to allow good electrical contact transport of (humidified) gases through the tubes [17].

3. Results and discussion

3.1. Thin film integrated SWNT electrodes

The preparation technique described above allows a flexible electrode architecture since desired functionalities can be introduced sequentially. This is shown by the layered structure of the GDE in Fig. 1b. The monolithic thin film electrode comprises the hydrophobic GDL (Fig. 1a) and the hydrophilic catalyst layer (Fig. 1c). The GDL part exhibits high porosity which is crucial for efficient gas supply and removal of product water. The corresponding TEM image shows the interpenetrating network of nano-sized SWNT bundles ('SWNT' in Fig. 1a) and micro-sized PTFE ('Teflon', Fig. 1a). The white arrows indicate interfaces between the hydrophobic and hydrophilic components. The morphology of the catalyst part (Fig. 1c) corresponds to bundles of platinized SWNTs (dark dots).

As shown by the TEM images in Fig. 2 the catalyst (dark spots) is distributed homogeneously in the CNT network. For statistical evaluation different sample regions (red circles Fig. 2a,b) were chosen to determine catalyst size and distribution (Fig. 2b). Fig. 2c displays the structure of the catalyst layer comprising open tube ends (x), aligned tubes (y) and Pt particles (z).

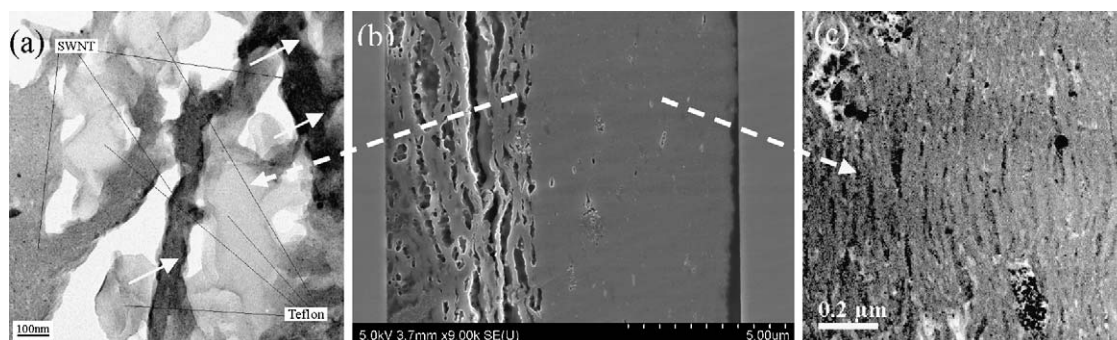


Fig. 1. (a) SWNT/PTFE-gas diffusion layer (TEM), (b) cross-section of integrated SWNT electrode (SEM), and (c) SWNT/Pt catalyst layer (TEM).

Download English Version:

<https://daneshyari.com/en/article/57361>

Download Persian Version:

<https://daneshyari.com/article/57361>

[Daneshyari.com](https://daneshyari.com)