



## Ir–C xerogels synthesized by sol–gel method for NO reduction

Zhi Liu<sup>a,b</sup>, Aiqin Wang<sup>a</sup>, Xiaodong Wang<sup>a</sup>, Tao Zhang<sup>a,\*</sup>

<sup>a</sup> State Key Laboratory of Catalysis, Dalian Institute of Chemical Physics, Chinese Academy of Sciences, Dalian 116023, China

<sup>b</sup> Graduate School of Chinese Academy of Sciences, Beijing 100039, China

### ARTICLE INFO

#### Article history:

Available online 21 April 2008

#### Keywords:

Carbon xerogels  
Iridium  
NO reduction  
Carbon monoxide  
Sol–gel

### ABSTRACT

Iridium–carbon (Ir–C) xerogels were synthesized via a one-pot sol–gel polycondensation of hexachloroiridic acid, resorcinol and formaldehyde, followed by carbonization in a nitrogen atmosphere at 500–1000 °C. The samples were characterized by various techniques including N<sub>2</sub> adsorption, XRD and TEM. The N<sub>2</sub> adsorption showed that the Ir–C samples were of microporous structures, and their specific surface areas increased with the pyrolysis temperature. Both the XRD and TEM revealed that the Ir particles in the Ir–C samples were highly dispersed in the carbon matrix, in contrast with the large Ir particles in the Ir/C sample which was obtained by impregnation. The Ir–C xerogels exhibited high activities and selectivities towards N<sub>2</sub> in the reduction of NO with carbon or CO. In particular, the Ir–C samples behaved much stably than the Ir/C, demonstrating the superiority of the one-pot synthesis method.

© 2008 Elsevier B.V. All rights reserved.

### 1. Introduction

Carbon gels are a kind of novel nanostructured carbon materials. They can be obtained by pyrolysis of organic gels, which are formed by the sol–gel polycondensation of certain organic monomers, such as resorcinol with formaldehyde, following Pekala's method [1,2]. The advantages of the carbon gels over the conventional carbon materials are the well-developed and controllable porosities, high surface areas, various shapes in macroscopic scale, and the easy incorporation of metal or metal oxide into the carbon framework. These unique properties make them promising materials as catalysts, catalyst supports and adsorbents as well. Over the past decade, a great deal of research effort has been made to understand how the synthesis parameters, such as the initial pH of the R–F solution, the catalyst employed, and the drying procedure, are affecting the resulting nanostructures, in particular the porosities and surface areas [3–8]. By contrast, the applications of carbon gels, especially in catalysis, are less exploited, and only a few examples have been reported so far [9–14].

Moreno-Castilla and co-workers firstly introduced transition metals into the organic aerogels and investigated the catalytic performances of Pt–carbon for xylene combustion [14]. Fortunately, they found that the activity of the catalysts increased with Pt particle size, thus the catalytic performance is stable, even in an oxidizing atmosphere. They also found that the transition metals

incorporated into the carbon aerogels could catalyze the graphitization of carbon aerogels, which made it possible to produce graphite materials at 1000 °C [11]. The same group also investigated the catalytic performance of metal oxide–carbon aerogels for the isomerization of 1-butene [9].

In our previous work [15], we synthesized Cu–carbon and Co–carbon xerogels and investigated their potentials as catalysts for NO reduction. Although a very high NO conversion could be obtained at above 500 °C over these two metal-containing carbon xerogels, the activity decay still occurred with prolonging the time on stream due to the carbon gasification. To minimize the gasification of the synthesized carbon xerogels, either decreasing the reaction temperature or employment of an external reductant will be desirable. Based on our own previous work [16,17] and other literature reported work [18,19], highly dispersed iridium has been proved to be a very active and selective catalyst for NO reduction with hydrocarbons or CO even under the presence of oxygen in the feed stream. Therefore, in the present work, we incorporated Ir into the carbon xerogels and investigated its catalytic performances for NO reduction, with carbon itself or by addition of CO as the reductant.

### 2. Experimental

Ir-containing carbon xerogels (denoted as Ir–C) were prepared following the method described by Moreno-Castilla et al. [9]. Briefly, 6.160 g (0.056 mol) of resorcinol, 7.056 g (0.392 mol) of water and 0.537 g of hexachloroiridic acid (H<sub>2</sub>IrCl<sub>6</sub>, 44 wt.%) were mixed and stirred for 10 min. The amount of hexachlor-

\* Corresponding author. Tel.: +86 411 84379015; fax: +86 411 84691570.  
E-mail address: [taozhang@dicp.ac.cn](mailto:taozhang@dicp.ac.cn) (T. Zhang).

iridic acid added to the solution was calculated to obtain 1% by weight of the Ir in the initial solution. Then, 9.080 g (0.112 mol) of formaldehyde (37 wt.%) was added and the resulting solution was stirred until the organic gel formation. Afterwards, the organic gel was cured at 85 °C under vacuum for 7 days. The aqua-gels thus obtained were dried in N<sub>2</sub> atmosphere in a tubular furnace at 110 °C overnight to obtain the Ir-containing organic xerogels. Ir-C xerogels were finally obtained by pyrolyzing the Ir-containing organic xerogels at a specified temperature (500, 750 or 1000 °C) with a heating rate of 2 °C/min under N<sub>2</sub> for 5 h. A blank sample (C) was also prepared under the same conditions as those for the Ir-C, but without the addition of the Ir precursor. The exact iridium content of the Ir-C xerogel was determined by burning a fraction of it at 650 °C under air flow up to constant weight. The Ir-C or C xerogels will be referred to in the text by adding the carbonization temperature to the xerogel name, e.g., Ir-C1000 means a carbonization temperature of 1000 °C. For comparison, the catalyst Ir/C was also prepared by impregnating the above-prepared blank carbon xerogel (C1000) with the hexachloroiridic acid, and then by drying and calcination in N<sub>2</sub> at 500 °C for 3 h.

Textural characterizations were carried out by adsorption of N<sub>2</sub> at -196 °C on a Micromeritics ASAP 2010 apparatus. Before measurement, the samples were degassed firstly at 383 K for 3 h and then at 623 K for 5 h under vacuum. The specific surface areas (*S*<sub>BET</sub>) of samples were calculated by BET equation, and the micropore surface area (*S*<sub>mic</sub>) and micropore volume (*V*<sub>mic</sub>) were determined by *t*-plot calculations.

Powder X-ray diffraction (XRD) patterns were collected with D/Max-βb diffractometer using Cu Kα radiation source (λ = 0.15432 nm). A continuous mode was used to collect data from 10° to 80° of 2θ at a scanning speed of 5°/min.

Transmission electron microscopy (TEM) images were obtained on a JEOL 2000EX electron microscope operating at an accelerating voltage of 120 kV. The samples were pulverized in an agate mortar, ultrasonic dispersed in ethanol and then dropped onto the carbon-coated copper grids prior to measurement.

The catalytic activities of the Ir-C xerogels for NO reduction were measured in a plug flow reactor using 0.2 g of the Ir-C sample in a gas mixture containing 2000 ppm NO (and 2000 ppm CO) in He at a total gas flow rate of 60 ml/min (corresponding to GHSV of 18,000 h<sup>-1</sup>). The outlet gas mixture was analyzed by an on-line gas chromatograph (Agilent 6890N) equipped with a thermal conductivity detector (TCD), a Porapak QS column and a 13X molecular sieve column. NO conversion to N<sub>2</sub> (*Y*<sub>N<sub>2</sub></sub>) or N<sub>2</sub>O (*Y*<sub>N<sub>2</sub>O</sub>), and the selectivity to N<sub>2</sub> (*S*<sub>N<sub>2</sub></sub>) or N<sub>2</sub>O (*S*<sub>N<sub>2</sub>O</sub>) were defined as

$$Y_{N_2} = \frac{2N_2}{NO_{inlet}} \quad Y_{N_2O} = \frac{2N_2O}{NO_{inlet}}, \quad S_{N_2} (\%) = \frac{Y_{N_2}}{Y_{N_2} + Y_{N_2O}} \times 100 \quad S_{N_2O} (\%) = \frac{Y_{N_2O}}{Y_{N_2} + Y_{N_2O}} \times 100$$

### 3. Results and discussion

#### 3.1. Textural properties of Ir-C catalysts

Fig. 1 shows the N<sub>2</sub> adsorption-desorption isotherms of the C1000 and the three Ir-C samples which were obtained by pyrolysis at different temperatures. It can be seen that all of the four samples show typical type I isotherms, indicating their microporous structures. Table 1 lists some textural parameters of the four samples. A comparison between the C1000 and the Ir-C1000 in their textural properties shows that the incorporation of Ir only slightly decreased the BET surface area and the micropore volume. On the other hand, among the three Ir-C samples, we can

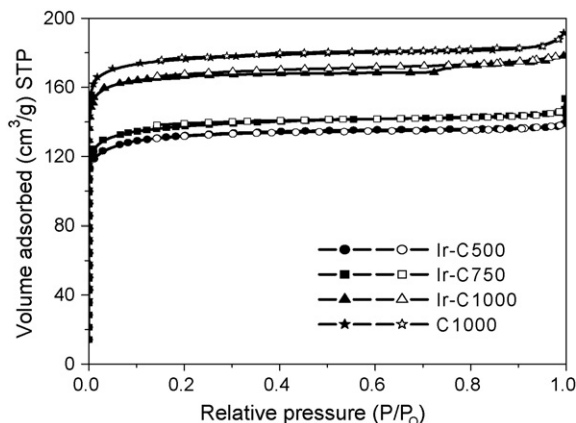


Fig. 1. Adsorption isotherms of N<sub>2</sub> on Ir-C samples prepared by pyrolysis at different temperatures. Closed symbols: adsorption isotherm; open symbols: desorption isotherm.

Table 1  
Textural properties of Ir-C xerogels derived from sol-gel process

Samples	Ir content <sup>a</sup> (%)	<i>S</i> <sub>BET</sub> (m <sup>2</sup> /g)	<i>S</i> <sub>mic</sub> (m <sup>2</sup> /g)	<i>V</i> <sub>mic</sub> (cm <sup>3</sup> /g)
C1000	0	543	507	0.25
Ir-C500	3.86	442	378	0.18
Ir-C750	4.73	474	427	0.20
Ir-C1000	4.91	488	439	0.21

<sup>a</sup> Metal content was determined by pyrolysis under air.

clearly see that both the specific surface areas and the pore volumes increased with the pyrolysis temperature.

#### 3.2. Characterization by XRD and TEM

Fig. 2 shows the XRD patterns of the three Ir-C samples. For comparison, those of the blank sample C1000 and the corresponding supported Ir/C1000 sample are also presented. All of the carbon xerogel samples, with or without Ir in the matrix, exhibit two broad peaks at ~22° and ~43° corresponding to amorphous carbon structure [11,15]. Besides, when Ir was introduced into the carbon matrix by impregnation (Ir/C1000), three strong diffraction peaks at 2θ = 41°, 47° and 69° are observed, which are due to the presence of metallic Ir phase [19]. The sharp peaks of metallic Ir suggest that a poor dispersion of Ir particles on the Ir/C1000 sample, which is very different from other commercial metal

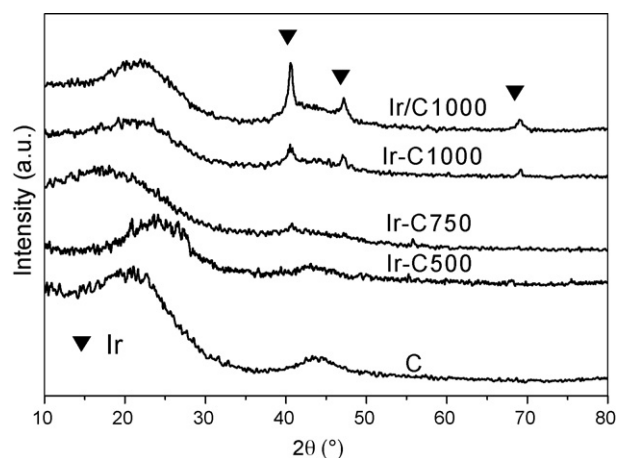


Fig. 2. X-ray diffraction patterns of different C and Ir-C samples.

Download English Version:

<https://daneshyari.com/en/article/57505>

Download Persian Version:

<https://daneshyari.com/article/57505>

[Daneshyari.com](https://daneshyari.com)