



Hazardous animal waste carcasses transformation into slow release fertilizers

Patrick Sharrock^{a,*}, Marina Fiallo^a, Ange Nzihou^b, Mouna Chkir^b

^a LERISM, Paul Sabatier University, Castres 81104, France

^b RAPSODEE, Ecole des Mines d'Albi-Carmaux, Albi 81013, France

ARTICLE INFO

Article history:

Received 30 September 2008

Received in revised form 16 December 2008

Accepted 17 December 2008

Available online 27 December 2008

Keywords:

Animal by-products

Slow release fertilizer

Calcium phosphate ashes

ABSTRACT

Because of the need to address disposal of materials infected with pathogens new regulations have come into effect for the transport and disposal of dead farm animals or carcasses. For precautionary reasons, disposal to landfill, composting, biogas generation or fertilizer use are banned recycling paths because of incomplete knowledge about contamination transmission paths. Thermal treatment is recognized as a safe elimination process. Animal wastes have a high calorific value (above 16 MJ/kg). However, combustion of the organics leaves mineral residues (near 30%). The ashes contain mostly calcium and phosphate with some sodium, potassium and magnesium. We have examined the transformation of the ashes into a slow release fertilizer. We used a mixture of acids to partly dissolve the combustion residues and form slurry. In a second step, base was added to neutralize and solidify the reaction mixture. The final product was a whitish polycrystalline solid. Leaching tests were made to evaluate the nutrient release rate in laboratory columns. Water leachates were analyzed for up to ten pore-bed volumes and showed, as expected, large differences in release rates. Nitrate release was slowed and phosphate did not level even after ten pore-bed volumes. This demonstrates that insoluble precipitates (gypsum) contribute to control soluble ion release.

© 2009 Elsevier B.V. All rights reserved.

1. Introduction

Dead animals and abattoir by-products represent nearly 30% of the live weight of processed animals. Animal by-products are classified in three different categories according to European regulation (CE) 1774/2002 which entered into effect in 2003. Class 1 concerns products suspected of carrying infectious diseases, particularly encephalitis, as well as contaminated by illicit or dangerous substances. Cadavers from wild, domesticated or zoo animals also enter this category. Class 2 pertains to farm animals found dead or containing medicinal residues. Class 3 is attributed to animal remnants originating from abattoir processing of human food grade certified live animals. This class can be valorized, usually by separating fats from lean components, and producing combustible lipids and meat and bone meal (MBM) for feed or fertilizer. Class 2 products can also be valorized, but not in animal feed, whereas class 3 must be destroyed or co-incinerated [1,2].

In France, an average of 2.8 million tones of animal by-products is treated annually, including 1.8 million tones of class 3 materials. France represents 18% of the European production which totals over 15 million tones. Forty-nine percent goes directly into energy production, 21% into pet food, 17% serves in oil chemistry, 5% in animal

feed, 3% in human food, only 2% serves as fertilizer [3] and the rest in fuel such as biodiesel [4].

Products allowed in pet food include transformed animal protein, gelatins, blood components, calcium phosphates, hydrolyzed feathers, grease and fish oils. The dangerous class 1&2 products are incinerated (or co-incinerated with other wastes) as illustrated in Fig. 1. This process releases combustion gases to the atmosphere, allows recovery of steam, and leaves behind bottom ashes and fly ashes to be dealt with [5]. The increasing cost of land-filling thermal process residues is making incineration more expensive.

We have previously examined MBM ashes and reported on their properties [6,7] and potential beneficial reuse as phosphate minerals [8]. In this report, we describe how the ashes from duck waste carcasses can be chemically transformed into a slow release fertilizer (SRF).

The availability of plant nutrients in the soil is fundamental to improve growth and crop yields. The extent of P movement in soil is known to be dependent on moisture [9]. Phosphate fertilizer is also related to tillage [10]. Because phosphate is the usual limiting nutrient for the formation of algal blooms, phosphate losses by runoff and leaching should be minimized in agricultural land. SRF is an answer in this respect. Seasonal variations in soil N fertilizers have been correlated to water leaching [11], and application rates should not exceed crop removal rate to prevent nitrate pollution [12]. Monitoring soil solution N concentrations are recommended as well as using multiple applications of less soluble N sources (urea) to maintain optimum N concentrations at different times during the

* Corresponding author at: Department of Chemistry, Avenue Pompidou, Castres 81104, France. Tel.: +33563621159; fax: +33562264783.

E-mail address: Patrick.sharrock@iut-tlse3.fr (P. Sharrock).

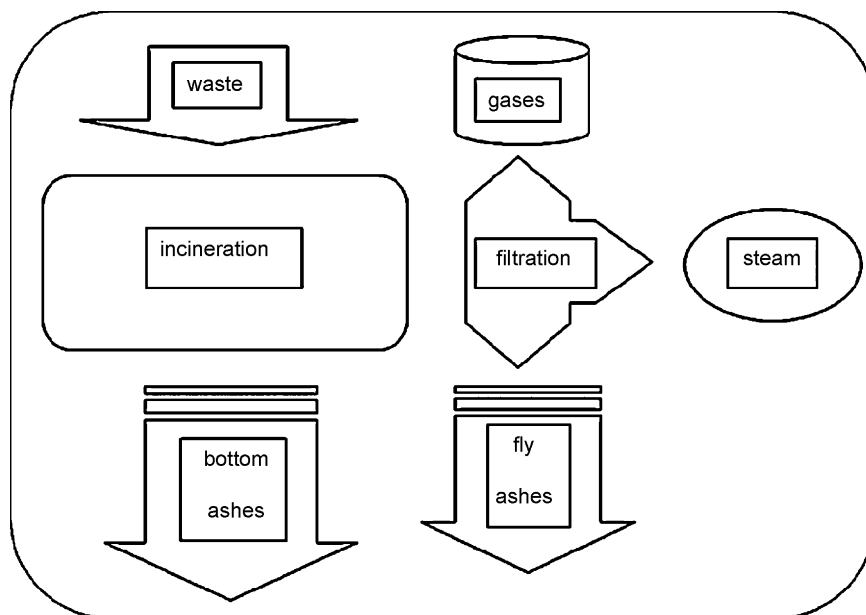


Fig. 1. Flow diagram for the thermal destruction of animal by-products.

growing season. Again, a SRF would be a very practical solution to simplify fertilizer management [13]. The diffusion and reaction processes in soil of phosphate and calcium has been discussed [14]. It is now recognized that nutrient exports are related to excessive fertilizer loadings particularly in high rainfall zones [15].

Slow-release fertilizers are generally categorized into one of several groups: palletized or matrix based [16], chemically altered [17], coated [18] or infiltrated into zeolite reservoirs [19]. Because nutrients are released at a slower rate throughout the season with SRF, plants are able to take up most of the nutrients without waste by leaching [20]. SRF is also more convenient, since less frequent application is required [21].

2. Experimental

2.1. Animal wastes

Duck carcasses were placed in a ventilated muffle furnace and heated to 750 °C for 1 h using a 2°/min. heating rate. After cooling to room temperature, the ashes were crushed with a mortar and pestle and sieved to pass a 2 mm mesh. The yield of white to gray colored ashes was close to 30% of the starting weight. Samples were further ground to very fine powder for infrared spectroscopy (Mattson Genesis FTIR) and X-ray diffraction (Philips Xpert) analysis.

2.2. Formation of slow release fertilizer

Chemical transformation was operated in polyethylene vials by introducing 10 g of ashes into 10 ml of acid. The acids used were sulfuric acid, phosphoric acid or nitric acid at 10% by weight concentration. The acid reaction produced foam and the frothing slowly subsided after 1 h. The still acid suspension was neutralized to pH 7 using the aqueous bases ammonium hydroxide or potassium hydroxide. Following this exothermal reaction, the suspension was mixed with a spatula to form a paste which solidified during the next 5 min. The SRF solids were broken into 5 mm granules to perform the leaching tests.

2.3. Leaching tests

Leaching experiments were carried out in glass chromatography columns equipped with N°3 sintered glass filters. Free flowing sand

was mixed with 10% by weight of the SRF granules and packed into the columns and covered with glass wool. After measuring the volume of water need to saturate the solids in the column, leaching events were performed by introducing one bed volume of distilled water into the column and collecting the leachates exiting the column by gravity at one atmosphere pressure. Calcinite (a mixed ammonium and calcium nitrate salt from Norsk Hydro) was used as a totally soluble fast release fertilizer to compare leaching rates under identical experimental conditions. Sulfate, nitrate and phosphate anion concentrations were measured by ion chromatography (Metrohm) using a sodium hydroxide and carbonate buffer at pH 10. Small samples of the granules were extracted from the columns after the leaching events to analyze the remnants by FTIR (Mattson Genesis). Thermogravimetric analysis was performed under air atmosphere with a SETARAM ATG92 instrument.

3. Results and discussion

3.1. Formation and reactivity of calcined bone

Duck carcasses begin to burn with emission of smoke at 300 °C. At 500 °C the charred residues are dark black but after combustion at 750 °C the ashes are off white. Industrial destruction of MBM implies contact with flames at temperatures near 1000 °C. MBM has exothermal combustion energy of 1.7 kJ/g. We preferred to expose the carcasses for 1 h at temperatures below 850 °C to prevent carbonate decomposition and sintering of the minerals. Thus the ashes reacted quickly with the acids, carbon dioxide gas escaped from the reaction mixture and the acids penetrated the porous calcined bone structures.

We previously showed the combustion residues are closely comparable to hydroxyapatite minerals [7]. Acid dissolution partly produces hydrogenphosphate anions and releases calcium ions. These ions recombine following neutralization to form a variety of sparingly soluble salts including monetite or brushite and gypsum. However, nitrate salts remain soluble but trapped into the composite matrix.

3.2. Analysis of slow release fertilizers

The X-ray diffraction analysis of the chemically transformed ashes is difficult due to the numerous products obtained when sul-

Download English Version:

<https://daneshyari.com/en/article/581755>

Download Persian Version:

<https://daneshyari.com/article/581755>

[Daneshyari.com](https://daneshyari.com)