



# Estimation of continuity of electroactive inorganic films based on apparent anti-Ohmic trend in their charge transfer resistance



Maria A. Komkova<sup>a</sup>, Elena V. Karpova<sup>a</sup>, Grigory A. Sukhorukov<sup>a</sup>, Alexey A. Sadovnikov<sup>b</sup>, Arkady A. Karyakin<sup>a,\*</sup>

<sup>a</sup> Chemistry Faculty of M.V. Lomonosov Moscow State University, 119991, Moscow, Russia

<sup>b</sup> Institute of General and Inorganic Chemistry, Russian Acad. Sci., 119991, Moscow, Russia

## ARTICLE INFO

### Article history:

Received 13 July 2016

Received in revised form 27 September 2016

Accepted 27 September 2016

Available online 28 September 2016

### Keywords:

hexacyanoferrate

Prussian Blue

impedance

charge transfer resistance

continuity

## ABSTRACT

We report on the microscopy-free, pure electrochemical approach for estimation of the continuity of electroactive inorganic films. Impedance spectra of the transition metal hexacyanoferrate films, electrochemically deposited under the optimized conditions, have been fitted to the Randles-type equivalent circuit, complicated by diffusion impedance with reflective boundary conditions, connected in series to the charge transfer resistance. An apparent anti-Ohmic trend is revealed in the sharp decrease of the latter with an increase in amount of the deposited inorganic film commonly presuming its thickness. Assigning charge transfer resistance to the resistance of the electrode|film interface, its observed decrease with subsequent saturation is explained in terms of an increase of the interface area until the entire electrode is covered with the inorganic film completely. Scanning electron microscopy (SEM) confirms the “anti-Ohmic” and saturation regions correspond to the partially covered and fully covered electrode surfaces, respectively. The dependence of charge transfer resistance on the amount of the deposited film thus provides an estimation of the continuity of inorganic films, which is highly important in a view of their practical applications. Except for cost efficiency, microscopy-free tools are attractive because in some cases, for instance for recessed electrodes, microscopy is hardly applicable.

© 2016 Elsevier Ltd. All rights reserved.

## 1. Introduction

Electroactive inorganic films immediately after discovery electroactivity of Prussian Blue [1–3] attracted a specific attention due to their unique properties. Among them transition metal hexacyanoferrates have already found wide use in analytical applications [4]. Of particular interest Prussian Blue is thought to be advanced electrocatalyst for hydrogen peroxide reduction: in neutral aqueous media, favorable for applications in life science as well as for biosensors, Prussian Blue is three orders of magnitude more active (in terms of 1000 times higher electrochemical rate constant) providing three orders of magnitude improved sensitivity of the corresponding sensors, and three orders of magnitude more selective compared to the commonly used platinum [4]. Nano-structuring the electrocatalyst onto an inert electrode supports results in elaboration of the electrochemical sensor with outstanding performance characteristics [5,6]. Despite non-iron

transition metal hexacyanoferrates being silent in the electrocatalysis of  $\text{H}_2\text{O}_2$  reduction [7], they serve as excellent matrixes for stabilization of Prussian Blue providing “super-stable” sensors [8].

Wide practical applications of transition metal hexacyanoferrates initiated an interest to study their fundamental properties, particularly charge transfer peculiarities. Prussian Blue is true redox film displaying at its redox potential (i) the highest conductance in terms of both maximum conductivity and the largest electron diffusion coefficient [9], (ii) the lowest charge transfer resistance at the electrode–film interface [10], as well as (iii) the maximum capacitance [11]. The latter was proposed to estimate the thickness of Prussian Blue film [12]. Impedance investigations were carried out also for cupric [13], cobalt [14] and nickel [15] hexacyanoferrates. We note that, transition metal hexacyanoferrates used in certain impedance studies [10,13,15,16] were, according to their cyclic voltammograms, of non-regular structure or even poor quality.

Accordingly, initial objective of the present study was to investigate charge transfer properties of electroactive inorganic films, synthesized under optimal conditions achieving their regular structure with the highest catalytic activity and/or stability.

\* Corresponding author at: M.V. Lomonosov Moscow State University, Lenin Hills, Moscow 119991, Russia.

E-mail address: [karyakin@analyt.chem.msu.ru](mailto:karyakin@analyt.chem.msu.ru) (A.A. Karyakin).

Indeed, in contrast to previous studies on charge transfer resistance reporting its independence of the amount of Prussian Blue deposited [10,16], we've found its sharp decrease with an increase in amount of inorganic film. We've found that the discovered apparent anti-Ohmic trend in charge transfer resistance with its subsequent saturation correlates with continuity of inorganic films thus providing a microscope-free approach for estimation of the latter.

## 2. Experimental

### 2.1. Materials

Experiments were carried out with Millipore Milli-Q water (resistivity 18.2 M $\Omega$  cm at a room temperature). Inorganic salts (FeCl<sub>3</sub>·6H<sub>2</sub>O, NiCl<sub>2</sub>·6H<sub>2</sub>O and K<sub>3</sub>[Fe(CN)<sub>6</sub>]) were obtained at the highest purity from Reachim (Russia) and used as received. Glassy carbon disk electrodes (SU-2500, 2.0 mm in diameter) pressed in Teflon were used as working electrodes. Prior to use, the working electrodes were mechanically polished in a water suspension of alumina (Sigma-Aldrich) first with the particle size of 0.3  $\mu$ m up to a mirror finish observed, then with the particle size of 0.05  $\mu$ m until a stable voltammograms with minimum capacitance obtained.

### 2.2. Instrumentation

Deposition of transition metal hexacyanoferrates, as well as their characterization by cyclic voltammetry, was carried out in a three-compartment electrochemical cell with Ag|AgCl |1 M KCl reference. PalmSens potentiostat/galvanostat (PalmSens Instruments BV, Netherlands) interfaced to PC was used.

Impedance spectra were recorded with Solartron 1255 frequency response analyzer (Solartron, UK). Impedance measurements were carried out in electrochemical cell with the common space of working and platinum cylinder auxiliary electrode, the latter encircling working electrode, and Ag|AgCl |1 M KCl reference, connected through Luggin capillary.

Scanning electron microscope Carl Zeiss NVision 40 (Carl Zeiss, Germany) was used to observe the surface morphology.

### 2.3. Methods

Electrodeposition of Prussian Blue was carried out by cycling the applied potential from 0.4 V to 0.75 V at a sweep rate of 0.02 V s<sup>-1</sup> during from 1 to 4 cycles. The growing solution contained 4 mM of K<sub>3</sub>[Fe(CN)<sub>6</sub>], 4 mM FeCl<sub>3</sub>·6H<sub>2</sub>O and 0.1 M KCl in 0.1 M HCl [5]. For deposition of Ni hexacyanoferrate the solution containing 0.5 mM K<sub>3</sub>[Fe(CN)<sub>6</sub>], 1 mM NiCl<sub>2</sub>·6H<sub>2</sub>O and 0.5 M KCl in 0.1 M HCl was used. Solution pH of 0.1 M KCl with 0.1 M HCl supporting electrolyte was approximately 1.2. The deposition was carried out by cycling the applied potential from 0.0 V to 0.75 V at a sweep rate of 0.1 V s<sup>-1</sup> during from 1 to 15 cycles [8]. After deposition the transition metals hexacyanoferrate films were activated electrochemically by cycling in the background electrolyte until a stable voltammogram was obtained and then annealed at 100 °C during 1 h to improve operational stability removing weakly bounded water.

An amount of the deposited Prussian Blue was calculated integrating current peaks in cyclic voltammograms and assuming a transfer of 4 electrons per unit cell [17].

Impedance spectra were recorded at a room temperature applying sine-wave voltage amplitude of 5 mV at the redox potential of transition metal hexacyanoferrate found from its cyclic voltammograms in the same solution.

All experiments were carried out in air saturated solutions. Current values were recalculated to geometric electrode area.


The micrographs were recorded with the scanning electron microscope operating at 7.00 kV accelerating voltage and from 4.6 to 5.1 mm working distance with InLens detector. The specimens were coated with 2 nm chromium film.

## 3. Results and discussion

Since, as mentioned, a significant part of impedance studies was carried out with irregular or even poor quality transition metal hexacyanoferrate films, special attention has been paid to deposit them under the optimized conditions [4,5,8]. Fig. 1 a displays cyclic voltammograms of Prussian Blue modified electrodes in the supporting electrolyte. Sharp current peaks with separation less than 30 mV point to regular structure of inorganic film; the conclusion is made on the basis of spectroelectrochemical investigations carried out already 35 years ago [2]. Similar conclusion can be made for the deposited Nickel hexacyanoferrate from its cyclic voltammograms shown in Fig. 1 b.

Impedance spectra of Prussian Blue modified electrodes recorded at different dc potentials have shown that the lowest impedance values are recorded at the Prussian Blue|Prussian White redox potential confirming its property as a true redox film (above). All subsequent impedance spectra have been taken at the film redox potential.

Fig. 2 displays impedance spectra of Prussian Blue modified electrodes with different amount of inorganic film. As seen, the impedance spectra are successfully fitted to the simplest equivalent circuit valid for conducting polymers (Fig. 2, inset) [18]. Here  $R_s$  is solution resistance,  $R_{ct}$  is charge transfer resistance, CPE

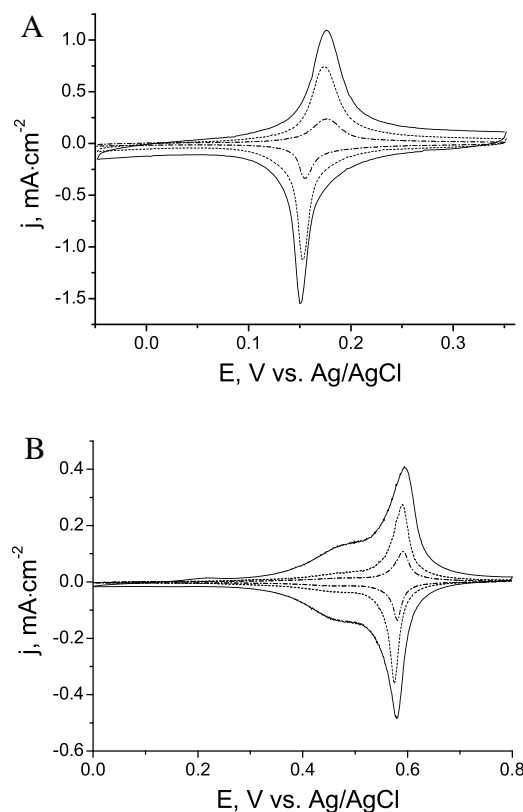

**Fig. 1.** Cyclic voltammograms of (a) Prussian Blue: 0.90 nmol cm<sup>-2</sup> (dash-dot line), 2.45 nmol cm<sup>-2</sup> (short dash line), 4.05 nmol cm<sup>-2</sup> (solid line) and (b) nickel hexacyanoferrate: 0.40 nmol cm<sup>-2</sup> (dash-dot line), 1.15 nmol cm<sup>-2</sup> (short dash line), 4.10 nmol cm<sup>-2</sup> (solid line); in 0.1 M KCl and 0.1 M HCl, sweep rate 40 mV s<sup>-1</sup>.

Download English Version:

<https://daneshyari.com/en/article/6473011>

Download Persian Version:

<https://daneshyari.com/article/6473011>

[Daneshyari.com](https://daneshyari.com)