



The complex shear modulus of dough over a wide frequency range

Valentin Leroy^{a,1}, Karen M. Pitura^b, Martin G. Scanlon^{b,*}, John H. Page^a

^a Department of Physics & Astronomy, University of Manitoba, Winnipeg, Manitoba, Canada R3T 2N2

^b Department of Food Science, University of Manitoba, Winnipeg, Manitoba, Canada R3T 2N2

ARTICLE INFO

Article history:

Received 4 November 2009

Received in revised form 2 February 2010

Accepted 3 February 2010

Keywords:

Bread dough
Dough rheology
Soft solid
Viscoelasticity
Mechanical impedance
Rheometry
Shear waves
Ultrasound
Relaxation models

ABSTRACT

It is shown from small strain shear rheometry and low intensity ultrasonic shear wave measurements that power law behaviour describes the frequency dependence of the complex shear modulus of dough made from a strong North American breadmaking wheat flour. This is the first characterization of the linear viscoelastic behaviour over such a wide frequency range (more than eight decades). Standard rheometry was used to determine shear moduli at low frequencies while an inclined incidence wave reflection technique was used to measure the complex shear modulus in the 10^5 Hz region. The ultrasonic data demonstrate that previous descriptions of the constitutive properties of this rheologically complex material do not incorporate a sufficiently broad range of relaxation times to comprehensively model the rheology of dough at all frequencies. Modeling the dough as a power-law gel material permitted its linear viscoelastic response to be described well over the full frequency range.

© 2010 Elsevier B.V. All rights reserved.

1. Introduction

Wheat flour doughs are interesting, rheologically complex materials [1–3], and to date it has not been possible to agree upon a constitutive model that comprehensively predicts their mechanical behaviour [4]. A comprehensive understanding of the constitutive properties of dough is essential because typical dough processing operations cover such a wide range of rates of stress application [5], extending from the very slow deformation induced by out-gassing of carbon dioxide into bubbles within the dough during proving [6] to the high strain rates imposed during dough mixing [7], during sheeting of the dough [8] and during extrusion operations [9]. Therefore, in investigations of the rheology of dough, it is vital that an extensive range of testing rates is covered [10], otherwise extrapolation from a restricted set of rates to predict mechanical behaviour where rates of stress application are higher or lower may well lead to inaccurate results [11].

An important aspect of the mechanical behaviour of any soft solid is its response to shear solicitations in the linear viscoelastic

regime [12,13]. Although there have been numerous evaluations of the shear modulus of dough, most analyses have been performed over a limited frequency range, typically less than five decades [2,14]. Two studies, one in Europe [15] and one in North America [16], have reported shear modulus values at higher rates of testing using ultrasonic techniques. However, two very different results were obtained, with the reported shear modulus being orders of magnitude higher in the North American study [16] where an all-purpose flour (presumably of North American origin) was used and values similar in magnitude to the longitudinal and bulk moduli of dough were found. It has been remarked that the “strength” of the flour may markedly influence the choice of constitutive model deemed appropriate for characterizing the properties of dough [12]. Since breadmaking flours in North America are typically made from grists of stronger wheat varieties, one would expect the resulting doughs to exhibit greater shear stiffness. However, it seems highly implausible that differences in the source of wheat flour can give rise to a 1000-fold difference in the shear modulus of dough at ultrasonic frequencies.

Therefore, the objective of this paper was to perform both small strain shear rheometry and low intensity ultrasonic shear wave measurements on doughs made from the same strong North American breadmaking wheat flour. In this way, the complex shear modulus of dough in the linear viscoelastic regime could be unambiguously characterized over a very wide frequency range.

* Corresponding author. Tel.: +1 204 474 6480; fax: +1 204 474 7630.

E-mail address: scanlon@cc.umanitoba.ca (M.G. Scanlon).

¹ Present address: Laboratoire Matière et Systèmes Complexes, Université Paris Diderot-Paris 7, CNRS (UMR 7057), 10 rue Alice Domon et Léonie Duquet, 75205 Paris, France.

2. Materials and methods

A mechanical development process [17] was used to prepare all doughs from a strong breadmaking flour by mixing 100 g of Canadian Western Hard White Spring wheat flour (13.8% protein; 14% moisture) with 2.40 g of salt and 60 ml of distilled water. The dough was allowed to rest in a sealed plastic container for at least 20 min prior to specimen preparation for shear testing, either by ultrasound or by rheometry. The density of the dough (ρ) was independently determined to be $1198 \pm 7 \text{ kg m}^{-3}$ from measurements on sub-samples using Archimedes principle [17].

To prepare specimens for rheometry, the whole dough piece was made into a sheet by passing through a dough-sheeting device with successive reductions in gap to obtain a final dough thickness of 3–4 mm. The sheeted dough was allowed to rest for 10 min and a specimen was excised using a circular steel cutter. The specimen was then carefully mounted on the rheometer.

An AR 2000 rheometer was used with 40 mm diameter parallel plates at 20 °C, essentially as described by Phan-Thien and co-workers [2,12,18]. The upper plate was lowered at $50 \mu\text{m s}^{-1}$ to compress the dough to a normal force of 2 N. The exposed dough surface at the specimen perimeter was coated with mineral oil. Doughs were allowed to rest for 45 min in the rheometer prior to testing, a time that sufficed to relax all but the most slowly relaxing normal stresses [2,12]. Frequency sweeps were performed (0.01–100 Hz) at a constant shear stress of 1.0 Pa (determined from preliminary analyses to be well within the linear viscoelastic region).

Due to the very strong attenuation of shear waves in dough, the complex shear modulus at ultrasonic frequencies was obtained using an inclined incidence wave reflection technique [13] that has been used to measure the shear modulus of other highly attenuative materials (e.g., high molecular weight polydimethylsiloxanes). In our experimental set-up (Fig. 1) a shear transducer emitted an ultrasonic pulse centered at 400 kHz that propagated into an acrylic block. The shear wave that was partly reflected at the acrylic–dough interface propagated again through the acrylic, was reflected at the acrylic–air interface and followed the same path back to the transducer, which was detected as a pulse whose complex fast Fourier transform (FFT) $A_{\text{dough}}^*(f)$ was determined. Measuring the reflected pulse when there was no dough at the interface provided a reference FFT, denoted $A_{\text{ref}}^*(f)$. The ratio $x^* = A_{\text{dough}}^*/A_{\text{ref}}^*$ is related to the acoustic impedances Z^* and Z_0^* and to the angles θ_i and θ_r by

$$x^* = \left(\frac{Z_0^* \cos(\theta_i) - Z^* \cos(\theta_r)}{Z_0^* \cos(\theta_i) + Z^* \cos(\theta_r)} \right)^2, \quad (1)$$

where $Z^* = \rho v^*$, ρ , and $v^* = [1/\nu_s + i\alpha/\omega]^{-1}$ are the (shear) impedance, density and complex velocity of the dough, with ν_s and α being its sound speed and attenuation, $Z_0^* \approx Z_0 = \rho_0 v_0$ (1.62 MRay) is the impedance of acrylic (since the losses in acrylic are

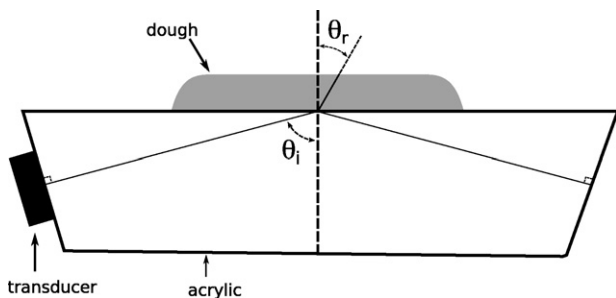


Fig. 1. Experimental set-up for the inclined incidence wave reflection method used to measure shear wave velocity of dough.

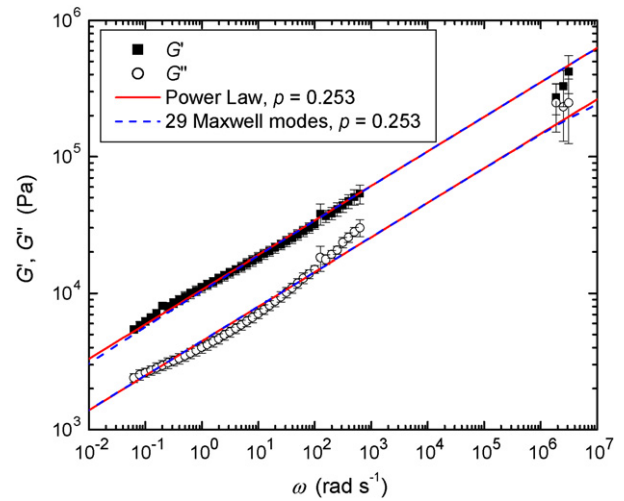


Fig. 2. Real (■) and imaginary (○) parts of complex shear modulus of dough as a function of angular frequency determined by rheometry and ultrasound. Broken blue lines are model descriptions for a discrete Maxwell relaxation spectrum (see text), while solid red lines are power-law relations ($G'(\omega) = 10600\omega^{0.253}$; $G''(\omega) = 4460\omega^{0.253}$ corresponding to $S = 9380 \text{ Pa s}^{0.253}$).

negligible at these frequencies, Z_0 can be taken to be real), θ_i , the angle of incidence, is 75°, and θ_r is the angle of refraction [$\sin(\theta_r) = \nu_s \sin(\theta_i)/\nu_0$].

From Eq. (1) we can extract Z^* :

$$Z^* = Z_0 \frac{\cos(\theta_i)}{\cos(\theta_r)} \left(\frac{1 - \sqrt{x^*}}{1 + \sqrt{x^*}} \right) \quad (2)$$

Although in Eq. (2) θ_r depends on Z^* , if the shear velocity in the dough resting on the acrylic block is small compared with the shear velocity in acrylic, $\cos(\theta_r) \approx 1$. The complex quantity Z^* obtained with Eq. (2) allows the real and imaginary parts of the shear modulus to be determined:

$$G' = \Re\left(\frac{Z^{*2}}{\rho}\right) \quad \text{and} \quad G'' = \Im\left(\frac{Z^{*2}}{\rho}\right) \quad (3)$$

To prepare specimens for ultrasonic testing, sub-samples of the dough piece were excised with a very sharp pathology blade just prior to measurement (so that the fresh surface ensured good contact between the dough and acrylic block). An important issue in accuracy of these measurements is temperature stability [13]. Sub-samples were equilibrated for 5 min on the block because we observed initial signal variation, probably because of temperature changes, that essentially disappeared over this time. In addition, if the temperature changed between acquisition of the reference and the dough signals, the phase shift induced by a change in shear wave velocity in the acrylic block brought about by the temperature change would interfere with determination of the small phase shift arising from reflection at the dough–acrylic interface. To reduce the effect, we measured the signal with the piece of dough on the acrylic first (i.e., A_{dough}^*), then we removed the dough and measured the reference signal (A_{ref}^*). Results at three frequencies were reported, chosen from the working bandwidth of the transducer: 300, 400 and 500 kHz. Up to 10 different sub-samples were investigated from different mixed doughs.

3. Results and discussion

The real and imaginary parts of the complex shear modulus of doughs made from a strong North American spring wheat flour over eight decades of frequency are shown in Fig. 2. It can be seen that it is possible to extrapolate rheometry data to the ultrasonic

Download English Version:

<https://daneshyari.com/en/article/671039>

Download Persian Version:

<https://daneshyari.com/article/671039>

[Daneshyari.com](https://daneshyari.com)