



Polymorphism of lead oxoborate

A.G. Tyulyupa^a, V.V. Voronov^b, P.P. Fedorov^{b,*}

^a Middle School, Sablinskoe, Stavropol region, 356322, Russia

^b A.M. Prokhorov General Physics Institute RAS, 38 Vavilov Street, Moscow 119991, Russia



ARTICLE INFO

Article history:

Received 16 October 2014

Received in revised form 8 May 2015

Accepted 12 May 2015

Available online 14 May 2015

Keywords:

Lead borate

Undercooling

Allotropy

Polymorphism

Nonlinear crystal

Metastable phase transition

Differential thermal analysis

ABSTRACT

The study of lead borate melt crystallization by differential thermal analysis (DTA) and X-ray diffraction analysis has shown that, for $\text{Pb}_4\text{O}(\text{BO}_3)_2$ (or $4\text{PbO}\cdot\text{B}_2\text{O}_3$) stoichiometric compound, its well-known orthorhombic modification (non-centrosymmetric *Aba2* space symmetry group (SSG), $a = 15.472(1)$, $b = 10.802(1)$, $c = 9.9486(6)$ Å unit cell parameters) is metastable. It forms from the undercooled melt and has a melting point of 530 ± 5 °C.

© 2015 Published by Elsevier B.V.

1. Introduction

Lattices of the single crystals of various composition borates are formed in non-centrosymmetric space symmetry groups. This phenomenon is linked to the complexity of anionic fragments in crystalline borates. As a result, they possess certain unique physical features, including non-linear optical (NLO) properties. Such non-linear crystals are capable of efficient transformation of laser irradiation and, therefore, can be used in high-power monochromatic sources of ultra-violet (UV) irradiation. In addition to their unique optical properties (wide spectrum region of optical transparency that reaches 150–200 nm boundary in the UV part of the spectrum [1,2]), borates, generally, have excellent mechanical properties and high optical damage thresholds that give them serious advantages over other oxygen-containing optical crystals such as phosphates, niobates, titanates, molybdates, iodates, nitrites, etc.

The class of borate optical materials includes a couple of widely used compounds: β - BaB_2O_4 (BBO) [3–5], LiB_3O_5 (LBO) [6], as well as some other materials such as: CsB_3O_5 (CBO) [7], LiCsB_2O_8 (CLBO) [8,9], $\text{KB}_2\text{B}_3\text{O}_7$ (KBBF), $\text{RbB}_2\text{B}_3\text{O}_7$ (RBBF) and $\text{CsB}_2\text{B}_3\text{O}_7$ (CBBF) [10,11], $\text{Sr}_2\text{Be}_2\text{B}_2\text{O}_7$ (SBBO) [12], $\text{K}_2\text{Al}_2\text{B}_2\text{O}_7$ (KABO) [13], $\text{BaAl}_2\text{B}_2\text{O}_7$ (BABO) [14], BiB_3O_6 (BiBO) [15,16], $\text{Ba}_4\text{B}_{11}\text{O}_{20}\text{F}$ (BBOF) [17], $\text{Li}_2\text{B}_4\text{O}_7$ (LB4) [1], $\text{GdCa}_4\text{O}(\text{BO}_3)_3$ (GdCOB) [18], $\text{YCa}_4\text{O}(\text{BO}_3)_3$

(YCOB) [19], $\text{BaAlBO}_3\text{F}_2$ (BABF) [20], $\text{La}_2\text{CaB}_{10}\text{O}_{19}$ (LCB) [21], $\text{Y}_{0.57}\text{La}_{0.72}\text{Sc}_{2.71}(\text{BO}_3)_4$ (YLSB) [22,23], etc. Along with quantum chemistry calculations and crystallography investigations [1,2,24], studying phase equilibria in the above oxide and fluoride systems are crucial for development of the single crystal growth technology and obtaining borate single crystals of the required size and high optical quality as it has been unequivocally demonstrated for LBO [25], BBO [26–30], and KBBF [1,10].

Recently, when a novel $\text{Pb}_4\text{O}(\text{BO}_3)_2$ NLO borate was discovered, it was found as expected that its space symmetry group (SSG) *Aba2* lacks a center of inversion [31,32]. $\text{Pb}_4\text{O}(\text{BO}_3)_2$ crystalline samples were prepared by quickly controlled quenching of the melt to 470 °C (the starting material was preliminarily prepared by melting a mixture of PBO and H_3BO_3 , gradually heating to 600 °C, and seasoning at this temperature for 20 h). In fact, the aforementioned $\text{Pb}_4\text{O}(\text{BO}_3)_2$ compound was described much earlier by Geller and Bunting [33] as $4\text{PbO}\cdot\text{B}_2\text{O}_3$ in the course of their study of the $\text{PbO}\text{--}\text{B}_2\text{O}_3$ system phase diagram. This compound undergoes a phase transformation at 552 °C and melts congruently at 565 °C. Existence of $4\text{PbO}\cdot\text{B}_2\text{O}_3$ was also independently confirmed in [34] while studying phase equilibria in the $\text{PbO}\text{--}\text{B}_2\text{O}_3\text{--}\text{WO}_3$ ternary system. In addition, McMurdie [35] published an unindexed X-ray diffraction pattern of $\text{Pb}_4\text{O}(\text{BO}_3)_2$, but his data do not agree with the similar results in [31,32]. The reason why scientists did not pay enough attention to $\text{Pb}_4\text{O}(\text{BO}_3)_2$ stems from the fact that the growth of $\text{Pb}_4\text{O}(\text{BO}_3)_2$ single crystals has been seriously hindered by the polymorphous phase transition of this compound despite the congruent character of the melting.

* Corresponding author. Tel.: +7 499 503 8292.

E-mail addresses: ppfedorov@yandex.ru, ppf@lst.gpi.ru (P.P. Fedorov).

Therefore, the purpose of our study was to further investigate the phase formation during crystallization of the $\text{Pb}_4\text{O}(\text{BO}_3)_2$ composition melt, $\text{Pb}_4\text{O}(\text{BO}_3)_2$ polymorphous phase transformation, and determine the conditions for the synthesis of $\text{Pb}_4\text{O}(\text{BO}_3)_2$ polymorph with non-linear optical properties.

2. Experimental

We used commercially available 99.5 wt.% pure lead oxide PbO (TU 6-09-5382-88 standard) and 99.9 wt.% pure boron oxide B_2O_3 (TU 6-09-3558-78 standard) from the Red Chemist manufacturer (St. Petersburg, Russia) as our starting materials. Prior to DTA experiments, PbO and B_2O_3 specimens were heated at 300–400 °C for 2 h to remove traces of moisture. Samples were weighed with MASSA-K electronic balance (0.005 g accuracy for 1 g samples).

X-Ray diffraction phase analysis (Bruker D8 Discover diffractometer, $\text{CuK}\alpha$ radiation, Ni filter) data for the polycrystalline $\text{Pb}_4\text{O}(\text{BO}_3)_2$ powder samples were treated with the use of TOPAS software package.

We investigated $\text{Pb}_4\text{O}(\text{BO}_3)_2$ phase transitions under heating and cooling conditions with the use of a differential thermal analysis (DTA) technique and our own proprietary DTA installation under air. Studied specimens (0.6–0.8 g) were placed in platinum crucible (1 ml). Alumina powder (1 g) was used as a standard reference material. Nichrome coiled wire served as a heating element. Grog alumina clay (shamotte) was utilized for thermal insulation, and zirconia ceramic pieces served as cover lids for the heating chamber sides. The cold junctions of the thermocouples were kept in ice–water at 0 °C. Temperature in the oven heating zone was regulated by the TRM-151 regulator (programmed controller manufactured by OVEN, Moscow, Russia). Signals from chromel–alumel (type K) thermocouples were registered by ZET-220 unit (ETMS, Moscow/Zelenograd, Russia) and treated with the use of ZetLab computer software. In order to enhance our DTA installation sensitivity to undercooling processes, we registered signal from the thermocouple attached to the crucible with the studied sample (instead of the reference sample) during thermal analysis experiments (i.e., temperature difference (DTA) vs. temperature (TA) curves, respectively). Thermocouples were calibrated in respect to NaCl (99.99 wt.% pure) melting point, and Na_2SO_4 (99.5 wt.% pure) melting point and polymorphic

transition temperature. We evaluate the accuracy of temperature determination in our experiments as ± 5 °C.

DTA curves were recorded for heating and cooling experiments at 5 °C/min for both types of experiments.

PbO was placed in a platinum crucible, then it was melted, and small portions of B_2O_3 were added later until $\text{Pb}_4\text{O}(\text{BO}_3)_2$ ($4\text{PbO}\cdot\text{B}_2\text{O}_3$) stoichiometry was achieved. Finally, the sample temperature was raised up to 950 °C to make the specimen homogeneous. Mass losses during such procedure did not exceed 1%.

3. Results and discussion

Both heating and cooling DTA curves (Fig. 1, curves 1 and 2, respectively) for $\text{Pb}_4\text{O}(\text{BO}_3)_2$ samples were complex and contain two thermal effects. Temperatures of such effect maxima in the cooling curve differed from ones in the heating curve by 12–14 °C or less (Fig. 1); but, nevertheless, the starting points of effects (552 °C for $\beta \rightarrow \alpha$ phase transition and 565 °C for $\alpha \rightarrow$ liquid transformation) were in a good agreement with the corresponding data [33] for the B_2O_3 –PbO system.

However, crystallization of $\text{Pb}_4\text{O}(\text{BO}_3)_2$ usually occurred from an undercooled melt (Fig. 1, curves 3). The temperature increase after the beginning of crystallization unequivocally indicated an exothermal character of the latter process as well as metastability of the undercooled liquid phase. Temperatures of crystallization from such undercooled melts at the same 5 °C/min cooling rate varied over a fairly broad interval (up to 100 °C). This confirmed the random crystallization nucleation mechanism in the melt [36,37]. Such random undercooling is quite typical in the case of poor wetting ability of the melt with the crucible [38].

Multiple heating experiments with $\text{Pb}_4\text{O}(\text{BO}_3)_2$ ($4\text{PbO}\cdot\text{B}_2\text{O}_3$) samples have shown that melting occurred at different temperatures. Corresponding DTA curves of such experiments could be arranged into two groups (Fig. 2): those that could be characterized as stable (S) or metastable (M) systems. The difference between $\text{Pb}_4\text{O}(\text{BO}_3)_2$ melting points in the S- and M-type curves was about 30 °C. S-Type DTA curves corresponded to the β - $\text{Pb}_4\text{O}(\text{BO}_3)_2 \rightarrow \alpha$ - $\text{Pb}_4\text{O}(\text{BO}_3)_2$ phase transformation and melting of α - $\text{Pb}_4\text{O}(\text{BO}_3)_2$ phase [33]. M-Type curves, apparently, corresponded to the $\text{Pb}_4\text{O}(\text{BO}_3)_2$

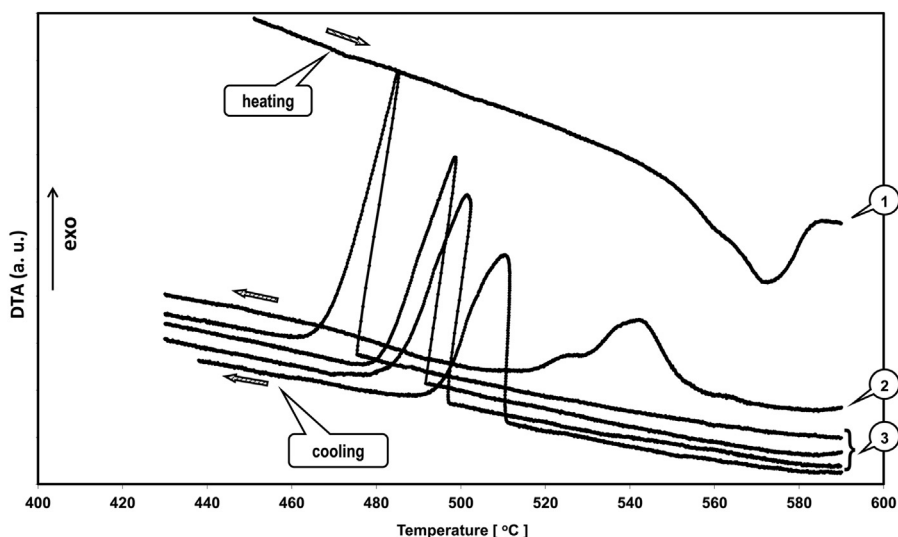


Fig. 1. Typical $\text{Pb}_4\text{O}(\text{BO}_3)_2$ DTA curves (5 °C/min): heating (1), cooling with crystallization without undercooling (2), and cooling with undercooling crystallization (3).

Download English Version:

<https://daneshyari.com/en/article/673061>

Download Persian Version:

<https://daneshyari.com/article/673061>

[Daneshyari.com](https://daneshyari.com)