



Thermal behavior of 3,4,5-triamino-1,2,4-triazole nitrate

Xue Liang^{a,b}, Zhao Feng-Qi^{b,*}, Xing Xiao-Ling^b, Zhou Zhi-Ming^c,
Wang Kai^c, Gao Hong-Xu^b, Yi Jian-Hua^b, Hu Rong-Zu^b

^a School of Chemistry and Materials Science, Shaanxi Normal University, Xi'an City 710062, China

^b National Key Lab of Science and Technology on Combustion and Explosion, Xi'an Modern Chemistry Research Institute, Xi'an City 710065, China

^c School of Chemical Engineering and Environment, Beijing Institute of Technology, Beijing 100081, China

ARTICLE INFO

Article history:

Received 12 June 2010

Received in revised form 9 August 2010

Accepted 12 August 2010

Available online 19 August 2010

Keywords:

3,4,5-Triamino-1,2,4-triazole nitrate

Thermal behavior

Specific heat capacity

Self-accelerating decomposition temperature

Adiabatic time-to-explosion

Critical temperature of Hot-Spot initiation

ABSTRACT

The thermal decomposition behaviors of 3,4,5-triamino-1,2,4-triazole nitrate were studied using a C-500 type Calvet Micro-calorimeter at four different heating rates. Its apparent activation energy and pre-exponential factor of exothermic decomposition reaction are $137.16 \text{ kJ mol}^{-1}$ and $10^{10.03} \text{ s}^{-1}$. The critical temperature of thermal explosion is 441.37 K . The entropy of activation ($\Delta S^\ddagger$), enthalpy of activation ($\Delta H^\ddagger$), and free energy of activation ($\Delta G^\ddagger$) of the decomposition reaction are $-65.65 \text{ J mol}^{-1} \text{ K}^{-1}$, $132.97 \text{ kJ mol}^{-1}$ and $166.35 \text{ kJ mol}^{-1}$, respectively. The self-accelerating decomposition temperature (T_{SADT}) is 429.56 K . The specific heat capacity was determined with a Micro-DSC method and a theoretical calculation method. Specific heat capacity ($\text{J g}^{-1} \text{ K}^{-1}$) equation is $C_p = 0.356 + 2.957 \times 10^{-3} T$ ($283.1 \text{ K} < T < 353.2 \text{ K}$). The adiabatic time-to-explosion is calculated to be a certain value between 702.22 s and 712.22 s . The critical temperature of Hot-Spot initiation is 600.325°C , and the characteristic drop height of impact sensitivity (H_{50}) is 27 cm .

© 2010 Elsevier B.V. All rights reserved.

1. Introduction

The most accepted definition of an ionic liquid is a salt with melting point below 373.15 K [1–3]. Ionic liquids attract increasing attention among academic and industrial chemists for their unique properties. The chemical and thermodynamic stabilities of these compounds, combined with their low vapor pressures and low melting points, have put them forth as potential replacements of many noxious organic solvents used in the chemical industry.

Recently, many studies in developing energetic salts and energetic ionic liquids based on 1,2,3-triazole and 1,2,4-triazole as cations and nitrates, perchlorates, and dinitramides as anions have been made [4–6]. On the thermal aspect, kinetic and thermodynamic of 3,4,5-triamino-1,2,4-triazole nitrate is a basic task in the content of thermal process. The thermal behavior of materials may be determined in a short time using thermal analysis techniques such as DSC, TG-DTG, but more intensive and precise thermal analysis can be carried out by using Micro-calorimeter.

In this work, a C-500 Calvet Micro-calorimeter was applied for researching the thermal decomposition behavior of 3,4,5-triamino-1,2,4-triazole nitrate at four different heating rates, and the data were analyzed to obtain the self acceleration decomposition tem-

perature (T_{SADT}) and critical temperature of thermal explosion (T_b), adiabatic time-to-explosion and critical temperature of Hot-Spot initiation were obtained at the same time.

2. Experimental

2.1. Materials


3,4,5-Triamino-1,2,4-triazole nitrate in this research was prepared by Beijing Institute of Technology and Xi'an Modern Chemistry Research Institute. The structure was characterized by means of organic elemental analyzer, ^{15}N NMR, ^{13}C NMR and HPLC-MS. The sample's purity was $>99.5 \text{ mass\%}$. The structure for 3,4,5-triamino-1,2,4-triazole nitrate are shown in Scheme 1. The 3,4,5-triamino-1,2,4-triazole nitrate was further purified by subjecting the sample to a very low pressure of about $5 \times 10^{-3} \text{ Pa}$ at temperature about 70°C for approximately 5 h. This procedure removed any volatile chemicals and water from the triazole ionic salts.

2.2. Equipment and conditions

The heat flow curves of the exothermic decomposition process of 3,4,5-triamino-1,2,4-triazole nitrate was measured using a Calvet Micro-calorimeter, type C-500 (Setaram, France), which had a sensitivity of $0.10 \mu\text{V mW}^{-1}$ and was equipped with two 10 mL ves-

* Corresponding author. Tel.: +86 29 88291663.

E-mail address: npecc@163.com (F.-Q. Zhao).

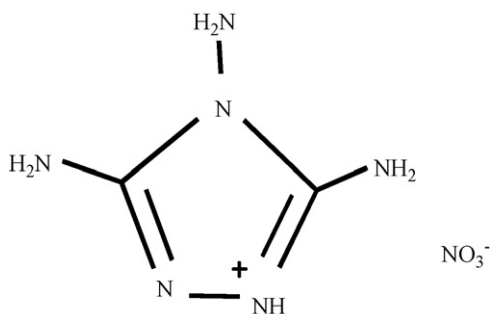

Scheme 1. The structure of 3,4,5-triamino-1,2,4-triazole nitrate.

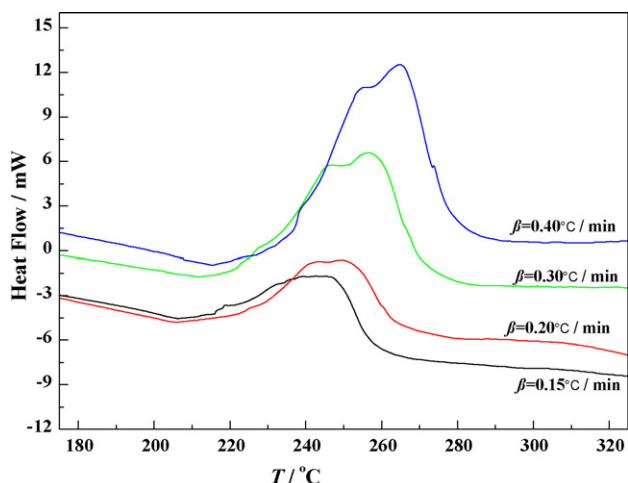


Fig. 1. Heat flow curves of 3,4,5-triamino-1,2,4-triazole nitrate at different heating rates.

sels. The precision of enthalpy measurement was less than 0.5% after adjusting. The four different heating rates used were 9 K h^{-1} (0.15 K min^{-1}), 12 K h^{-1} (0.20 K min^{-1}), 18 K h^{-1} (0.30 K min^{-1}) and 24 K h^{-1} (0.40 K min^{-1}), respectively. Sample used was about 10 mg, and the reference sample was $\alpha\text{-Al}_2\text{O}_3$. Each process was repeated three times, and the heat flow curves under same conditions overlap with each other, indicating that the reproducibility of test is satisfactory.

The measurement of specific heat capacity (C_p) was performed using a Micro-DSC III apparatus (Setaram, France). The amount of used sample was 479.29 mg. The heating rate was 9 K h^{-1} from temperatures 283.1 K to 353.2 K.

3. Results and discussion

3.1. Thermal decomposition behavior

The heat flow curves of 3,4,5-triamino-1,2,4-triazole nitrate at different heating rates are shown in Fig. 1, which show only one exothermic peak. The characteristic temperatures obtained by heat flow curves at different heating rates are listed in Table 1. In Table 1,

Table 1

Original data of the thermal decomposition reaction of 3,4,5-triamino-1,2,4-triazole nitrate at different heating rates.

β (K min^{-1})	T_e (K)	T_p (K)	$Q = -\Delta H$ (kJ mol^{-1})
0.15	482.23	518.36	365.40
0.20	487.67	522.06	367.80
0.30	490.99	527.74	369.34
0.40	496.01	533.91	361.56

Table 2

Kinetic parameters obtained from the data in Table 1.

Kissinger method			Ozawa method		T_{p0} (K)
E_k (kJ mol^{-1})	$\lg(A_k)$ (s^{-1})	r_k	E_{op} (kJ mol^{-1})	r_{op}	
137.16	10.03	0.9938	138.75	0.9945	508.41

β is the heating rate, T_p the peak temperature, T_e the onset temperature, and ΔH the enthalpy of decomposition reaction.

In order to obtain the apparent activation energy (E) and the pre-exponential constant (A) of the decomposition reaction for 3,4,5-triamino-1,2,4-triazole nitrate, multiple heating methods (Kissinger method [7] and Ozawa method [8]) were employed. Kissinger and Ozawa equations are as follows [9–14]

$$\ln \left(\frac{\beta_i}{T_{pi}^2} \right) = \ln \frac{AR}{E} - \frac{E}{R T_{pi}} \quad [i = 1, 2, \dots, 4] \quad (1)$$

$$\lg \beta_i = \lg \left(\frac{AE}{RG(\alpha)} \right) - 2.315 - 0.4567 \frac{E}{RT_i} \quad [i = 1, 2, \dots, 4] \quad (2)$$

where β_i is the linear heating rate, T_{pi} represents the peak temperature of the decomposition process, R is the gas constant.

From the original data in Table 1, the values of E and A obtained by Kissinger method (with a subscript of k) and Ozawa method (with a subscript of o) are listed in Table 2.

With the data listed in Table 2, entropy of activation ($\Delta S^\ddagger$), enthalpy of activation ($\Delta H^\ddagger$), and free energy of activation ($\Delta G^\ddagger$) of the decomposition reaction corresponding to $T = T_p$, $E = E_k$ and $A = A_k$ obtained by Eqs. (3)–(5) are $-65.65 \text{ J mol}^{-1} \text{ K}^{-1}$, $132.97 \text{ kJ mol}^{-1}$ and $166.35 \text{ kJ mol}^{-1}$, respectively.

$$A_k = \left(\frac{k_B T_{p0}}{h} \right) e^{\Delta S^\ddagger / R} \quad (3)$$

$$\Delta H^\ddagger = E_k - RT_{p0} \quad (4)$$

$$\Delta G^\ddagger = \Delta H^\ddagger - T_{p0} \Delta S^\ddagger \quad (5)$$

where k_B the Boltzmann constant ($1.3807 \times 10^{-23} \text{ J K}^{-1}$), and h the Plank constant ($6.626 \times 10^{-34} \text{ J s}^{-1}$).

The positive value of $\Delta G^\ddagger$, indicates that the exothermic decomposition reaction for 3,4,5-triamino-1,2,4-triazole nitrate must proceed under the heating condition.

3.2. Self-accelerating decomposition temperature (T_{SADT}) and critical temperature of thermal explosion (T_b)

The value T_{e0} (T_{SADT}) of T_e corresponding to $\beta = 0$ can be obtained by substituting the T_e and β from Table 1 into Eq. (6) [13–18]. The value of T_{e0} (T_{SADT}) is obtained is 429.56 K.

$$T_{(e,p)i} = T_{(e,p)0} + b\beta_i + c\beta_i^2 + d\beta_i^3 \quad [i = 1, 2, \dots, 4] \quad (6)$$

where b , c and d are coefficients.

The critical temperature of thermal explosion T_b obtained from Eq. (7) taken from Refs. [13–18] is 441.37 K, where $E_o = E_{op}$.

$$T_b = \frac{E_o - \sqrt{E_o^2 - 4E_o RT_{SADT}}}{2R} \quad (7)$$

3.3. Specific heat capacity (C_p)

Fig. 2 shows the determination results of 3,4,5-triamino-1,2,4-triazole nitrate using a continuous specific heat capacity mode of a Micro-DSC III apparatus. In determining temperature range, specific heat capacity of 3,4,5-triamino-1,2,4-triazole nitrate presents

Download English Version:

<https://daneshyari.com/en/article/674725>

Download Persian Version:

<https://daneshyari.com/article/674725>

[Daneshyari.com](https://daneshyari.com)