

HOSTED BY



Contents lists available at ScienceDirect

Engineering Science and Technology, an International Journal

journal homepage: www.elsevier.com/locate/jestech

Full Length Article

Modeling and prediction of cutting forces during the turning of red brass (C23000) using ANN and regression analysis

M. Hanief*, M.F. Wani, M.S. Charoo

Mechanical Engineering Department, National Institute of Technology, Srinagar, Jammu & Kashmir 190006, India

ARTICLE INFO

Article history:

Received 23 August 2016

Revised 21 October 2016

Accepted 31 October 2016

Available online xxx

Keywords:

ANN

Brass

Cutting forces

Regression

Turning

ABSTRACT

The life of a cutting tool is greatly influenced by the forces acting on it during a cutting operation. A machining operation is a complex process. It is very difficult to develop a comprehensive model involving all the parameters. The present study aims to develop a model to investigate the effects of cutting parameters (speed, depth of cut and feed rate) on the cutting forces during the turning operation of red brass (C23000) using high speed steel (HSS) tool. The experimental results are based on full factorial design methodology to increase the reliability and confidence limit of the data. Artificial neural network and multiple regression approaches were used to model the cutting forces on the basis of cutting parameters. In order to check the adequacy of the regression model, analysis of variance (ANOVA) was used. It was clear from the ANOVA that the regression model is capable to predict the cutting forces with high accuracy. However, ANN model was found to be more accurate than the regression model.

© 2016 Karabuk University. Publishing services by Elsevier B.V. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

1. Introduction

The cutting forces are a result of extreme conditions at the tool-workpiece interface. The interaction can be directly related to the tool wear and in worst cases to the failure of the tool. Consequently, the tool wear and cutting forces are related to each other [1,2]. Thus, it is necessary to carry out the optimization of cutting process to evaluate the optimal values of cutting parameters to determine the performance and useful life of the cutting tool. Surinder et al. [3] investigated the cutting forces (tangential and feed force) in turning of unidirectional glass fiber reinforced plastics (UD-GFRP). The process parameters of cutting tool (nose radius, rake angle, cutting speed, feed rate, depth of cut and cutting environment) were investigated using Taguchi robust design methodology. The relative significance of parameters was studied using ANOVA. The tangential force was found to decrease with decrease in tool nose radius, feed rate and depth of cut and increase with the cutting speed. Cascona et al. [4] developed mechanistic model for prediction of cutting forces in turning of non-axis-symmetric parts. This study presents a mechanistic model for predicting the orthogonal turning forces (in 3 directions), torque and power consumption along the machining path of non-axis-symmetric parts.

Dorlin et al. [5] studied the geometrical modeling of tool-workpiece interaction and its effects on the cutting forces during turning. The analysis focused on convex contact radius between the machined part and the tool. The experiments were based on cylindrical and face turning of Ti6Al4V titanium alloy. It was observed that the contact radius had significant effect on the cutting forces and the cutting forces increase with the increase in the radius. Xie et al. [6] studied cutting force and cutting temperature during the turning of titanium alloy using micro-grooved tool under dry conditions. The objective of the study was to estimate the influence of shape and size of micro groove on the temperature and force in dry turning. The micro-grooved tool decreases cutting temperature by 103 °C, while as the shear angle increases with decreasing micro-groove depth. Philip et al. [7] studied the effects of cutting speed and feed rate on tool wear, surface roughness and cutting force on nitrogen alloyed duplex stainless steel in a dry turning process, using Taguchi method. The results revealed that the feed had the most significant influence on the cutting forces. The cutting speed was found to be the most significant parameter affecting the tool wear. Shear force, ploughing force and particle fracture force were considered by Sikder et al. [8] to estimate the cutting force during the machining of metal matrix composites (MMCs). The chip formation force, ploughing force and fracture force were obtained by Johnson-Cook model, slip line field theory and Griffith's theory respectively. The results showed good agreement between the predicted and experimental values of the cutting forces. Two body abrasion and three body rolling due to

* Corresponding author.

E-mail addresses: hanief@nitsri.net (M. Hanief), mfwani@nitsri.net (M.F. Wani), shaficharoo123@nitsri.net (M.S. Charoo).

Peer review under responsibility of Karabuk University.

Nomenclature

f_x	thrust force (N)	Df	degrees of freedom
f_y	cutting force (N)	SS	sum of squares
f_z	feed force (N)	MSE	mean square error
f_R	resultant force (N)	MAPE	mean absolute % error
v	cutting speed (m/min)	ϕ	transfer function
f	feed rate (mm/rev)	t_i	target values
d	depth of cut (mm)	o_i	observed values
k, c_1, c_2, c_3	Model parameters	R^2	coefficient of determination

reinforcements in composites was studied by Uday et al. [9] during the machining of Al/SiCp composite. Theory of oblique cutting was used for predicting the cutting forces during the machining of this composite. With the assumption that 40% of the finer reinforcement particles contribute to abrasion at tool-chip interface, the model was found to be accurate. Similarly for 60% of coarser reinforcement contributing to the abrasion, the model yielded good results. Pramanik et al. [10] proposed a model for predicting the cutting forces during the cutting of aluminum-based SiC/Al₂O₃ particle reinforced MMCs. Three factors, chip formation force, ploughing force and particle fracture force were considered to be the force generation mechanisms. Merchant's analysis was used to obtain the chip formation force, while as, slip line field theory of plasticity and the Griffith theory of fracture were used to formulate the matrix ploughing deformation and particle fracture. It was concluded that the force due to chip formation is much higher than those due to ploughing and particle fracture. Joardar et al. [11] studied the influence of cutting speed, depth of cut and weight percentage of SiCp on the cutting forces during the turning of aluminum MMC (aluminum alloy reinforced with silicon carbide particles) under dry conditions, using response surface methodology. Cutting speed was found to be the most significant factor influencing the cutting forces. Shoba et al. [12] investigated the influence of machining parameters (cutting speed, feed rate and depth of cut) on the cutting forces during the turning of hybrid composites. Different percentages of SiC (0, 2, 4, 6 and 8%) by weight and rice husk ash were used in reinforced composite specimens. The comparison of reinforced and unreinforced specimens revealed that cutting forces decrease with the increase in weight percentage of the reinforcement. This trend was attributed to the dislocation densities produced from the mismatch between the reinforcement and the matrix. Fountas et al. [13] investigated the influence of cutting speed and feed-rate on the cutting forces during the turning of PA66 GF-30 Glass Fiber Reinforced Polyamide using carbide cutting tool. It was concluded that the soft computing techniques can be effectively used to predict the cutting force components. Vaxevedis et al. [14] also concluded from their research that ANN can be effectively used to predict the cutting forces and surface roughness while investigating the turning of AISI D6 tool steel, Ti6Al4V ELI and CuZn39Pb3 brass under dry cutting environment with spindle speed, feed rate and depth of cut as input; and surface roughness and cutting forces as outputs. Fountas et al. [15] conducted a series of 5 axis machining experiments in CAM environment to simulate operations using an L₂₇ orthogonal array. Four machining parameters namely tool type, stepover, lead angle and tilt angle as inputs and surface deviation and machining time were selected as the outputs. Similar investigation was conducted by Vaxevedis et al. [16] while turning the Ti-6Al-4V alloy with input as spindle speed, the feed rate and the depth of cut; and outputs as cutting force and the centre line average surface roughness. The methodology was found to be robust enough to predict optimal values for quality objectives.

Although several materials such as steels, aluminum alloys, composites etc. have been investigated during the turning to develop the model for cutting forces. But very few models and investigations are devoted to brasses. The intention of the present work is to develop a cutting force predictive model and to investigate the influence of cutting parameters on the cutting forces during the turning of red brass (C23000) using regression analysis and ANN (see Fig. 1).

2. Experimentation

In this study, red brass (C23000) cylindrical bars of diameter 30 cm as work piece material and **HSS** tool were used. The experiments were performed under dry conditions on a (5HP and 45–2000 rpm range) **Kiloshkar** make lathe. The tool post was fitted with a dynamometer for measuring three components of the cutting force, namely feed force (f_z), radial thrust force (f_x) and tangential (main) cutting force (f_y). The forces were recorded in a digital computer which was interfaced with the dynamometer. A full factorial design methodology was adopted and in total 27 (3³) experiments were performed. Feed rate, cutting speed and DOC were chosen for the study. The experimental details of machining process are given in Table 1. The resultant force was calculated by $f_R = \sqrt{f_x^2 + f_y^2 + f_z^2}$.

3. Results and discussion

3.1. Regression model

The model of predicted cutting force, F_R can be expressed as Eq. (1).

$$F_R = k v^{c_1} f^{c_2} d^{c_3} \quad (1)$$

where k , c_1 , c_2 and c_3 are model parameters

By logarithmic transformation Eq. (1) can be written as

$$\ln F_R = \ln k + c_1 \ln v + c_2 \ln f + c_3 \ln d \quad (2)$$

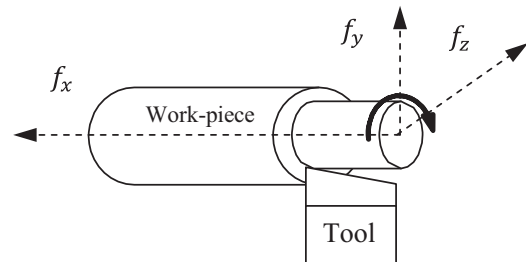


Fig. 1. Direction of forces in turning operation.

Download English Version:

<https://daneshyari.com/en/article/6893905>

Download Persian Version:

<https://daneshyari.com/article/6893905>

[Daneshyari.com](https://daneshyari.com)