

Microwave-assisted Synthesis Silver Nanoparticles and Their Surface Enhancement Raman Scattering



Liu Faxian^{1,2}, Liu Jie¹, Cao Xueling³

¹ Key Laboratory of Carbon Fiber and Functional Polymers, Ministry of Education, Beijing University of Chemical Technology, Beijing 100029, China; ² Jilin Petrochemical Company, Jilin 132002, China; ³ Jilin Institute of Chemical Technology, Jilin 132022, China

Abstract: A one-step microwave-assisted method was used for the synthesis of silver nanoparticles, and the corresponding nature and structure of silver nanoparticles were characterized by UV-Vis absorption spectroscopy, transmission electron microscopy (TEM), and atomic force microscopy (AFM). Raman scattering activities of silver nanoparticles with different reaction time were explored using rhodamine 6G (R6G) as a probe molecule. The results show that the intensity of surface enhancement Raman scattering (SERS) signals could be increased by silver nanoparticles. And then we made a comparison on SERS spectra of R6G studied silver nanoparticles to investigate the effect of surface enhancement Raman. Meanwhile, we studied the mechanism in the process of enhancement by silver nanoparticles.

Key words: microwave-assisted method; silver nanoparticles; surface enhancement Raman scattering

Since the surface enhancement Raman scattering (SERS) effect was discovered for the first time by M. Fleischmann^[1] in 1974, SERS has attracted considerable attention on both theoretical and experimental investigations^[2-9]. Recently, single-molecule detection^[10-13] should be the most progress, showing enhancement factors up to $10^{14}\sim 10^{15}$ on a single silver nanoparticle. Due to the excellent optical properties, silver nanoparticles have been widely used for SERS.

Different approaches to the synthesis of silver nanoparticles have been reported such as chemical reduction, UV photolysis and gamma irradiation^[14]. Among them, the chemical reduction was still the most common method. In addition, microwave-assisted heating has been coupled with the chemical reduction as a convenient and energy efficient preparation method of silver nanoparticles. The main advantage of microwave-assisting over conventional heating is rapid and uniform since no high temperatures or high pressures are needed^[15,16]. Therefore, both nucleation and growth could be controlled easily to produce nano-products with the desired shape or size. Microwave-assisted methods have been widely used for the synthesis of metallic

nanoparticles such as gold, silver, palladium and platinum^[10,17]. Here we reported a one-step microwave-assisted synthesis of silver nanoparticles. Furthermore, we provided a direct application of the silver nanoparticles to the surface enhancement Raman scattering. Meanwhile, silver nanoparticles were produced at three different reaction time, and then we made a comparison on SERS spectra of R6G molecules adsorbed on the three kinds of silver nanoparticles to investigate the effect of surface enhancement Raman.

1 Experiment

The silver nitrate was purchased from Sigma and used without further purification. The trisodium citrate was purchased from Beijing Chemical Company. All other reagents were of analytical reagent grade and used as received. The water used was purified through a Millipore system.

The silver nanoparticles were synthesized by BILON-CW-1000 ultrasonic microwave synthesizer (Shanghai Bilon Instrument Manufacturing CO.). The AgNO₃ aqueous (10 mL, 10 mmol/L) was added to trisodium citrate aqueous (10 mL, 10 mmol/L) at 37 °C. Two minutes later, the mixture was

Received date: September 14, 2016

Foundation item: The National Natural Science Foundation of China (51073011)

Corresponding author: Liu Jie, Ph. D., Professor, College of Materials Science and Engineering, Beijing University of Chemical Technology, Beijing 100029, P. R. China, Tel: 0086-10-64438724, E-mail: liujj_432@163.com

Copyright © 2017, Northwest Institute for Nonferrous Metal Research. Published by Elsevier BV. All rights reserved.

incubated with the microwave irradiation with indirect response mode for the different time ($t=8, 15, 20$ min). The solution was centrifuged with 10000 r/min and then thoroughly rinsed twice in deionized water to obtain silver nanoparticles. The deposit was collected and then subjected to freeze-drying to obtain silver nanoparticles in powder.

The UV-Vis spectra were recorded on a Shimadzu UV-3600 spectrophotometer for solutions with concentration of 10 mg/mL silver nanoparticles contained in 1 cm \times 1 cm quartz cuvettes (4 mL volume).

A certain amount of silver nanoparticles was gained with a special copper mesh, then placed and dried under an infrared lamp for 1.5 h. The copper mesh with the sample was placed into the sample tank, the working voltage of JEM-2000EX transmission electron microscopy was adjusted to 200 kV, and then transmission electron microscopy images was obtained.

Raman spectra were recorded on Raman spectrometer (Renishaw Invia, UK) equipped with inverse microscope (ZEISS Axiovert 25). The spectral response range of Raman spectra was 500~1700 cm^{-1} . The spectra were excited by 632.8 nm line of 35 mW He-Ne laser at 10 s exposure.

2 Results and Discussion

2.1 UV-Vis spectra of silver nanoparticles

For the microwave-assisted synthesis of silver nanoparticles, trisodium citrate was reacted with silver nitrate aqueous under extremely basic conditions (pH 8) at 37 $^{\circ}\text{C}$ by MWI instead of direct heating to maintain the temperature. The growth of silver nanoparticles as a function of reaction condition was followed by UV-Vis spectra. When the initial powers of MWI are varied from 100 to 700 W and the reaction time is 10 min, the maximum absorption wavelength red-shift gradually with reaction power, ascribed to the slow growth of silver nanoparticles (Fig.1). After 10 min of MWI at 500 W, the UV-Vis spectra change slightly when the molar ratio of silver nitrate and trisodium citrate varies in the range of 3:1~1:3 (Fig.2). However, for the molar ratio of 1:3, the maximum absorption wavelength decreases more quickly.

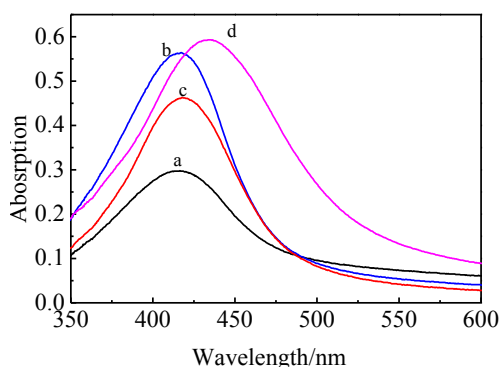


Fig.1 UV-Vis absorption spectra of silver nanoparticles prepared with different MWI powers (a- 100 W, b- 300 W, c- 500 W, d- 700 W)

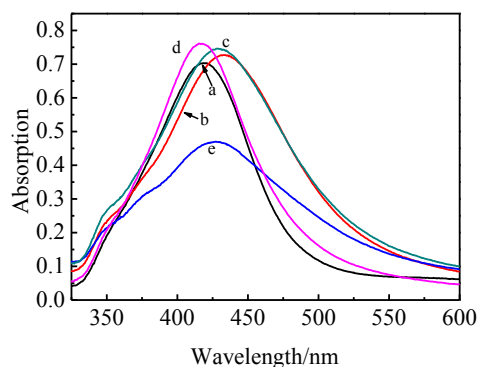


Fig.2 UV-Vis absorption spectra of silver nanoparticles prepared with different molar ratios of AgNO_3 and trisodium citrate (a- 3:1, b- 2:1, c- 1:1, d- 1:2, and e- 1:3)

Fig.3 provides the UV-Vis spectra of three original silver nanoparticles obtained by the reduction method, namely for the power setting of 500 W silver nitrate and trisodium citrate (the molar ratio was 1:1) were mixed and heated for different time ($t=8, 15, 20$ min). These spectra indicate that metallic silver nanoparticles have different sizes after different reaction time. At reaction time of 8, 15, 20 min, the plasmon resonance peaks appear at 408, 423, 461 nm, respectively (Fig.3). It is shown that the size of silver nanoparticles increases gradually with the increasing of the reaction time. So we could adjust the reaction conditions to prepare different sizes of silver nanoparticles.

2.2 TEM images of silver nanoparticles

TEM images of silver nanoparticles are shown in Fig.4. It is obvious that silver nanoparticles are uniformly spherical in shape and well-dispersed. The mean size of these nanoparticles is approximately 60 nm, which is in agreement with that of the UV-Vis spectrum. And with the increase in reaction time, the size of the silver nanoparticles was larger, but when the reaction time is 20 min, some certain aggregation occurs in silver nanoparticles.

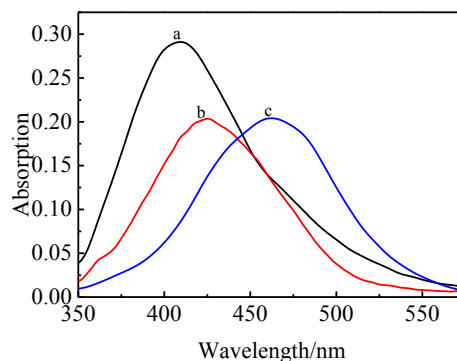


Fig.3 UV-Vis absorption spectra of silver nanoparticles prepared with different heating time (a- 8 min, b- 15 min, and c- 20 min)

Download English Version:

<https://daneshyari.com/en/article/7210267>

Download Persian Version:

<https://daneshyari.com/article/7210267>

[Daneshyari.com](https://daneshyari.com)