



# A new compact micro-ball lens structure at the cleaved tip of microfiber coupler for displacement sensing

A.A. Jasim<sup>a</sup>, A.Z. Zulkifli<sup>a</sup>, M.Z. Muhammad<sup>a</sup>, S.W. Harun<sup>a,b,\*</sup>, H. Ahmad<sup>b</sup>

<sup>a</sup> Department of Electrical Engineering, Faculty of Engineering, University of Malaya, 50603 Kuala Lumpur, Malaysia

<sup>b</sup> Photonics Research Center, Department of Physics, University of Malaya, 50603 Kuala Lumpur, Malaysia

## ARTICLE INFO

### Article history:

Received 28 May 2012

Received in revised form 4 September 2012

Accepted 4 September 2012

Available online 25 September 2012

### Keywords:

Tapered fiber

Micro-ball lens

Displacement sensor

## ABSTRACT

A compact micro-ball lens structure is fabricated at the cleaved tip of microfiber coupler (MFC) waist for displacement sensor application. The MFC is made by fusing and tapering two optical fibers using a flame brushing technique. It is then cleaved at the center of the minimum waist region. Then a micro-ball lens is formed at the tip of the microfiber by an arcing technique using a fusion splicing machine. The proposed displacement sensor uses the micro-ball lens as a probe and a reflector as a target. As the target is moved from the micro-ball lens, an interference fringe is obtained due to the interference between two reflected beams from the micro-ball lens and the reflector. At the smallest displacement of 0.6 mm, the output spectrum shows the interference fringes with highest extinction ratio and largest free spectral range (FSR). Both extinction ratio and FSR reduces following the power trend line with correlation coefficient of 0.99 as the displacement increases. The *Q* resonant factor of the comb spectrum increases from 1628 to 38,286 as the displacement increases from 0.6 to 3.6 mm.

© 2012 Elsevier B.V. All rights reserved.

## 1. Introduction

Microfibers with cross-sectional dimensions of the order of a few micrometers have received significant attention for applications in various areas such as lasing [1], sensing [2], filtering over wide spectral regions [3], and for nonlinear studies [4,5]. Furthermore, they can be manufactured via relatively simple top-down fabrication processes (such as flame [2] or laser-assisted tapering [6] and also micro-heater tapering [7]), wherein a standard heat-and-draw principle is employed. Recently, Fabry–Perot interferometers (FPIs) have extensively been explored in various sensing applications due to their high measurement sensitivities [8]. This interferometer is based on multiple-beam interference within two reflecting surfaces whereby the reflected light in the FPI is wavelength-modulated in exact accordance with the cavity length. Therefore it is suitable for various sensitive applications such as measuring velocity, displacement, strain, temperature and stiffness measurements [8–10].

Positioning technology is an important high precision technology useful for developing microsystems. In particular, displacement sensors are necessary for positioning devices with nano-scale

accuracy. Much attention has also been focused on micro-ball lens in recent years for achieving low-cost coupling [11]. In earlier works [9,10], non-contact vibration measurement has been demonstrated using an external Fabry–Perot interferometer. In this paper, we propose a new displacement sensor using the same cavity formation but with a microfiber ball lens instead of a GRIN lens as a sensing probe. The probe is made at the minimum waist region of microfiber coupler (MFC), which is cleaved to form a micro-ball lens using an arcing technique. This sensor has a wide measuring range, high resolution, and excellent accessibility for narrow target areas. The proposed sensor uses both microfiber and microfiber ball lens, which is more compact compared to the conventional single mode fiber and multimode fiber.

## 2. Fabrication of the microfiber coupler and micro-ball lens

An MFC structure is made by laterally fusing and tapering two optical fibers using an experimental setup as shown in Fig. 1. In this experiment, a standard telecom optical fiber (Corning SMF-28) was used to make a low noise microfiber coupler with the aid of the well-known flame-brushing technique [2]. In the fabrication process, two fibers were brought into close proximity after their protective plastic jacket was removed. Then, both fibers were twisted at two different locations and heated by a torch to fuse and stretch them. The torch uses a mixer of butane and oxygen

\* Corresponding author at: Department of Electrical Engineering, Faculty of Engineering, University of Malaya, 50603 Kuala Lumpur, Malaysia.

E-mail address: [swharun@um.edu.my](mailto:swharun@um.edu.my) (S.W. Harun).

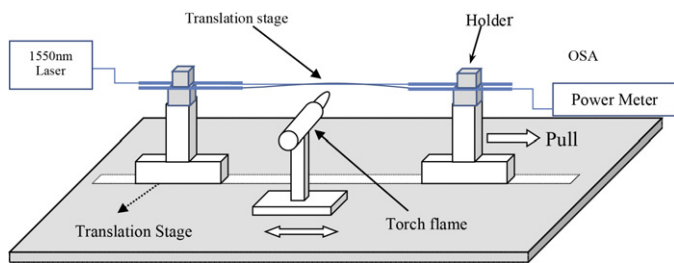


Fig. 1. Microfiber coupler fabrication setup.

gases to generate a flame with a temperature of around  $1400^{\circ}\text{C}$ . The longitudinal profile of the conical transition taper was achieved by reliably controlling the heat infused into the hot zone and precisely moving the translation stages. During the tapering process, the coupling ratio was monitored in real time by using a 1550 nm light source and power meters. The heating and pulling processes were stopped the moment a 50/50 coupling ratio was achieved. The diameter of the MFC waist was about  $5\text{ }\mu\text{m}$  and the lengths of tapered region and uniform waist were 70 mm and 40 mm, respectively.

The fabricated MFC was then used to form a micro-ball lens by an arcing technique using a fusion splicing machine. First, the MFC was cut at the center of the minimum waist region to form a micro-ball lens at the tip. The fabrication process involved two processes and they were loading and arcing processes. In the loading process, we opened the windshield of the splicer, the fiber holders and the fiber clamps and loaded the prepared MFC tip into the left side of the holder with the tapered region in the V-groove. It is important to make sure that the MFC is properly aligned in the V-groove before closing the fiber holder. The fiber clamp was closed afterwards to hold the fiber on the V-groove. Once the fiber was loaded correctly, the windshield was closed and finally the formation of the micro-ball lens started with the arching process. After setting the arc power, the cleaning arc power offset and the cleaning time, the fabrication of the micro-ball lens commenced. The MFC tip absorbed the arc discharging heat and melted instantaneously. Due to the surface tension, the melting part of the MFC started to form a spherical shaped tip gradually during solidification. As the spherical tip grew bigger, the effect of gravity increased and pulled the tip towards the ground. This causes the spherical tip to descend and increased the offset distance between the centre of the sphere and the axis of the fiber stylus. To avoid this misalignment, the MFC was rotated slowly while the tip solidified. Fig. 2(a) and (b) shows the microscope image of the micro-ball lens on the tip end of the

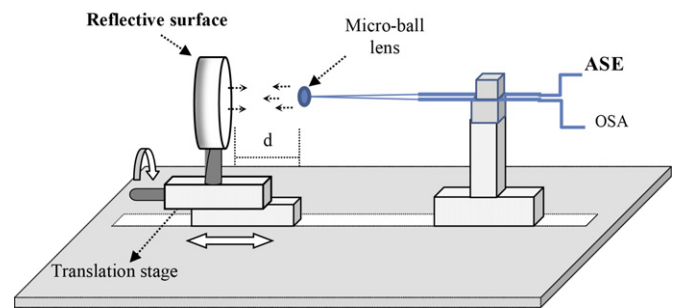


Fig. 3. The schematic diagram of the proposed displacement sensor.

MFC with and without the injection of red light, respectively. As shown in Fig. 2(b), the bright red color represents the scattering from the reflected red light.

Fig. 3 shows the experimental setup for the proposed micro-ball lens based displacement sensor with a reflective surface as a target. The reflector reflectivity at 1550 nm is estimated to be around 60%. The micro-ball lens coupler is fixed horizontally on a translation stage in front of a reflector at a distance ( $d$ ). One of the coupler ports is connected to an amplified spontaneous emission (ASE) light source while the other port is connected to an optical spectrum analyzer (OSA) as shown in the figure. The reflector is held by another translation stage so that the displacement between the reflector and micro-ball lens can be varied.

### 3. Results and discussion

The schematic diagram of the probe and reflector is shown in Fig. 4, in which directions of the propagating light reflected inside the probe and outside the probe by the reflector are indicated. When the ASE light is injected into the micro-ball lens through the input port of the MFC, part of it is reflected by the micro-ball lens surface while some portion passes through the micro-ball lens and is reflected by the reflector. We denote  $I_1$  as the part of light beam that is directly reflected by the inner surface of the micro-ball lens and  $I_2$  as the portion that passes through the micro-ball lens and travels across the gap with a distance  $d$  before being reflected by the reflector. The reflected beams interfere in the micro-ball lens and in the medium as they travel to the output port of the coupler. The interference fringe is recorded at OSA as shown in Fig. 5. As the reflector is moved away from the sphere, the fringe weakens.

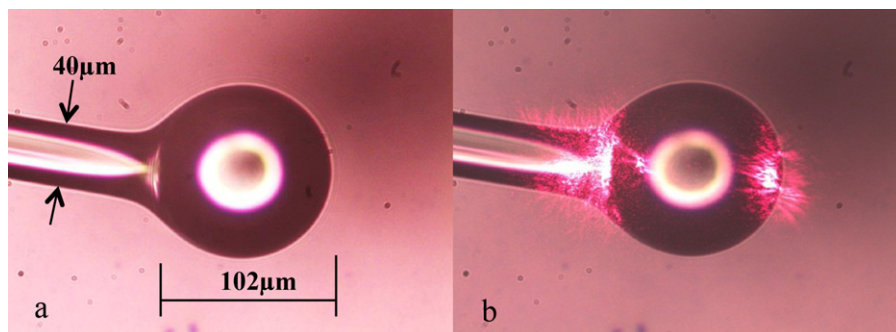


Fig. 2. Microscope images for the micro-ball lens fabricated at the cleaved tip of MFC (a) without injecting any light (b) with injection of red laser. (For interpretation of the references to color in the text, the reader is referred to the web version of the article.)

Download English Version:

<https://daneshyari.com/en/article/737328>

Download Persian Version:

<https://daneshyari.com/article/737328>

[Daneshyari.com](https://daneshyari.com)