



## Short communication

High performance of  $\text{La}_{0.6}\text{Sr}_{0.4}\text{Co}_{0.2}\text{Fe}_{0.8}\text{O}_3\text{--Ce}_{0.9}\text{Gd}_{0.1}\text{O}_{1.95}$  nanoparticulate cathode for intermediate temperature microtubular solid oxide fuel cells


Hirofumi Sumi\*, Toshiaki Yamaguchi, Koichi Hamamoto, Toshio Suzuki, Yoshinobu Fujishiro

Advanced Manufacturing Research Institute, National Institute of Advanced Industrial Science and Technology, Nagoya 463-8560, Japan

## HIGHLIGHTS

- Grain size of LSCF–GDC nanoparticulate cathode was less than 100 nm.
- Total cathode polarization resistance was only  $0.13\ \Omega\ \text{cm}^2$  at  $600\ ^\circ\text{C}$ .
- LSCF nanoparticulate cathode contributed to decrease the polarization resistance.

## GRAPHICAL ABSTRACT

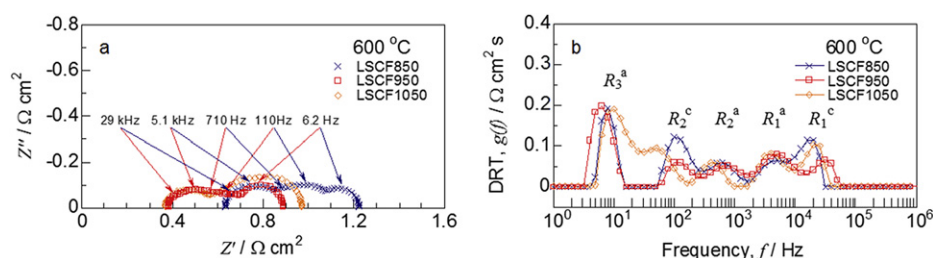

## ARTICLE INFO

## Article history:

Received 20 August 2012

Received in revised form

5 November 2012

Accepted 8 November 2012

Available online 16 November 2012

## Keywords:

Solid oxide fuel cell (SOFC)

Perovskite

Cathode

AC impedance

Distribution of relaxation times (DRT)

## ABSTRACT

The perovskite  $\text{La}_{0.6}\text{Sr}_{0.4}\text{Co}_{0.2}\text{Fe}_{0.8}\text{O}_3\text{--Ce}_{0.9}\text{Gd}_{0.1}\text{O}_{1.95}$  (LSCF–GDC) nanoparticulate cathode was applied for microtubular solid oxide fuel cells operated at intermediate temperatures. For the cell with the cathode sintered at  $950\ ^\circ\text{C}$ , maximum power densities of  $0.26$ ,  $0.54$  and  $0.73\ \text{W cm}^{-2}$  were obtained at  $550$ ,  $600$  and  $650\ ^\circ\text{C}$ , respectively. The ohmic resistance increased for the cathode sintered at  $850\ ^\circ\text{C}$ , and the polarization resistance increased for the cathode sintered at  $1050\ ^\circ\text{C}$ . The cathode polarization resistances of ionic conduction process in the LSCF bulk and adsorption/desorption process on the LSCF surface were estimated by the distribution of relaxation times analysis, which were only  $0.066$  and  $0.065\ \Omega\ \text{cm}^2$  at  $600\ ^\circ\text{C}$  for the cathode sintered at  $950\ ^\circ\text{C}$ . The grain size of the cathode was less than  $100\ \text{nm}$ , which resulted in high performance due to an overall decrease in cathode polarization resistance.

© 2012 Elsevier B.V. All rights reserved.

## 1. Introduction

Solid oxide fuel cells (SOFCs) are expected to emerge as power generation systems with high energy conversion efficiencies. Recently, many researchers have focused on lowering the operating temperature of SOFCs from  $800\text{--}1000\ ^\circ\text{C}$  to  $500\text{--}700\ ^\circ\text{C}$  in order to improve their durability, start-up time and so on. Previously, the authors have developed anode-supported microtubular SOFCs with high power densities via the “Advanced Ceramic Reactor Project” of

the New Energy and Industrial Technology Development Organization (NEDO) in Japan. We have successfully formed dense electrolyte thin-films of thickness *ca.*  $5\ \mu\text{m}$  by dip-coating on the anode substrate, which contributes to a decrease in the ohmic resistance [1]. The anode polarization resistance is decreased by controlling the nanostructure of the anode substrate using acrylic resin as a pore former [2]. The power density per cathode area reached  $1\ \text{W cm}^{-2}$  at a low temperature of  $550\ ^\circ\text{C}$  for the microtubular SOFCs with a diameter of  $0.8\ \text{mm}$  [3]. Furthermore, a power of  $2\ \text{W}$  can be obtained at  $490\ ^\circ\text{C}$  for a  $3 \times 3$ -cell module with a volume of  $1\ \text{cm}^3$  [4].

High catalytic and electrochemical activities are also required to promote oxide ion transfer and oxygen exchange processes as well

\* Corresponding author. Tel.: +81 52 736 7592; fax: +81 52 736 7405.

E-mail address: [h-sumi@aist.go.jp](mailto:h-sumi@aist.go.jp) (H. Sumi).

as high electronic conductivities at low temperatures for cathode materials. Perovskite  $\text{La}_{0.6}\text{Sr}_{0.4}\text{Co}_{0.2}\text{Fe}_{0.8}\text{O}_3$  (LSCF) is one of the most promising cathodes for intermediate temperature (IT)-SOFCs. The LSCF cathode is a mixed ionic–electronic conductor with an electrical conductivity of more than  $10^2 \text{ S cm}^{-1}$  at 500–700 °C, and is a good match with zirconia based electrolytes in terms of its thermal expansion coefficient [5,6]. Dusastre and Kilner [7] and Murray et al. [8] reported that the cathode polarization resistance decreased significantly by adding 30–50 vol.% Gd-doped ceria (GDC) to LSCF. Furthermore, the adding of a noble metal catalyst such as Pd [9], Pt [10], Ag [11] and so on into LSCF promoted the cathode reaction at temperatures below 600 °C. However, the noble catalysts are too expensive to be applied to IT-SOFCs. Recently, Shah and Barnett [12], Darbandi and Hahn [13] and Leng et al. [14] developed nanoparticulate cathodes with high catalytic and electrochemical activities for IT-SOFCs. They only evaluated half-cells in air to investigate cathode polarization resistance using an AC impedance method.

Previously, the authors were successful in evaluating the effect of anode porosity on the polarization resistance by the distribution of relaxation times (DRT) analysis [15]. This method can directly detect the number of electrode processes using mathematical techniques without assuming the equivalent circuits for actual SOFCs in hydrogen/air [16,17]. In this study, the polarization resistances of the LSCF–GDC nanoparticulate cathodes with different sintering temperatures were evaluated by the DRT analysis for anode-supported microtubular SOFCs.

## 2. Experimental

Anode microtubes were made from NiO (Sumitomo metal mining), 8 mol%  $\text{Y}_2\text{O}_3$  stabilized  $\text{ZrO}_2$  (8YSZ; Tosoh), pore former (acrylic resin; Sekisui Plastic) and binder (Cellulose; Yuken Kogyo) powders. The weight ratio of NiO to 8YSZ was 60:40, and the particle size of the pore former was ca. 5  $\mu\text{m}$ . These powders were mixed with a kneading machine by adding an appropriate amount of water over a period of 2 h. The hardness of the mixture clay was ca. 12 measured by a type A durometer (ISO 7619). The anode microtubes were extruded using a piston cylinder with a metal hold with an outside diameter of 2.4 mm and an inside diameter of 2.0 mm. After extrusion, the tubes were dried overnight in air at room temperature. A slurry was prepared by mixing 8YSZ, binder (polyvinyl butyral; Sekisui Chemical) dispersant (tallow propylene diamine, Kao) and plasticizer (dioctyl adipate; Wako Pure Chemical Industries) into ethanol and toluene solvents for 48 h. The 8YSZ electrolyte was formed by dip-coating at a pulling rate of 1  $\text{mm s}^{-1}$ . The 8YSZ thin-film electrolyte and NiO-8YSZ anode microtube were co-sintered for 1 h in air at 1350 °C. The interlayer of  $\text{Ce}_{0.9}\text{Gd}_{0.1}\text{O}_{1.95}$  (GDC; Shin-etsu Chemical) was formed on the electrolyte by a similar manner, and sintered for 1 h in air at 1200 °C. The cathode was a LSCF–GDC (70:30 wt.%) composite. The LSCF nanoparticulate powder was prepared using co-precipitation and low temperature calcination by Dowa Electronics Materials. The LSCF–GDC cathode was formed by dip-coating at a pulling rate of 2  $\text{mm s}^{-1}$ , and sintered for 1 h in air at 850, 950 or 1050 °C (denoted LSCF850–GDC, LSCF950–GDC and LSCF1050–GDC, respectively). The outside diameter of the microtubes was 1.8 mm and the area of the cathode was 0.6  $\text{cm}^2$  after sintering. The thicknesses of the anode, the electrolyte, the interlayer and the cathode were ca. 200, 5, 1 and 20  $\mu\text{m}$ , respectively. The cathode microstructure was observed using a FE-SEM (JEOL; JSM-6330F) with an accelerating voltage of 15 kV.

The characteristics of the power generation and the AC impedance were evaluated with a potentiostat/galvanostat (Solartron Analytical 1287) and an impedance analyzer (Solartron Analytical 1255B). A mixture of 40%  $\text{H}_2$ –3%  $\text{H}_2\text{O}$ –57%  $\text{N}_2$  was supplied as fuel at

a flow rate of 50  $\text{mL min}^{-1}$  to the anode side, and air was supplied as oxidant at 50  $\text{mL min}^{-1}$  to the cathode side. Operating temperatures were 500, 550, 600 and 650 °C. Silver wires were used as current collectors. Current–potential ( $i$ – $V$ ) characteristics were measured from open circuit voltage (OCV) to 0.4 V at a sweep rate of 5  $\text{mV s}^{-1}$ . AC impedance spectra were measured under OCV in the frequency range from 1 MHz to 0.1 Hz with 20 steps per logarithmic decade.

Generally, polarization resistances are analyzed by an equivalent circuit with a parallel resistance–conductance (RC) element. An ideal RC element has a single relaxation time  $\tau$  defined by the appropriate  $R$  and  $C$  values ( $\tau = RC$ ). However, the actual polarization resistance for SOFCs cannot be perfectly fitted by one RC element because relaxation times are generally distributed for the actual electrode processes. Therefore, the polarization resistances are generally fitted by an equivalent circuit with RQ element (constant phase elements in parallel with a resistor) for the complex non-linear least squares (CNLS) method [18]. The DRT method can directly detect the number of electrode processes by mathematical techniques without assuming the equivalent circuits of the polarization components [16,17]. In this study, polarization impedance  $Z_{\text{pol}}(\omega)$  are considered to be an equivalent circuit composed of an infinite number of RC elements in the following series.

$$Z_{\text{pol}}(\omega) = R_{\text{pol}} \int_0^{\infty} \frac{\gamma(\tau)}{1 + j\omega\tau} d\tau \quad \text{with} \quad \int_0^{\infty} \gamma(\tau) d\tau = 1 \quad (1)$$

here,  $R_{\text{pol}}$  is the total DC polarization resistance,  $\gamma(\tau)$  is the DRT,  $\omega$  is the angular frequency and  $j$  is the imaginary unit. The distribution function  $g(f)$  (with  $f = \omega/2\pi$ ) was calculated using the software program FTIKREG [19] to solve an ill-posed inverse problem by Tikhonov regularization. However, it was impossible to obtain good results for DRT analysis for impedance spectra with an inductance at high frequency [15]. The inductance components were removed by the same method as described in Ref. [15] before DRT analysis for the impedance spectra in this study.

## 3. Results and discussion

Fig. 1 shows the scanning electron images of the (a) LSCF850–GDC, (b) LSCF950–GDC and (c) LSCF1050–GDC cathodes after sintering. The LSCF nanoparticulate powder can be obtained by co-precipitation and low temperature calcination. The grain size of the LSCF850–GDC was only 30–50 nm as shown in Fig. 1(a). The LSCF grains grew up when the sintering temperatures were increased. The size of LSCF1050 was approximately 100 nm. Furthermore, grains more than 300 nm in diameter were observed after sintering at 1050 °C. They are likely to be GDC, because the GDC grains were further grown to a diameter of ca. 1  $\mu\text{m}$  in the interlayer sintered at 1200 °C as shown in the lower image of Fig. 1. The grain size is expected to affect the length of double phase boundaries and electronic conduction paths. On the other hand, the electrolyte and the interlayer were in good contact for all of the cathodes. However, the interface between interlayer and the cathode was unclear because the both of the layers were porous. It was expected that the cathode sintered at the higher temperature was in better contact between the interlayer and the cathode.

Fig. 2 shows the  $i$ – $V$  characteristics for the anode-supported microtubular SOFCs with the LSCF850–GDC, LSCF950–GDC and LSCF1050–GDC cathodes at 500–650 °C. Regarding the influence of the sintering temperature, the electrode sintered at 950 °C gave the best performance. At an operating temperature of 600 °C, the maximum power densities were 0.41, 0.54 and 0.49  $\text{W cm}^{-2}$ , and the area specific resistances (ASRs) derived from the slopes of the  $i$ – $V$  curves near OCV were 1.2, 0.88 and 0.94  $\Omega \text{ cm}^2$  for the

Download English Version:

<https://daneshyari.com/en/article/7741112>

Download Persian Version:

<https://daneshyari.com/article/7741112>

[Daneshyari.com](https://daneshyari.com)