



Method of sacrificial anode dual transistor-driving in stray current field



M. Narozny*, K. Zakowski, K. Darowicki

Department of Electrochemistry, Corrosion and Materials Engineering, Chemical Faculty, Gdansk University of Technology, 11/12 G. Narutowicza St., 80-233 Gdansk, Poland

ARTICLE INFO

Article history:

Received 27 February 2015
Received in revised form 1 June 2015
Accepted 2 June 2015
Available online 20 June 2015

Keywords:

Carbon steel
Polarisation
Weight loss
Cathodic protection

ABSTRACT

In order to control a magnesium anode in a stray current interference field, a dual transistor driving system has been proposed. It consisted of a combination of PNP and NPN transistors. Dual transistor driven system and direct anode to cathode connection were electrochemically tested in 3% NaCl solution. The dual transistor driven system increased the anode efficiency and reduced hydrogen evolution and the risk of embrittlement. Anode susceptibility to the cathodic and anodic stray current interference was reduced.

© 2015 Elsevier Ltd. All rights reserved.

1. Introduction

Sacrificial anode cathodic protection system (CP) is the simplest possible electrochemical corrosion protection system [1,2]. It is often referred to as a self-regulating system. It is only partially true. Cathodic protection current is proportional to the potential difference between the anode and the protected structure and is inversely proportional to the ohmic resistance between the two [3]. In most cases, such a limited control of current is acceptable. However, in certain situations an anode driving system is needed, for instance in zones of stray current interference [4–6]. Sometimes a diode has been used in order to raise the potential of a high strength steels [7–9]. High strength steels are susceptible to hydrogen embrittlement and cracking [10–12]. Thus their potential has to be kept within a desired range.

In high specific resistance grounds [13,14], magnesium anodes are often used due their high electronegative potential [16]. Ground resistivity can vary greatly, for instance due to groundwater level changes or floods. If ground resistivity becomes too low, an enhanced anode consumption might occur. If there is any additional cathodic polarisation of the protected structure caused by stray currents [17,18], overprotection, hydrogen evolution and cathodic

disbondment of coatings might occur [19–21]. Thus a driving system would be beneficial. A proper one would remove the drawbacks while providing complete cathodic protection.

In this paper a magnesium anode protection current regulation system is proposed. It utilises two bipolar germanium transistors – NPN and PNP ones. The proposed driving system is usable both in earth and seawater. This work is a continuation of previous research involving single transistor driving system for magnesium anodes [22].

2. Materials and methods

In order to maintain benefits of a single PNP driving transistor system and improve its performance under cathodic stray current interference, a dual transistor driving system has been proposed. It consists of two transistors – an NPN and PNP ones. Both of the transistors should have as low base-emitter voltage as possible. Thus germanium transistors are preferred. The system configuration is presented in Fig. 1. Both of the transistors share the same base and emitter. Emitters are connected to the protected structure and bases to the auxiliary zinc driving electrode. Their collectors are connected to the anode and anti-anode. Collector of the PNP transistor is connected to the magnesium anode and collector of the NPN transistor is connected to the copper anti-anode. Anti-anode can be made of any material which has a higher electropositive potential than the cathodically overprotected structure. Its potential has to be high enough in order to let the NPN transistor conduct. For instance it could be made of steel, cast iron etc.

* Corresponding author. Tel.: +48 600 483 673.

E-mail addresses: michal.narozny@pg.gda.pl (M. Narozny), krzysztof.zakowski@pg.gda.pl (K. Zakowski), kazimierz.darowicki@pg.gda.pl (K. Darowicki).

Without any external interference only the PNP transistor conducts current (negative potential at the base and positive at the emitter) and the NPN transistor is blocked. If stray current interference causes potential of the protected structure to drop below the potential of the auxiliary electrode, the PNP transistor is blocked and the NPN transistor starts to conduct current (positive potential at the base and negative at the emitter). The NPN transistor is connected to the copper auxiliary electrode which promotes negative charge transfer from the overprotected construction to the positive copper electrode. Thus, the rate of depolarization is enhanced.

Experiments were performed in 3% NaCl water solution which simulated a seawater environment. Cubic magnesium $1 \times 1 \times 1$ inch anodes were used. Electric connector of the anodes was made of steel. It was sealed with silicon to prevent any galvanic coupling. In electrochemical testing, an AD162 PNP transistor and GT4D NPN transistor were used. The driving system was tested in an arrangement proposed by the NACE Standard TM0190: "Impressed Current Laboratory Testing of Aluminium Alloy Anodes". The magnesium anode and copper anti-anode were placed along the axis of the cylindrical steel mesh. The steel mesh cathode was made of S235JR steel and its surface area equalled 750 cm^2 . 0.51Ω shunt resistors were used to measure NPN and PNP collector currents. Auxiliary saturated $\text{Zn}|\text{ZnSO}_4$ electrode was used to monitor the construction potential. Furthermore, a reference sample was prepared. It consisted of a magnesium anode directly connected to the steel mesh cathode. Magnesium anodes were weighed before and after the experiments. Expositions lasted a week.

Stray current interference and the driving system response were investigated. The system was perturbed with an external power source. The voltage was applied between the construction and the axially mounted auxiliary steel electrode. The behaviour under either cathodic or anodic stray current interference was tested. Both NPN and PNP transistors' collector currents and cathode potential vs $\text{Zn}|\text{ZnSO}_4(\text{sat.})$ were simultaneously measured. Stray current signal was randomly generated using a laboratory class dc power supply.

3. Results and discussion

Typical experimental results are presented in Figs. 2 and 3 for a non-driven and transistor driven cells, respectively. A cathode in the non-driven set up was excessively polarised. Its potential was negative to the saturated $\text{Zn}|\text{ZnSO}_4(\text{sat.})$ electrode. The consumption rate of the cathode equalled 6.3 kg/year for 1 A protection current intensity. Hydrogen evolution was observed and calcareous cathodic protection sediments were formed on the surface of

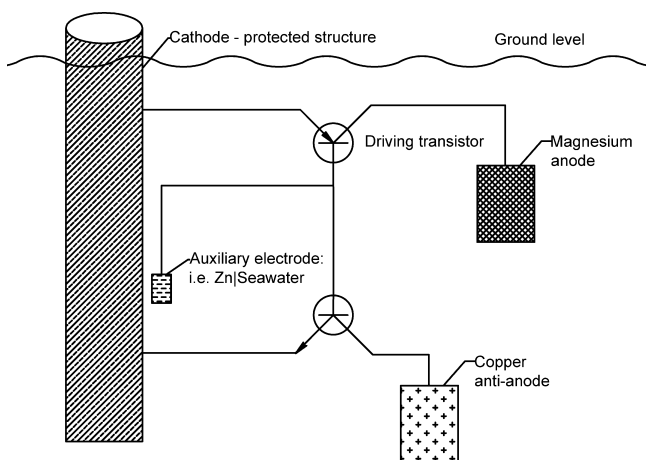


Fig. 1. Scheme of circuit connection.

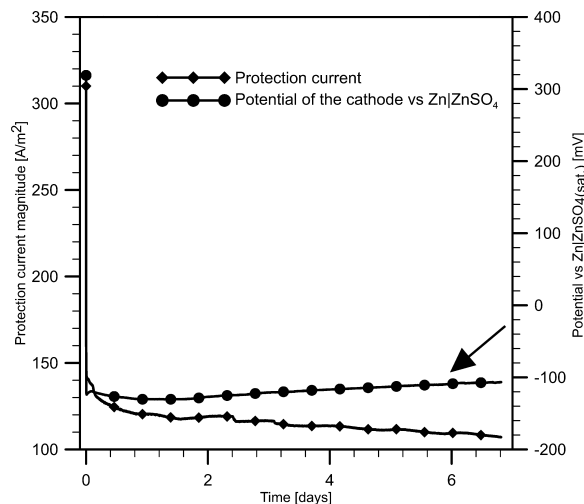


Fig. 2. Cathode potential vs $\text{Zn}|\text{ZnSO}_4(\text{sat.})$ reference electrode and protection current density curves for a non-driven driven circuit.

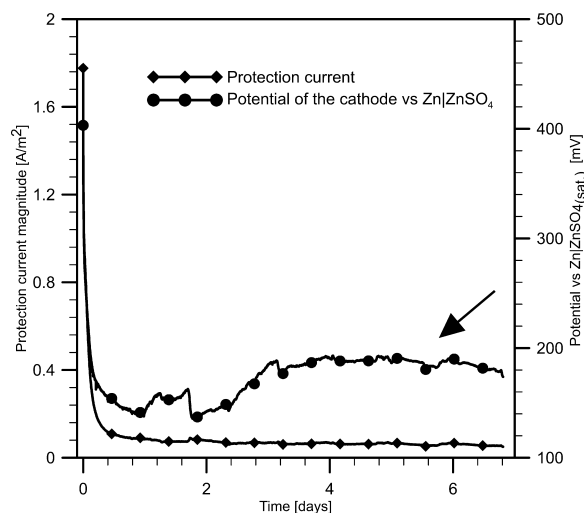


Fig. 3. Time function plots of cathode potential vs $\text{Zn}|\text{ZnSO}_4(\text{sat.})$ reference electrode and magnitude of protection current density for a dual transistor driven circuit.

the protected structure – Fig. 4. Potential of the cathode and protection current settled quickly with very high initial current and potential values. Excessive protection is not undesirable, a great part of the protection current is wasted for water decomposition reaction resulting in uneconomical anode use. Experimental data and derived anode properties are presented in Table 1.

A transistor driven circuit exhibited a high initial current due to a voltage difference between the zinc driving electrode and the steel mesh cathode – approximately $|400 \text{ mV}|$ which

Table 1
Weight loss measurement results and derived anode properties.

	Direct anode-cathode connection	Dual transistor driven
Initial weight [g]	49.90	48.38
Weight loss [g]	13.67	0.53
Estimated operating time of 1 kg anode	1.4 years	35.7 years
Theoretical anode current output [A h/kg]	2206	
Real anode current output [A h/kg]	1382	1965
Consumption rate [kg/(A·year)]	6.3	4.5
Anode efficiency [%]	63%	89%

Download English Version:

<https://daneshyari.com/en/article/7895422>

Download Persian Version:

<https://daneshyari.com/article/7895422>

[Daneshyari.com](https://daneshyari.com)