

## Regular article

## In-situ observation of an irradiation creep deformation mechanism in zirconium alloys

M. Gaumé<sup>a</sup>, P. Baldo<sup>b</sup>, F. Momprou<sup>c</sup>, F. Onimus<sup>a,\*</sup><sup>a</sup> DEN, Service de Recherches de Métallurgie Appliquées, CEA Saclay, Université Paris-Saclay, F-91191 Gif-sur-Yvette, France<sup>b</sup> Materials Science Division, Argonne National Laboratory, Argonne, IL 60439, United States<sup>c</sup> CEMES-CNRS, Université de Toulouse, 29 Rue Jeanne Marvig, 31055 Toulouse Cedex 4, France

## ARTICLE INFO

## Article history:

Received 18 April 2018

Received in revised form 16 May 2018

Accepted 19 May 2018

Available online xxxx

## Keywords:

Transmission electron microscopy

Irradiation

Creep

Zirconium

Dislocation

## ABSTRACT

We report an original experimental study on a zirconium alloy deformed in situ under ion irradiation and applied stress inside a Transmission Electron Microscope. We observe that dislocations initially pinned on irradiation defects can be unpinned and glide at a lower stress under the effect of the irradiation. It is proposed that unpinning occurs by a local effect of the displacement cascade created by the incoming ion in the vicinity of the pinning point. This novel mechanism of dislocation glide assisted by irradiation is thought to play a crucial role on in-reactor irradiation creep of zirconium alloys.

© 2018 Acta Materialia Inc. Published by Elsevier Ltd. All rights reserved.

During the early 60's, the irradiation creep, a visco-plastic deformation phenomenon occurring under small constant load and long term irradiation, was discovered on structural materials used in the first nuclear reactors [1–4]. As austenitic stainless steels and zirconium alloys became the most used structural materials for this application, many experimental results were available. Creep parameters, such as the stress exponent, the flux exponent and the irradiation creep activation energy were measured [5–11]. Based on these data, many theoretical mechanisms were proposed to explain the in-reactor behavior [12–19]. However very few microscopic experimental evidence [20] were available to assess which is the elementary deformation mechanism controlling irradiation creep. Despite recent efforts using advanced micro-scale testing devices under ion irradiation [21–25], there is still no clear knowledge and understanding of such mechanism.

As pointed out in Ref. [18], irradiation has two antagonistic effects on deformation creep. The first one is an inhibition of thermal creep mechanisms due to the creation of a high density of point defect clusters, in the form of small dislocation loops, acting as obstacles against dislocation glide and climb. This irradiation-retarded creep can be clearly evidenced when creep tests are conducted after irradiation or under a low neutron flux. It is related to the irradiation induced hardening. The second effect of irradiation is, on the contrary, to enhance, or even induce, creep. Indeed, it is often observed that under high neutron flux, the creep rate is higher than during out-of-pile tests. Many

mechanisms have been proposed to explain this surprising phenomenon and they all involve the production of vacancies and self-interstitials under irradiation. However, these mechanisms differ in their descriptions of the fate of these point defects. Some theoretical mechanisms postulate that irradiation creep is induced solely by dislocation climb due to a biased absorption of point defects by dislocations under stress. Other proposed irradiation creep mechanisms are based on an enhanced climb-glide of dislocations by absorption of point defects under irradiation [18].

In order to assess these deformation mechanisms, we performed an experimental study using in-situ ion irradiation under an applied stress inside a Transmission Electron Microscope (TEM). This technique allows the direct observation of elementary mechanisms in real-time and at the nanometer scale. Very few attempts of this kind can be found in the literature [26–29].

The experiments were performed in the Intermediate Voltage Electron Microscope (IVEM) facility at the Argonne National Laboratory [30]. An ion beam implanter is directly connected with a TEM. The ion beam can be blanked, allowing observations under and out irradiation. Irradiations were performed using 1 MeV Kr<sup>2+</sup> ions and a flux of  $6 \times 10^{14}$  ions · m<sup>-2</sup> · s<sup>-1</sup>. The final fluences ranged between 1 and  $3 \times 10^{18}$  ions · m<sup>-2</sup>.

Small tensile test specimens, with electron transparent areas, were taken out of a sheet of a recrystallized zirconium alloy referred to as Zircaloy-4. Details concerning this material and the sample preparation can be found in Supplementary data. The samples were installed on a GATAN single tilt heating and straining holder (Fig. 1). The deformation

\* Corresponding author.

E-mail address: [fabien.onimus@cea.fr](mailto:fabien.onimus@cea.fr) (F. Onimus).

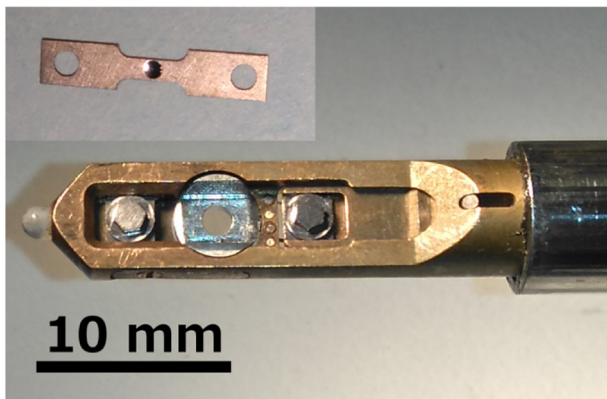


Fig. 1. Head of the heating and straining GATAN TEM sample holder. Encapsulated is shown the dog-bone shape sample used for the in situ straining experiments.

of the specimen is obtained by applying a controlled displacement of one of the grip. Observations were made in the early stages of plastic deformation by reaching a critical displacement value where first dislocation motions were noticed. During the experiment, because of the overall dislocation motion, the stress is progressively relaxed. The experiments were performed at room temperature and at temperatures ranging from 350 to 450 °C thanks to a furnace located below the sample. Samples were irradiated during several periods of few tens of seconds. When no more dislocation motion was observed, either during or out irradiation, a further slight increase of the displacement was applied. Most of the observations of dislocation motion were made after a short period of irradiation.

The motion of more than 40 dislocations in 16 different grains in several samples was analyzed. The major finding is that all the dislocations observed under applied stress were progressively pinned by the irradiation defects, when the ion beam was switched off. When the ion beam was switched on, the dislocations started to move, under irradiation, until the beam was switched off again. This stop-and-go motion was reproduced several times in all the experiments conducted.

To illustrate this phenomenon, one experiment, performed at 380 °C  $\pm$  30 °C, is described and analyzed in the following. The irradiation sequence is explained in Fig. 2 with a plot of the irradiation flux as a function of time. It is composed of irradiation periods, at constant flux of  $6 \times 10^{14}$  ions  $\cdot$  m $^{-2}$   $\cdot$  s $^{-1}$ , noted B, D, F and periods when the ion beam was off noted A, C and E. This sequence was obtained after a short irradiation period of  $0.13 \times 10^{18}$  ions  $\cdot$  m $^{-2}$ . A film showing part of this sequence, accelerated two times, is provided as Supplementary data.

To analyse this sequence, the image difference technique [31] was used (Fig. 3). The image A).a) of Fig. 3 illustrates the dislocation at a time defined as  $t = 0$  s and the image A).b) shows the same dislocation at  $t = 20$  s. The image difference a)–b) exhibits a uniform grey contrast

proving that the dislocation did not move between these two images, pinned by small irradiation loops. The images B).a) and B).b) show the glide of the dislocation under irradiation. The dislocation moves by successive rapid jumps and stops, presumably due to the pinning and unpinning of the dislocation, under the combined effect of stress and irradiation. During this period (B) the dislocation mean velocity is 17 nm  $\cdot$  s $^{-1}$ . After 18 s, the irradiation beam is switched off (C). The images difference C).a) shows that the dislocation still glides, during 49 s at a lower mean velocity of 8 nm  $\cdot$  s $^{-1}$ . Then, the dislocation stops as illustrated by the image difference on fig. C).b). The ion beam is left off during 68 s to make sure that the dislocation is stopped. As soon as the second irradiation period (D) starts the dislocation almost instantaneously glides (images difference D).a)). When the beam is again switched off the dislocation stops again (Fig. 3.E), and so on. During the irradiation periods, the dislocation motion occurs by successive fast jumps interrupted by longer stops. The waiting time ( $t_w$ ) was analyzed for 9 stops. It ranges from 1 to 11 s, with a mean waiting time of 6 s. Comparatively, the jumping time was very short, less than the time between two frames, i.e. 0.1 s.

The crystal orientation of the grain was determined using electron diffraction. Based on the slip traces left by the dislocations on the surface, the glide plane was found to be the (01 $\bar{1}$ 1) pyramidal plane, the Burgers vector of the dislocation being  $\mathbf{b} = 1/3[2\bar{1}10]$ . The gliding dislocation observed has thus a screw character. More details can be found in Supplementary data.

Experiments performed at room temperature show similar results except that a lower dislocation velocity of 2 to 4 nm  $\cdot$  s $^{-1}$  was measured. This observation indicates that the deformation mechanism is only slightly thermally activated and does not require a high point defect mobility, in agreement with the low activation energy often measured for irradiation creep behaviours. A film showing the dislocation motion at room temperature, accelerated two times, can be found in the Supplementary data.

The role of irradiation on dislocations originally gliding in unirradiated samples was also investigated at temperatures ranging from 350 to 450 °C. For that purpose, the sample was first strained prior to irradiation and dislocation motion was observed. During the dislocation motion, the ion beam was switched on. Irradiation defects appeared in the specimen and the dislocation progressively stopped. To compensate for the possible stress relaxation, the displacement was increased. But despite this stress increase the dislocation did not glide again. For a high enough applied displacement without the ion beam, new dislocations, presumably originating from grain boundaries, were observed to glide, with difficulty, through the irradiation defects. The observation of the pinning of originally gliding dislocations results from their interaction with irradiation defects and may explain the irradiation induced hardening and the irradiation-retarded creep previously described. It is believed that initial dislocations were pinned by large jogs formed during a long time irradiation after they stopped. On the contrary, new dislocations formed at grain boundaries are presumably less jogged

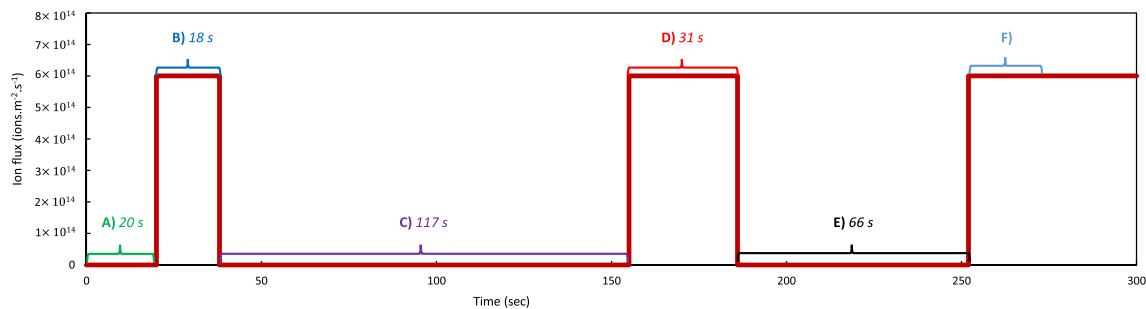


Fig. 2. Irradiation steps during the in-situ irradiation experiment using 1 MeV Kr $^{2+}$  ion at a temperature of 380 °C  $\pm$  30 °C.

Download English Version:

<https://daneshyari.com/en/article/7910554>

Download Persian Version:

<https://daneshyari.com/article/7910554>

[Daneshyari.com](https://daneshyari.com)