



Mechanical property improvement induced by nanoscaled deformation twins in cold-sprayed Cu coatings

Yan Feng^a, Wenya Li^{a,*}, Chaowei Guo^b, Mingjie Gong^a, Kang Yang^a

^a State Key Laboratory of Solidification Processing, School of Materials Science and Engineering, Northwestern Polytechnical University, Xi'an 710072, PR China

^b School of Material Science and Engineering, Xi'an Jiao Tong University, Xi'an 710049, PR China



ARTICLE INFO

Keywords:

Deformation twin
Nanotwins
Hardness
Cold spray

ABSTRACT

Nanoscaled deformation twins have been observed in cold sprayed Cu coatings and the coating hardness has been improved by this kind of tiny twins. Strain rate up to 10^9 s^{-1} at the impact interfaces can be achieved at the cold spray process, and the maximum shearing compressive stress and tensile stress are 392 MPa and 397 MPa, respectively, obtained from impacting simulations. They are larger than the required shearing stress for the formation of deformation twins in Cu. The orientation relationship between the stripes can be determined to be $(11\bar{1})_M \parallel (11\bar{1})_T$ and $(\bar{1}10)_M \parallel (101)_T$ both in coatings prepared by cold spray Cu particles annealed at 700 °C and 250 °C, respectively. The hardness of the coatings is higher than that of the corresponding substrates which indicates the improvement by the work hardening effect in the cold spray process. Though the misorientation of the deformation twins in the coatings slightly deviates from 60°, the existence of nanoscaled deformation twins improves its hardness significantly.

1. Introduction

Nanoscaled twins have been widely investigated due to their specific effect on simultaneously improving strength and ductility. Studies showed that the strength, ductility and work hardening of nanotwinned Cu (nt-Cu) are influenced by the twin lamellar thickness (λ). For example, the yield strength of such nt-Cu first increases as twin thickness decreases [1,2], reaching a maximal strength of 900 MPa at $\lambda \approx 15 \text{ nm}$. Interestingly, a pronounced increment in tensile uniform ductility and work hardening is observed in nt-Cu with monotonically decreasing λ [3]. Up to now, severe plastic deformation and pulse electrolytic deposition are the most effective methods to obtain nanoscaled twins or lamellas in Cu.

It is worth noting that, cold spray is a kind of low-temperature solid-state coating process in which spray particles undergo extensive plastic deformation at extremely high strain-rates (up to 10^9 s^{-1} at impact interfaces) [4]. Coatings of soft metallic materials, such as copper, aluminum, titanium and metal matrix composites can be easily formed using the cold spray technique [5–10]. Cold sprayed coatings have been well studied due to the advantages in mechanical properties, corrosion resistance, electronic as well as thermal conductive properties [11,12]. The increase in strength and hardness is attributed to the work hardening effect or grain refinement which is introduced in the cold spray process [13–15]. It is well known that deformation temperature, strain

rate, grain size as well as alloying elements are the factors that influence the work hardening effect. Generally, the increase of dislocation density and the tangling of the dislocations cause the work hardening in cold spray. However, there are evidences that the deformation twins improve the mechanical property not only in hcp metals [16–18] in which the slip systems are limited, but also in fcc polycrystals in which the slip systems are more and dislocation motion can easily occur [19–21]. In cold sprayed Cu coatings, the exterior of the deposited Cu particles experiences extensive deformation, while the slight deformation in the interior of particles, which is due to the localized deformation and adiabatic shear instability occurring in the cold spray process. Therefore, the strain rate at the edge of each particle is larger than that in the center of it. As a result, there would be deformation twins in large deformed zone and sometimes dynamic recrystallization in small deformed zone. Therefore, the appearance of deformation twins in the cold sprayed Cu coatings may lead to the increase of hardness especially when the twins are in nanoscale. In this paper, the microstructure of cold sprayed Cu coatings was observed as well as the nanoindentation was performed in order to evaluate the coating mechanical properties, and the effect of nanoscaled deformation twins on the improvement of hardness was discussed.

* Corresponding author.

E-mail address: liwy@nwpu.edu.cn (W. Li).

2. Material and methods

A spherical gas-atomized Cu powder ($-120 + 150$ mesh, LERMPS Lab, France) was selected as the original material. To investigate the influence of grain size on the microstructure and mechanical property of the coating, two kinds of heat treatments were performed on the original powder. One is annealed at $700\text{ }^{\circ}\text{C}$ for 24 h in vacuum in order to relieve the residual stresses and get as larger as possible grain size. The other one is annealed at $250\text{ }^{\circ}\text{C}$ for 24 h in vacuum in order to relieve the residual stresses. These two kinds of powders are deposited onto the Cu substrate by cold spraying. The used spray nozzle had an expansion ratio of about 4.9 and a divergent section length of 170 mm. High compressed air was used as the accelerating gas at a pressure of 2.8 MPa and temperature of about $550\text{ }^{\circ}\text{C}$, while argon was used as powder carrier gas at a pressure of 3.0 MPa and flow rate of 40 L/min. The standoff distance from the nozzle to the substrate surface was 30 mm. The transverse speed of spray gun was 100 mm/s for coating deposition. Finally, coatings about $200\text{ }\mu\text{m}$ were fabricated by cold spraying method described above with powders annealed at $700\text{ }^{\circ}\text{C}$ and $250\text{ }^{\circ}\text{C}$ for 24 h, respectively.

Microstructures of the powder and coatings were examined with an Optical Microscope (OM) (OLYMPUS GX71, Japan). Orientations of twins were investigated by Electron Backscattered Diffraction (EBSD) and Transmission Electronic Microscopy (TEM) techniques. EBSD samples were polished by both mechanical and vibrating methods and carried out at room temperature by using the Scanning Electron Microscopy (SEM, TESCAN MIRA3 XMU) equipped with an EBSD detector (Oxford Nordlys). The scanning step size was chosen to be $0.6\text{ }\mu\text{m}$ and $0.05\text{ }\mu\text{m}$ for substrates and coatings, respectively. TEM observation and Selected Area Electron Diffraction were conducted on FEI Tecnai F30 equipment. Microhardness of both coatings and substrates were tested in-situ by a Hysitron PI 87 indenter equipped on FEI Helios 600 SEM, in which the loading was constant for each point ($2000\text{ }\mu\text{N}$) and the displacement was measured for comparing the hardness.

3. Results and discussion

Fig. 1 shows the cross-sectional microstructure of original particles and particles annealed at $700\text{ }^{\circ}\text{C}$ and $250\text{ }^{\circ}\text{C}$ for 24 h. It is obvious that annealing at $700\text{ }^{\circ}\text{C}$ and $250\text{ }^{\circ}\text{C}$ for 24 h results in the difference in grain size of the Cu particles. The grains of the particle annealed at $700\text{ }^{\circ}\text{C}$ for 24 h penetrate across it since they grow as large as possible, while the grains in the particle annealed at $250\text{ }^{\circ}\text{C}$ for 24 h are still with the same size as the original ones. Nevertheless residual stresses could be released due to both kinds of annealing. It can be seen that the grain boundaries of Sample-700 are not so clear comparing with that of Sample-250 due to the obvious growing up of grains at the annealing process, as described in our previous work [22]. Besides the difference in grain size, there are some stripe-like microstructures in the interiors

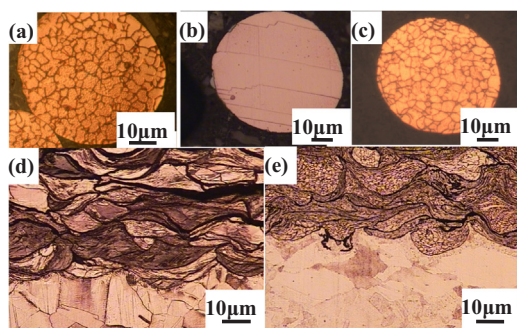


Fig. 1. Cross-sectional microstructure of original Cu particles (a) and particles annealed at $700\text{ }^{\circ}\text{C}$ (b) and $250\text{ }^{\circ}\text{C}$ (c) for 24 h, as well as the micrographs of the coatings deposited with the particles annealed at $700\text{ }^{\circ}\text{C}$ (d) and $250\text{ }^{\circ}\text{C}$ (e).

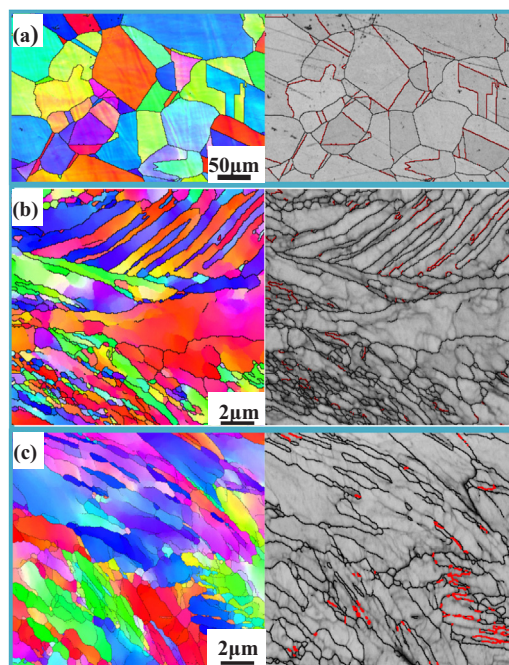


Fig. 2. Inverse Pole Figure (IPF) images and the corresponding grayscale images with large-angle grain boundaries (red lines) identified as the boundaries of misorientation angle equals to $60 \pm 5^{\circ}$ of the substrate (a) and the coatings in Sample-700 (b) and Sample-250(c).

of grains. The stripes exist both in Sample-700 and Sample-250, which are proved to be deformation twins by using EBSD and TEM as follows.

EBSD orientation contrast and the corresponding grain boundaries of substrates and coatings are shown in Fig. 2. As similar to most of the annealed Cu, the grains of substrates are equiaxed. In order to identify the characteristics of the grain boundaries, we used grayscale image to show the grain boundaries including the high-angle grain boundaries as well as the twin boundaries for the substrates. The red lines in the grayscale images indicate the boundaries of misorientation angle of 60° , which are considered to be twin boundaries. It is observed that the twin boundaries of the substrates are straight, and distributed not only in the large grains, but also interior of some small grains as shown in Fig. 2(a). In addition, the twins observed in the Cu substrates are represented as $60^{\circ} < 111 >$, that is a 60° rotation about $< 111 >$ axes with the $\{111\}$ twinning plane. The EBSD orientation contrast and corresponding grain boundaries of the cold-sprayed coatings in Sample-700 and Sample-250 are demonstrated in Fig. 2(b) and (c). It is interesting that the stripes of coatings observed in Fig. 1 are also seen in the orientation contrast images, and the orientations of these stripes can be observed from the difference in color. After analyzing, the boundaries of misorientation angle of 60° are indicated with red lines in the corresponding grayscale images. These red lines are not so straight and uncontinuous comparing with those twin boundaries in substrates. As being analyzed by Channel 5 software, it is revealed that the misorientation angle of the uncontinuous part of boundaries is slightly deviated from 60° due to the orientation variation in a stripe.

Stripes in the cold-sprayed coatings can also be evaluated by TEM, and misorientation between these stripes can be confirmed by the Selected Area Electronic Diffraction (SAED). Fig. 3(a) and (b) are the bright field images of the stripes in Sample-700 and Sample-250, respectively. It is clearly observed that the stripes are inhomogeneous in thickness with dimension of several nanometers to hundreds of nanometers. Interfaces of the stripes are relatively straight as shown in the images due to the comparatively local area, thus the stripes appear as plate-like in TEM images.

Corresponding SAED around the interface of stripes is inserted in

Download English Version:

<https://daneshyari.com/en/article/7972101>

Download Persian Version:

<https://daneshyari.com/article/7972101>

[Daneshyari.com](https://daneshyari.com)