

Effects of grain size on plastic deformation in a β CuAlBe shape memory alloy

S. Montecinos^{a,b,*}, A. Cuniberti^{a,b}

^a Instituto de Física de Materiales Tandil-IFIMAT, Facultad de Ciencias Exactas, Universidad Nacional del Centro de la Provincia de Buenos Aires, Argentina

^b CONICET, Argentina

ARTICLE INFO

Article history:

Received 5 December 2013

Received in revised form

7 February 2014

Accepted 8 February 2014

Available online 15 February 2014

Keywords:

Mechanical characterization

Strain measurement

Shape memory alloys

Martensitic transformations

Plasticity

ABSTRACT

The effects of grain size on the deformation under compression of a β Cu–11.4Al–0.5Be (wt%) polycrystalline shape memory alloy were analyzed. As the maximum stress increases, major levels of pseudoelastic strain are obtained and the strain retained on unloading increases. The plot retained strain versus applied strain gives a unique curve that is independent of the grain size, with a pure pseudoelastic behavior up to around 3% of applied strain. The largest pseudoelastic strain possible to obtain increases as the grain size increases. Surpassed that strain, plastic deformation occurs and the macroscopic plastic stress follows a Hall–Petch type relation.

In samples with plastic deformation the reverse martensitic transformation occurs in two stages, with a second high temperature calorimetric peak associated to the transformation of plastic deformed martensite.

© 2014 Elsevier B.V. All rights reserved.

1. Introduction

The CuAlBe alloys, based on the CuAl system, are receiving high attention, because they exhibit shape memory properties due to a thermoelastic martensitic transformation. Small additions of Be on the Cu–11Al (wt%) system produce an important lowering of the martensitic transformation critical temperature [1], which allows a larger temperature range at which the shape memory effect is operative. In CuAlBe shape memory alloys, the β phase is stable at temperatures higher than 870 K [1], but it can be retained at lower temperatures by rapid cooling [2]. Upon quenching, the metastable β phase becomes ordered and then transforms to 18R martensite [3]. However, the martensitic transformation can also be induced by the application of mechanical stress, producing the pseudoelastic effect. Under appropriate conditions, when the load is removed, the deformation is almost completely recovered and a hysteretic loop is formed, which is associated with energy dissipation. Because of these properties, the use of CuAlBe alloys as passive dampers of seismic energy is highly promising [4,5].

Studies about the pseudoelastic effect of CuAlBe alloys have been reported [6–13]. In a previous work we analyzed the deformation of a CuAlBe polycrystalline alloy with a grain size of 0.5 mm [6]. Compression cycles up to increasing loadings at room temperature

were carried out, and a macroscopic plastic limit of around 600 MPa was determined. Such determination was performed through a direct and precise evaluation of the involved deformations, achievable under compression tests. It has been found in CuAlBe alloys that the pseudoelastic behavior is affected by the grain constraint [7], so the martensite-start stress, the pseudoelastic slope and the stress hysteresis decrease as the grain size increases [7,14]. It is well known that in the single phase metallic alloys, the yield stress decreases as the grain size decreases due to the grain boundaries are important obstacles to slip, and the relationship of the yield stress with the grain size is often expressed by the Hall–Petch relation [15,16]. Studies on the relationship between the grain size and the plastic limit in shape memory alloys are scarce, possibly due to the difficulties introduced by the overlapping of pseudoelastic strain and plastic strain. Paradkar et al. [17] has demonstrated the validity of the Hall–Petch relationship for a two phase TiAlNb shape memory alloy, while Khan et al. [18] deformed CuAl in martensitic state and also found it follows that relationship.

In the present work, we study the effects of grain size on the deformation of a β Cu–11.4Al–0.5Be (wt%) polycrystalline alloy. Samples were subjected to compression cycles at room temperature. The influence of the grain size on the strain components and the plastic limit was analyzed.

2. Experimental procedure

A β Cu–11.4Al–0.5Be (wt%) polycrystalline alloy was used in the present work. The chemical composition was determined by

* Corresponding author at: Instituto de Física de Materiales Tandil-IFIMAT, Facultad de Ciencias Exactas, Universidad Nacional del Centro de la Provincia de Buenos Aires, Argentina. Tel.: +54 249 443 9670; fax: +54 249 4439 679.

E-mail addresses: dmonteci@exa.unicen.edu.ar, dmonteci@hotmail.com (S. Montecinos).

atomic absorption spectrophotometry. Cylindrical samples around 5.1 mm diameter and 14.3 mm length were prepared for compression tests, with a length/diameter ratio ~ 2.8 . The grain size in the as-received specimens was 0.05 mm. To obtain different grain sizes, samples were kept in a resistance furnace at 1073 K for different times and water quenched at room temperature. For light optical microscopy observations, the samples were electropolished in a saturated solution of chromium trioxide in phosphoric acid at 4 V, and immersed for a few seconds in a solution of ferric chloride in order to reveal the microstructural details. Mean grain size (d) was estimated by an area analysis method from optical micrographs [19]. The area of each grain was determined using the software Image Tool 3.0, and the diameter of each grain was estimated as the diameter which would correspond to the measured grain area if they had a circular form. d was obtained as the average value for each sample, considering at least three micrographs. The frequency distributions of the grain size/mean grain size obtained for the different thermal treatment times are essentially similar, with a departure of around ± 1 from the maximal frequency point. Compression tests were performed with a Shimadzu Autograph-DSS-10T universal testing machine at room temperature, and a constant cross-head speed of 1 mm/min. The end faces were covered with a thin Teflon film and lubricated with grease in order to reduce the friction. The stress–strain curves were registered with (i) the paper recorder of the testing machine, (ii) a high-speed digital acquisition system, and the length of the samples in each condition was also measured with a precision digital caliper, $\Delta = 5 \times 10^{-3}$ mm.

From samples subjected to compression, small discs of around 1 mm thick and mass of ~ 200 mg were cut. Calorimetric measurements were performed with a Rheometric DSC calorimeter at 10 K/min.

3. Results and discussion

Representative stress–strain (σ – ϵ) curves of samples with different grain sizes are shown in Fig. 1. The first linear part in the loading curve corresponds to the elastic regime of the β phase. The linearity deviation is associated with the beginning of the martensitic transformation, and the stress at this point will be referred hereafter as the martensite-start stress (σ_s). Then, the martensitic transformation progresses, however, other deformation mechanisms could act as will be discussed. A hysteretic loop is formed on removing the load. For cycles at low maximum stresses the strain is almost fully recovered leading to the pseudoelastic (PE) behavior. For a sample with a mean grain size of 0.5 mm, a pure pseudoelastic behavior has been obtained up to around

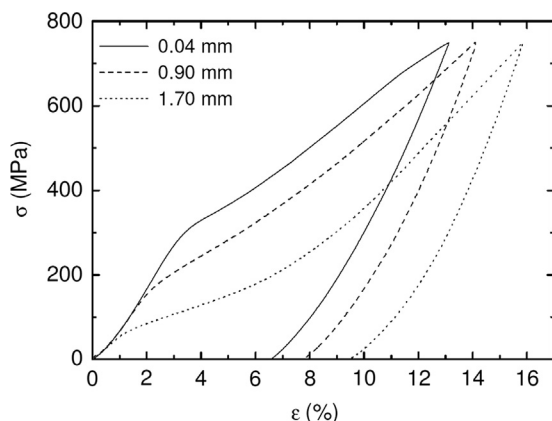


Fig. 1. Stress–strain curves for samples in the β phase with different grain sizes subjected to single cycles of compression.

300 MPa [6]. The grain size of the samples modifies the stress–strain cycles. σ_s decreases as the grain size increases, as we reported in previous works [7,14]. Beyond σ_s , two hardening stages are observed, more marked in the samples with high grain size. This could be understood considering that the largest grains will transform first at lower loads, while the smaller grains do at higher loads [20].

Micrographs of samples with different grain sizes obtained at room temperature after a single cycle of compression at 750 MPa are shown in Fig. 2. A large amount of martensite plates are observed in the samples, which could correspond to retained and/or plastically deformed martensite. In the samples with small grain size a fine network of martensite plates inside each grain is observed (Fig. 2a), while in those with high grain sizes, large martensite plates forming a grid network can be appreciated (Fig. 2b). It is interesting the observation reported on that point for martensitic CuAl and CuAlZn alloys by Khan et al. [18], who note that the martensite plate thickness (d_{mart}) increases for larger grain sizes, and propose an empirical relationship according to which d_{mart} is proportional to $d^{1/3}$.

To analyze the deformation processes occurring under loading, repeated cycles up to increasing levels of maximum stress (σ_m) in samples with different grain sizes were carried out. With the purpose of distinguish the reversible and irreversible deformation processes, samples were kept for 30 s in a resistance furnace at 1073 K after each cycle, reaching a temperature of around 550 K, and water quenched. For the analysis of the curves, the same methodology explained in reference [6] was used. The maximum strain can be considered as

$$\epsilon_{\text{max}} = \epsilon_{\text{el}} + \epsilon_{\text{ps}} + \epsilon_{\text{pl}} \quad (1)$$

where ϵ_{el} is the elastic deformation of the β phase, ϵ_{ps} is the pseudoelastic strain produced by the stress-induced martensite, and ϵ_{pl} is the strain associated with plastic deformation. The sum of the last two strains will be considered hereafter as the total applied strain (ϵ_{app}). The contributions to the maximum strain are indicated in Fig. 3a. On removing the loading, the induced martensite could not completely revert to the β phase, leaving retained strain (ϵ_{ret}). The strain associated to retained martensite is reversible under the flash heating, whereas if some plastic deformation takes place it is not recoverable, so, ϵ_{pl} will be considered as the measured strain after flash heating, ϵ_{TT} . Representative measured strains obtained for samples with grain sizes of 0.04 mm and 2.20 mm are shown in Fig. 3b. The stress levels needed to induce the martensite transformation and consequently ϵ_{app} decrease as the grain size increases. For all the specimens, as σ_m increases, major levels of ϵ_{ps} are obtained, and ϵ_{ret} increases. A high recovery is produced by the heat treatment with ϵ_{TT} values lower than 0.5% up to a certain stress level, above which ϵ_{TT} increases.

The retained strain levels depend on both the maximum stress and the grain size of the samples (Fig. 3b). However, it was found that the plot ϵ_{ret} versus ϵ_{app} for the samples with different grain sizes gives a unique curve that is independent of the grain size, as can be seen in Fig. 4a. This $\epsilon_{\text{ret}} - \epsilon_{\text{app}}$ relationship is an interesting resource for the estimation of the expected retained strain after applying certain total strain in samples with any grain size. For ϵ_{app} lower than around 3%, ϵ_{ret} is almost zero and a pure pseudoelastic behavior with closed cycles is obtained. For higher ϵ_{app} , ϵ_{ret} continuously increases. The maximum strain associated to the stress-induced martensite that is reversible by unloading and heating (ϵ_{ps} limit) is shown in Fig. 4b. As the grain size increases, ϵ_{ps} limit also increases, from $\sim 6\%$ up to around 9% for the highest grain size. This last value is comparable with the deformation of 9.7% product of the formation of a single martensitic variant with a Schmidt factor of 0.482 reported on a CuAlBe single crystal [8].

Download English Version:

<https://daneshyari.com/en/article/7981232>

Download Persian Version:

<https://daneshyari.com/article/7981232>

[Daneshyari.com](https://daneshyari.com)